

# Refractory metals as structural materials for fusion high heat flux components

David Hancock <sup>a, b, \*</sup>, David Homfray <sup>a</sup>, Michael Porton <sup>a</sup>, Iain Todd <sup>b</sup>, Brad Wynne <sup>a, b</sup>

<sup>a</sup> Culham Centre for Fusion Energy, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK

<sup>b</sup> University of Sheffield, Department of Materials Science and Engineering, Sir Robert Hadfield Building, Mappin Street, Sheffield, S1 3JD, UK

## ARTICLE INFO

### Article history:

Received 22 June 2018

Received in revised form

24 September 2018

Accepted 25 September 2018

Available online 29 September 2018

### Keywords:

Fusion

High heat flux

Divertor

Materials

Refractory

## ABSTRACT

Tungsten is the favoured armour material for plasma facing components for future fusion reactors, but studies examining the use of tungsten or other refractory metals in the underlying cooled structures have historically excluded them, leaving current concepts heavily dependent on copper alloys such as copper chrome zirconium. This paper first outlines the challenge of selecting an appropriate alternative material for this application, with reference to historical selection methodology and design solutions, and then re-examines the use of refractory metals in the light of current design priorities and manufacturing techniques.

The rationale for considering refractory alloys as structural materials is discussed, showing how this is the result of relatively small changes to the logic previously applied, with a greater emphasis on high temperature operation, a re-evaluation of current costs, a relaxation of absolute activation limits, and the availability of advanced manufacturing techniques such as additive manufacturing. A set of qualitative and quantitative assessment criteria are proposed, drawing on the requirements detailed in the first section; including thermal and mechanical performance, radiation damage tolerance, manufacturability, and cost and availability. Considering these criteria in parallel rather than sequence gives a less binary approach to material selection and instead provides a strengths and weaknesses based summary from which more nuanced conclusions can be drawn.

Data on relevant material properties for a range of candidate materials, including elemental refractory metals and a selection of related alloys are gathered from a range of sources and collated using a newly developed set of tools written in the python language. These tools are then used to apply the aforementioned assessment criteria and display the results. The lack of relevant data for a number of promising materials is highlighted, and although a conclusive best material cannot be identified, refractory alloys in general are proposed as worthy of further investigation.

© 2018 Published by Elsevier B.V.

## 1. Introduction

### 1.1. The divertor problem

Energy from controlled nuclear fusion promises clean, safe, and abundant electricity and significant advances have been made in recent history, particularly in the field of magnetic confinement fusion, employing the tokamak reactor design. Significant technical challenges remain, however, and commercial viability has yet to be

proven. One of the most significant challenges faced by designers of fusion power plants, whatever the technology used, will be extracting heat and exhaust gasses efficiently.

For the tokamak concept, a core element of the power exhaust system is the divertor, where magnetic field lines are directly incident on a region of the vessel wall (the divertor target) and which is subject to steady state heat fluxes in the form of radiation and high energy particles in excess of  $10\text{MW m}^{-2}$  with excursions due to off-normal events producing transient loads an order of magnitude higher. There is currently no divertor target design suitable for use in a demonstration fusion power plant, either due to insufficient heat handling capability, thermal efficiency, or component lifetime [1]. Significant effort is being spent reducing the heat and particle fluxes incident on the target by adapting the

\* Corresponding author. Culham Centre for Fusion Energy, Culham Science Centre, Abingdon, Oxon, OX14 3DB, UK.

E-mail address: [david.hancock@ukaea.uk](mailto:david.hancock@ukaea.uk) (D. Hancock).

plasma geometry, e.g. Refs. [2,3], but engineering requirements still exceed capability. When compared to designs used for ITER and other current machines, peak incident heat flux, surface material erosion, irradiation damage, and required coolant efficiency are all likely to be higher, in some cases considerably [4].

### 1.2. Divertor target state of the art

Away from exposed liquid or vapour-based proposals [5,6] which have a number of significant outstanding technical and physics challenges, leading concepts broadly fall into two categories: water cooled pipes in tungsten monoblocks similar to the design used for ITER [7] and helium cooled thimbles or pipes employing jet impingement [8].

Fig. 1 shows two example divertor target designs: one ITER-like and the other a helium-cooled alternative. The former consists of a water cooled CuCrZr pipe with twisted tape insert surrounded by tungsten “monoblocks” as armour and steel mounting blocks as mechanical support. The other uses a tungsten laminate pipe with Eurofer steel connections and perforated cartridge insert in place of the copper elements.

A third, high pressure cascade jet impingement concept [11] draws on elements of both of these with a focus on thermal efficiency as well as high performance, but has yet to be fully tested in a representative environment or a manufacturing route proven.

### 1.3. Why focus on the structural material?

As shown above, the fundamental elements of these and other divertor target concepts can broadly be divided into the following sub-components: coolant, armour, cooled structure, and mechanical support.

Pure tungsten or possibly an alloy thereof with additions for ductility or self passivation are generally understood to be the sole candidates for the armour material due to its high melting point, high sputtering resistance, vacuum compatibility, and reasonable resistance to irradiation damage [12], though alternatives including other refractory metals have been considered [13].

The supporting substructure is assumed to be steel, in keeping with divertor cassette designs for ITER [7] and the current DEMO baseline for first wall components, although the design is still evolving and alloys based on zirconium, chromium, and vanadium have also been discussed [14].

Leading candidate coolants include water and helium, with supercritical CO<sub>2</sub>, liquid metals, and molten salts considered for more advanced concepts [15]. Hydrogen is used for cooling turbine generators due to its higher thermal conductivity and specific heat, but it has historically been discounted for fusion applications because of embrittlement concerns [16].

Between the armour and mechanical support, the cooled structural material must be joined to the armour and compatible with the chosen coolant, while containing coolant pressure and conducting heat away from the armour. The choice of this material has the largest impact on overall component performance, driving operational temperature, heat flux handling capability, and integration with surrounding interfaces.

Armour material choice is therefore relatively fixed and (beyond facilitating the choice of plasma geometry) the supporting substructure does not have a significant impact on performance of the plasma facing components, but the selection of coolant and the material for the cooled structure remain much more open to innovation and as such provide a potentially strategic avenue to improvements in performance from current designs. In addition, advanced manufacturing techniques, including additive manufacturing (AM), may allow both the use of materials formerly difficult to form and the production of optimised geometries which further enhance performance.

## 2. Structural material selection process

The interfaces between the cooled substructure, the surrounding subcomponents, and the operating environment lead to a raft of somewhat conflicting selection criteria.

Recent material selection processes have focused strongly on thermal conductivity and the avoidance of brittle materials, maximising heat handling capability and ease of fabrication [17,18]. In addition, a conservative approach to manufacturing risk and the costs of qualifying new materials have further restricted the range of options considered, leading to a narrow reliance on copper alloys such as CuCrZr for water cooled designs and tungsten for higher temperature helium cooled concepts. Refractory alloys other than tungsten have historically featured prominently in attempts to design higher power density concepts, but have ultimately been sidelined due to a strict adherence to activation limits or concerns about hydrogen compatibility [19,20]. In addition, these studies have tended to make decisions based on performance at a single temperature point, rather than evaluating performance at a range of operating conditions.

As detailed in section 6, radiation by the high energy neutrons produced by fusion causes a wide range of damage effects. The scale and nature of these effects is in many cases specific to neutron fluence and energy spectrum. It may be, in some cases, possible to partially extrapolate trends from existing fission-based data, but the lack of a fusion specific (i.e. 14 MeV) neutron source means that there is almost no data at relevant damage levels for the materials under consideration. In an ideal case, a rigorous material selection process would compare both irradiated and unirradiated properties

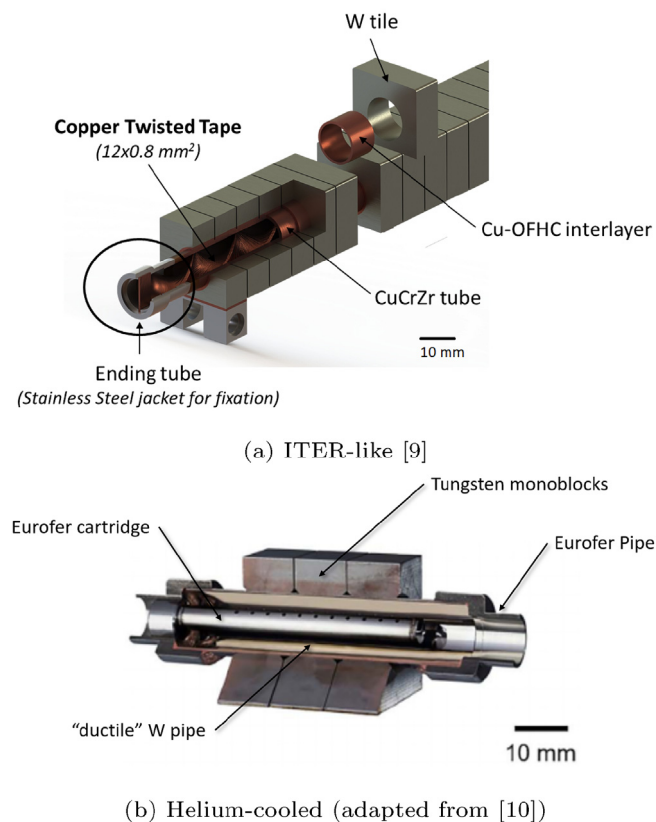


Fig. 1. ITER-like and Helium cooled divertor target designs [9].

for all the materials under consideration, giving manufacture to end-of-life performance. The collection of neutron irradiated data for all candidate materials is, however, both cost and time prohibitive if commercial fusion is to be achieved, and so strategic pre-selection is required to direct targeted irradiation campaigns.

A fresh approach to material selection is needed which allows a continuous re-assessment of material options based on current knowledge, technologies, and revised priorities while still seeking to learn from the large volume of relevant historical research. In the absence of an “ideal” material and complete data, a more parallel strengths and weaknesses based approach is proposed.

An initial downselection is still useful, enabling a subset of candidate elements with broadly attractive properties to be compared. After a brief examination of the historical interest in and key attributes of alloys based on these elements, each requirement is examined in turn and rather than rejecting any candidates which “fail,” either on the basis of lack of data or less than ideal performance, all the materials are retained throughout. This then leaves a greater number of possible candidates from which a selection can ultimately be made based on a pragmatic choice with carefully considered compromises. This choice can either be taken immediately or, if gaps in knowledge about more promising materials are identified, can feed into irradiation campaigns and alloy development programmes.

Divertor structural material requirements have been, for this paper, grouped into five distinct but inter-related categories: thermomechanical performance, radiation damage tolerance, compatibility with operational environment (including coolant), manufacturability (incorporating forming processes and joining to armour and support substructure and pipework), and price and availability.

Despite their exclusion by the preliminary selection, current preferred structural materials including copper, CuCrZr and stainless steel 316LN (in the absence of extensive data for EUROFER) are included at each stage, giving a clearer comparison with the baseline.

### 3. Preliminary downselection

Fig. 2 shows a flowchart for one approach to a high level downselection method with a particular emphasis on high temperature divertor operation, using a coolant operating at an

arbitrary nominal bulk temperature of 600 °C, which leads to refractory metals as candidate materials.

As detailed in Section 1.1, improved thermofluid efficiency will be required for commercial fusion power plants over current concepts. Selecting a coolant temperature above that achievable by the baseline concepts introduces an inherent improvement over current water-cooled baseline. This temperature is also selected to highlight the effect of altered design priorities on the core palette of materials.

The process used in this case begins with mechanical strength at high temperature as well as high thermal conductivity, before applying further restrictions based on activation and then availability, cost and mechanical performance under irradiation.

Melting point is used as a simple metric for high temperature operation. 2000 K (1726 °C) is chosen as a convenient threshold by taking onset of significant creep at 30% of melting point and aiming for a 600 °C coolant. Thermal conductivity is considered at room temperature as a first step. “Low” activation materials are considered to be those for which activation levels are below thresholds as defined in Section 6. “Availability, cost and irradiation performance” is a more qualitative filter, enabling a pragmatic exclusion of particularly rare or costly elements or those particularly vulnerable to neutron damage.

The significant difference between this and previous methods is to allow the low ductility of chromium, and moderate thermal conductivity of vanadium, while excluding copper and steel on the basis of their lower melting points. Allowing molybdenum despite its less than favourable activation leaves it as a possible additional candidate and is retained for reasons highlighted later in this paper. It is notable at this stage that such a high-temperature focussed approach naturally lends itself to the refractory metal elements and excludes “traditional” materials including CuCrZr and steels which would otherwise remain the baseline beyond ITER.

A reduced initial threshold temperature would significantly widen the scope of the study, and so focussing on refractory metals as a group gives focus to the exercise and facilitates obtaining comparable data.

### 4. Overview of refractory metals

#### 4.1. Tungsten

With tungsten as the primary candidate for plasma facing armour, including cooling directly would be an attractive option, rather than relying on joints which have historically been the location for part failures under testing, as well as reducing the number of joints to qualify. Tungsten's inherent brittleness has thus far, however, excluded it from consideration as a structural material, particularly as the ductile to brittle temperature of traditionally manufactured bulk material is raised above 800 °C under neutron irradiation. More recently, however, cold rolled and thin laminated material, as used in the concept shown in Fig. 1b above, has demonstrated more ductility and toughness than conventional tungsten. Attempts to introduce alloying elements such as Tantalum to increase ductility have shown additional surface modification effects under ion irradiation [21] and no suitable alternative has been discovered. High temperature helium-cooled jet impingement concepts such as the HEMJ design do employ tungsten doped with 1 wt% La2O3 (WL10) as the impingement surface, though this is supported by a steel substructure [22] and this design requires an enormous number of steel to tungsten welds and a further joint between the tungsten alloy and pure tungsten armour.

Conductivity > 30 MW/m.K & melting point > 2000 K

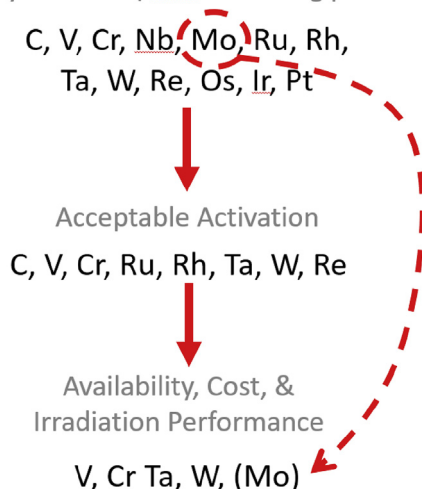


Fig. 2. Material downselection flowchart.

#### 4.2. Molybdenum

Molybdenum and its various alloys are used in a range of high temperature structural applications, due to their high thermal conductivity, high strength, and low thermal expansion. TZM (0.5% Ti, 0.08% Zirconium, balance Mo) is one of the most commonly used Mo alloys; its additions of titanium and zirconium act to increase strength and raise the recrystallization temperature. However, TZM in particular is not optimised for use under irradiation and the limited, exploratory irradiation experiments to date have raised concerns over embrittlement [23]. Various developmental alternatives have been proposed to mitigate these effects but are far from commercialisation. It is also important to note that traditional Mo alloys would be suitable only in selected high heat flux locations within a fusion power plant; elsewhere the higher neutron fluxes bring its activation above the permanent disposal waste (PDW) radiological dose limit. Mitigation options for this are discussed in section 6.

#### 4.3. Tantalum

Tantalum has been discussed for fusion applications for more than 20 years [24], and is an attractive prospect for high temperature applications due to its high ductility and corrosion resistance when compared to other refractories, as well as having similarly high strength and melting point. A number of tantalum alloys were developed in the 1960's for space reactor applications, chief among them T-111 (8% W, 2% Hf, < 100 ppm O, < 50 ppm C, < 50 ppm N, < 10 ppm H) [25] which has been frequently proposed for fusion applications, most recently as a replacement for WL10 in the helium-cooled HEMJ design discussed above. A variant, T-222, with 10 wt% W and 2.5 wt% Hf, has superior mechanical strength, though available data is less comprehensive [26]. A range of tantalum-tungsten alloys is more readily available, with tungsten percentages ranging from 2.5% (Tantaloy 63) to 10% (Tantaloy 60) with increasing hardness and yield strength and decreasing ductility [27].

The minimum operating temperature under irradiation is estimated to be well over 1000 °C, however, providing a formidable cooling and balance of plant design challenge. Hydrogen embrittlement also remains a significant worry below 600 °C even before irradiation. Cost and stability of supply in large quantities have historically been cited as grounds for concern, but are not currently as significant.

#### 4.4. Chromium

Chromium alloys were heavily pursued in the 60s and 70s in Australia, US and Russia as a candidate high temperature material via various alloying and thermal treatment studies [28]. Once a potential rival to the eventually dominant nickel superalloys within the aerospace industry, the chromium alloys ultimately fell out of favour and have found only limited applications in the interim. Interestingly, the fusion community undertook some coarse thermo-mechanical testing of two commercially available Plansee chromium alloys in the early 2000s, before abandoning them citing the lack of room temperature ductility as a barrier to application [29]. Given advancements in manufacturing techniques including AM, this may not remain as significant a hurdle. In addition, the alloys in question (Ducropur — a high purity near-elemental product; Ducrolloy — a 5% Fe alloy to tailor thermal expansion for specific electronic applications) were clearly not developed for to fulfil fusion requirements with the historical chromium studies clearly indicating preferential alloying and/or treatment techniques that successfully offered high temperature strengthening or room

temperature ductility superior to the two commercial variants considered.

#### 4.5. Vanadium

There has been considerable interest in using vanadium alloys in fusion applications since the 1990s [30,31]. Vanadium alloys are inherently promising as a candidate structural material for fusion reactors because of their low irradiation-induced activity, favourable mechanical properties and good manufacturability. V-4Cr-4Ti is currently considered to be the reference V alloy for use in fusion reactors [32]. The nominal operating temperature range for this alloy is of order 600 °C to 800 °C. However, the supply of this reference material is limited with the largest ingots to date produced in the US, Europe and China but each only representing a few 10 s kg. Further challenges are presented with respect to its heat handling and the prospective integrity of a W-V joint given the moderate thermal conductivity and dissimilar thermal expansion coefficient to tungsten.

### 5. Thermomechanical performance

For many of the materials under consideration only limited thermophysical data is available and so the following section gives a review of several sources, including historical studies cited above (e.g. Refs. [29,31,32]), material handbooks (e.g. Ref. [27]), internal ITER project technical data (e.g. Refs. [33,34]), and data provided by material suppliers (e.g. Ref. [35]). The aim is primarily to draw preliminary performance comparisons (particularly at high temperature), demonstrate the proposed methodology, and highlight key gaps in available information using the sources above, rather than provide absolute conclusions or provide an extensive database of material property data. Graphs are plotted without extrapolation for one data source for each property, rather than averaging, and so data may be available from alternative sources where there appears to be a gap.

The influence of heat treatment and thermal history is significant for all of these materials, and values for both annealed and stress relieved conditions are not always available. Where possible, given the preference for high temperature operation, enhanced ductility over strength (in most cases), and the likelihood of extended periods of time at elevated temperature during operation, the recrystallised values are used. This has a significant impact, for example on the yield stress of tungsten, which varies by a factor of 14 between the recrystallised and stress relieved states at room temperature [34].

As stated above, one of the most significant challenges facing designers of fusion high heat flux components is the lack of fusion-neutron irradiated property data for candidate materials at suitable irradiation temperatures, durations, spectra, and fluence levels [12]. Sections 5.1 and 6 do begin to discuss some of the effects of irradiation on structural materials, but in the absence of suitable irradiated data this section will focus on unirradiated comparisons. The hope is that if promising alternative candidate materials emerge from this new selection methodology, irradiation campaigns will follow.

#### 5.1. Operating temperature window

A temperature window can be defined as a guide to describe limits within which the structural material can best be used [36], although geometric considerations and careful assessment of failure mechanisms must also be taken into consideration. At high temperature, the structural material must retain its mechanical strength, usually limited by thermal creep or increases in

environmental interactions as outlined in section 7. At lower temperatures, structural properties are usually reduced by radiation effects, particularly radiation embrittlement, which in BCC materials leads to an increase in the ductile to brittle transition temperature (DBTT) and a loss of ductility.

This window should not, however, be considered to provide absolute limits of operation. The lower limit in particular may be extended if guidance for design with brittle materials is followed, an area of active development for fusion reactor confinement boundaries [37]. Similarly, by careful design and analysis, it may be possible to have parts of a structural component operating at much higher temperature where stresses are less significant or where not exposed to damaging environmental conditions.

### 5.1.1. High temperature strength

To properly assess high temperature strength, ultimate and yield stress and creep properties across the full temperature range of interest are required, including irradiated properties under fusion neutron irradiation.

Young's modulus is available for a relatively large number of options, however, and gives a general indication of strength. As Fig. 3 shows, molybdenum and vanadium are closest to tungsten in absolute terms, but only molybdenum and tantalum retain their strength at temperatures over 800 °C.

Figs. 4 and 5 show yield stress and ultimate tensile strength for the materials under consideration. As justified above, annealed or recrystallised values have been taken where possible, though like-for-like comparative data for all materials is not available, hence tungsten's surprisingly low relative yield stress. When considering ultimate tensile strength, TZM's enhanced ductility over tungsten gives it significant advantages above 600 °C and T-111 also shows promise across the full temperature range.

### 5.1.2. Ductile to brittle transition temperature

At the other end of the temperature window, the ductile to brittle transition temperature defines a lower bound for ideal operation. Design rules for brittle materials such as ceramics in fusion structures are being considered [37]. These are preliminary, however, and ductility throughout the operational temperature range is clearly preferable.

The quantification of radiation induced embrittlement poses an additional challenge, with large uncertainties reported in the

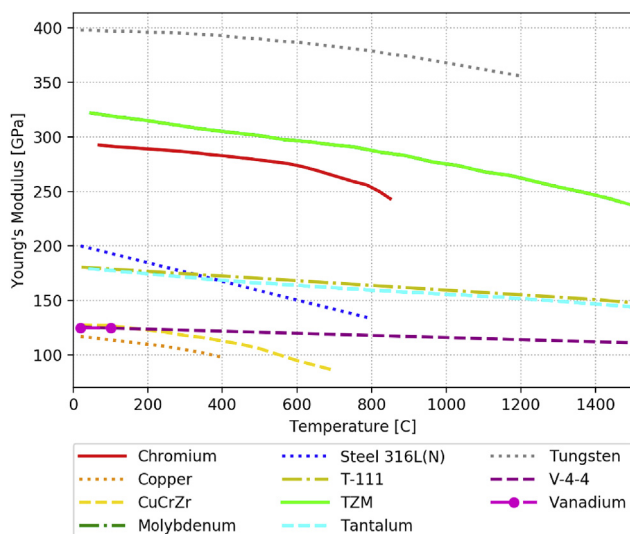


Fig. 3. Young's modulus with temperature [26,31,33,35]

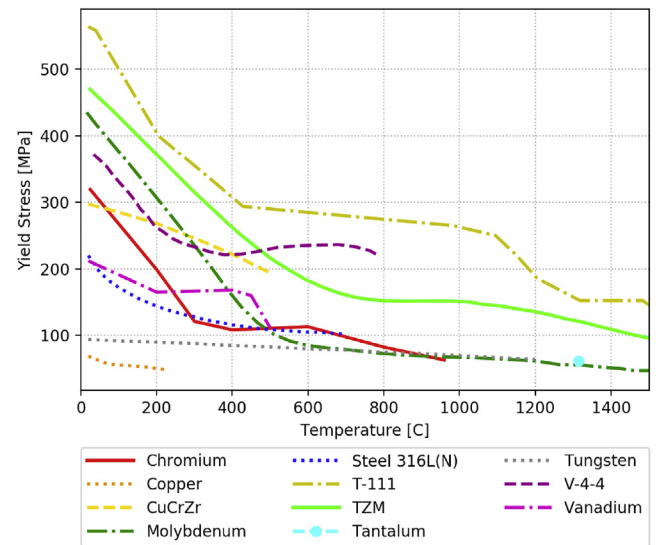


Fig. 4. Yield stress with temperature [26,27,29,33,35]

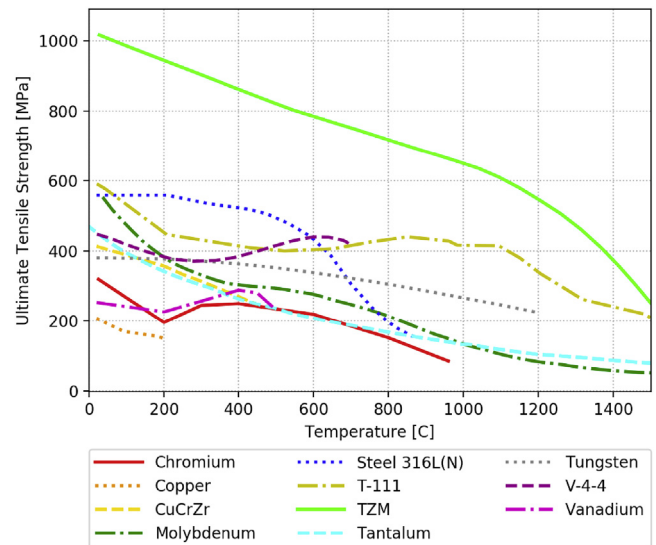


Fig. 5. Ultimate tensile strength with temperature [26,31,33,35]

change in the DBTT of irradiated tungsten and values up to 880 °C used as the baseline [38], leading to the conclusion that at least some brittleness must be anticipated if refractory metals are to be used in the structure.

Directly comparable unirradiated data for all the materials under consideration is not available, and irradiated data is sparse. In addition, fracture toughness measurements are heavily dependent on the details of sample geometry and test conditions.

Data for percentage reduction in area is somewhat more readily available and Fig. 6 gives values for a number of materials.

This graph shows that in the pure and unirradiated state, of the refractory elements only tantalum and vanadium have particularly attractive ductility at temperatures up to 400 °C, with molybdenum a close third. Care should be taken, however, as even moderate quantities of oxygen or other impurities and relatively low levels of irradiation damage have been shown to significantly degrade ductility [23]. In addition, DBTT (particularly of tungsten) is heavily dependent on grain size and grain refinement may provide a

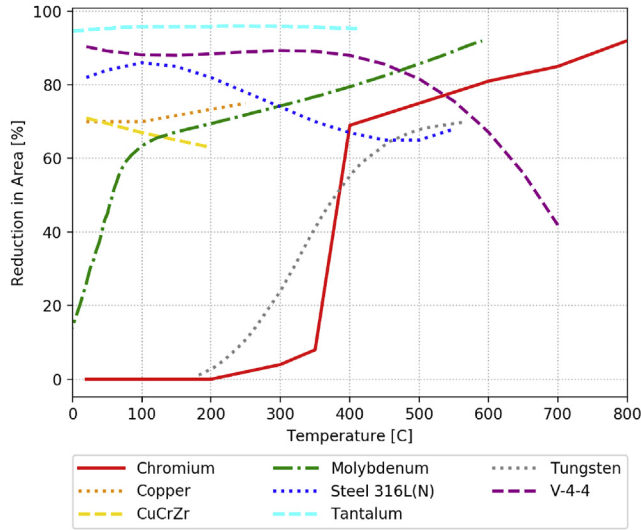


Fig. 6. Percentage reduction in area with temperature [27,32,33]

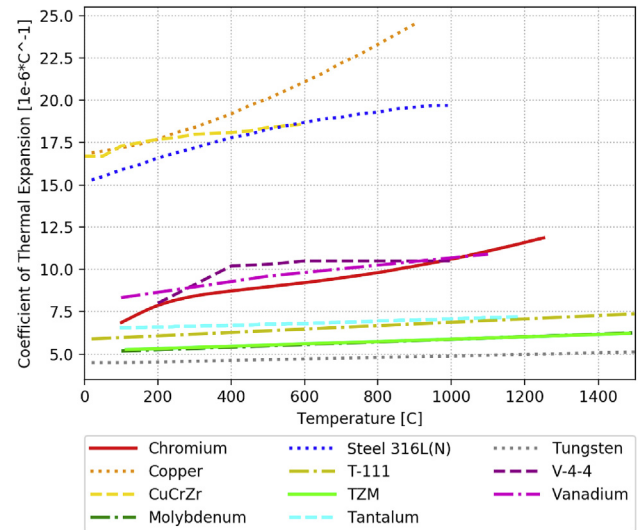


Fig. 8. Thermal expansion with temperature [26,31,33,35]

mitigation strategy if subsequent recrystallisation can be avoided [10].

## 5.2. Thermal stress

### 5.2.1. Thermal conductivity

With steep thermal gradients inevitable in cooled components subject to high heat flux, understanding and quantifying the interaction between thermal and mechanical performance is critical. Thermal conductivity is the primary driver of this thermal gradient but, as shown in Fig. 7, apart from copper and its alloys, other candidate materials become increasingly comparable at high temperature.

### 5.2.2. Coefficient of thermal expansion

High thermal gradients induce high thermal stresses, particularly when joints between dissimilar materials are considered. A lower thermal expansion coefficient generally means a lower thermal stress, but as Fig. 8 shows, differentiating clearly between candidates on this metric alone is insufficient. The challenge of

joining copper or steel to tungsten armour is well highlighted however, it is possible to identify chromium and vanadium as an intermediate group, and it is clear that tantalum and molybdenum alloys are much better matched to tungsten.

### 5.2.3. Thermal stress figure of merit

In order to clarify these interrelated criteria, Zinkle and Ghoneim [36] define a figure of merit for thermal stress  $M$  to qualitatively rank candidate materials, dependent on ultimate tensile strength, thermal conductivity, Young's modulus, coefficient of thermal expansion, and Poisson's ratio. This is related to the maximum allowable heat flux  $\phi_{qmax}$ :

$$\phi_{qmax} \propto \frac{M}{\Delta x} = \frac{\sigma_{UTS} k_{th} (1 - \nu)}{\alpha_{th} E \Delta x} \quad (1)$$

Where  $\Delta x$  is the wall thickness of a constrained plate. Thus higher values of  $M$  indicate a better ability for a given material to handle high heat fluxes. Fig. 9 shows  $M_{[material]}$  (normalised against

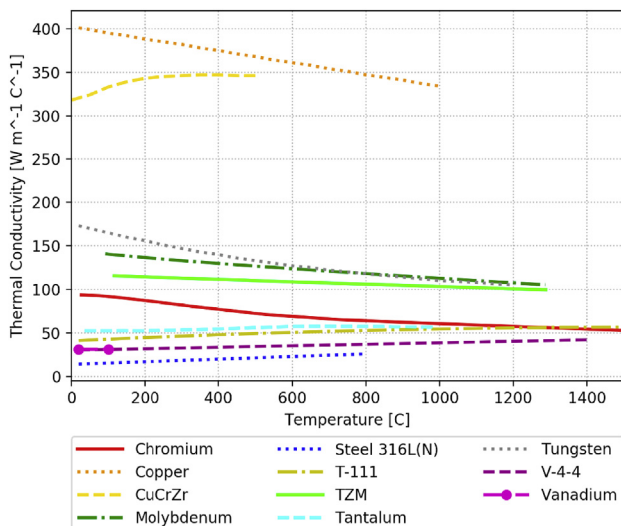


Fig. 7. Thermal conductivity with temperature [26,31,33,35]

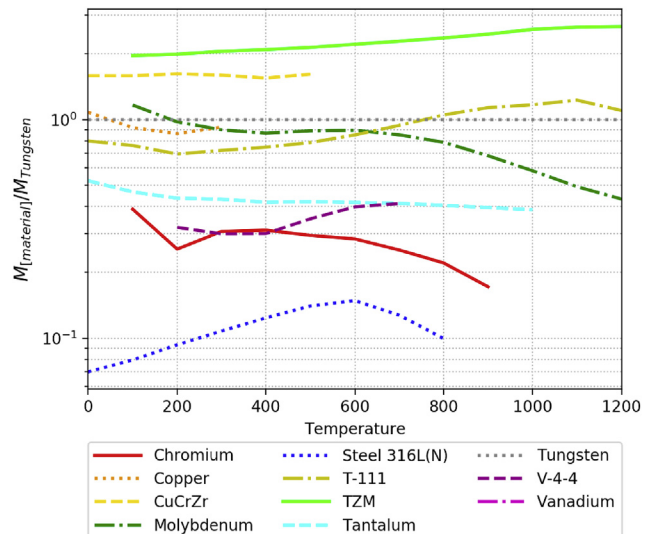


Fig. 9. Thermal stress figure of merit with temperature relative to tungsten.

$M_{tungsten}$  for clarity) plotted against temperature for a 5mm thick plate in a range of high heat flux materials.

This graph makes it clear why CuCrZr has been such a strong candidate for high heat flux components operating at lower temperatures. However, the significant reduction in strength at high temperature (Figs. 4 and 5) precludes it from use above about 350 °C [38].

Notably, TZM emerges as an attractive prospect, surpassing even CuCrZr, and elemental molybdenum is comparable to pure copper. The remaining materials are much more closely grouped, with tantalum and its alloys only slightly better than chromium, vanadium or even steel.

#### 5.2.4. Thermal mismatch stress

Thermal stress within the structural material due to thermal gradient is not the whole story, however. The primary cause of failure in prototype divertor components has been the interface between the structure (in most cases CuCrZr) and the tungsten armour [39]. Pure copper is used in ITER as a ductile interlayer to mitigate this, and concepts employing more complex compliant or graded structures have also been proposed for DEMO [40,41]. At the same time, alternative materials with lower thermal mismatches are being explored, including chromium [42]. Applying a thin-walled tube approximation, the stress induced in the structural material due to the thermal expansion mismatch can be calculated using equation (2):

$$\sigma_{mm} = \frac{\alpha_2(T_{2,mean} - T_{ref}) - \alpha_1(T_{1,mean} - T_{ref})}{\frac{(1 - \nu_2)t_1}{t_2 E_2} + \frac{1 - \nu_1}{E_1}} \quad (2)$$

$$T_{1,mean} = T_{coolant} + \frac{q}{h} + \frac{qt_1}{2k_1}$$

$$T_{2,mean} = T_{coolant} + \frac{q}{h} + \frac{qt_1}{k_1} + \frac{qt_2}{2k_2}$$

where  $\phi_{mm}$  is the mismatch stress,  $T_{ref}$  is the reference starting temperature of the component,  $T_{coolant}$  is the bulk coolant temperature,  $q$  is the incident heat flux,  $t_1$  and  $t_2$  are the thicknesses of structure and armour respectively,  $T_{1,mean}$  and  $T_{2,mean}$  are the mean temperatures in each material,  $\nu_1$  and  $\nu_2$  are Poisson's ratios,  $\alpha_1$   $\alpha_2$

are thermal expansion coefficients, and  $E_1$  and  $E_2$  are Young's moduli [43].

Fig. 10 shows a graph of the magnitude of this stress with applied heat fluxes up to 25MW m<sup>-2</sup> calculated for 1 mm of a range of materials paired with 5 mm of tungsten using 150 °C coolant. Values are not plotted once mean temperatures in the structural material are 100 °C above the maximum temperature for which material data has been provided.

Notably, at a certain combination of heat flux, material thicknesses, and thermal conductivities, using a material with a slightly larger thermal expansion coefficient and lower thermal conductivity than tungsten results in a lower stress at the interface than even a tungsten-tungsten joint, due to the large temperature gradient mitigating the thermal expansion mismatch. At heat fluxes below approximately 7MW m<sup>-2</sup> tantalum and molybdenum alloys show the best performance. At higher heat fluxes, however, chromium and vanadium become the clear favourites. The “ideal” heat flux for CuCrZr for this combination of material thicknesses, temperatures, and convective heat transfer coefficients is higher than has been plotted, but the mean material temperature at this point is sufficiently high that structural properties are significantly degraded.

Fig. 11 highlights the sensitivity of material pairing to component design parameters. For example, increasing the coolant temperature to 500 °C significantly improves the performance of tantalum and molybdenum alloys, but further excludes copper alloys and moves chromium and vanadium outside their operating temperature windows.

The choice of  $T_{ref}$  is also a critical factor in the validity of these graphs, as bonding is usually carried out at elevated temperatures. Geometric design and variation in heat transfer coefficient or methods to remove residual stress during and post assembly (e.g. Ref. [44]) will further significantly impact these values, and so these calculations should be taken as demonstrating a figure of merit to be used as a tool for assessing coupled sets of design parameters including material choice rather than as engineering design proposals as they stand.

## 6. Radiation damage tolerance

As well as radiation induced loss of ductility as described in Section 5.1, additional radiation damage mechanisms must be considered, namely activation and swelling.

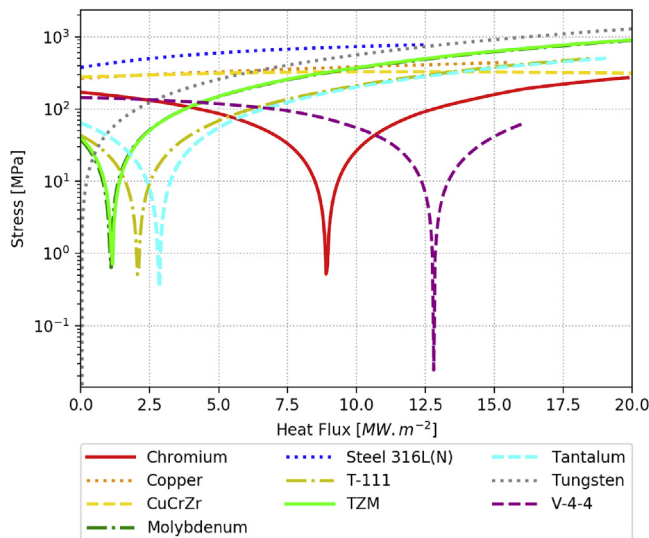


Fig. 10. Thermal mismatch stress using 150 °C coolant.

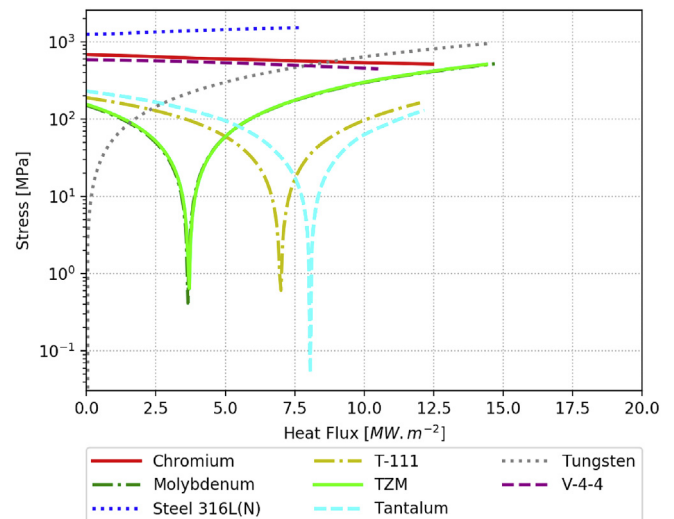


Fig. 11. Thermal mismatch stress using 500 °C coolant.

In order to satisfy environmental responsibility and reduce decommissioning costs, the fusion community have set ambitious and stringent requirements on the activation of power plant components as follows:

As given in Ref. [45], for remote handling recycling the dose rate limit is:

$$\sum_{i=1}^{118} A_i(A_i X) < 10 \frac{mSv}{hr} \quad (3)$$

and Decay heat < 10W/m<sup>3</sup>

For hands-on recycling the dose rate limit is:

$$\sum_{i=1}^{118} A_i(A_i X) < 10 \frac{\mu Sv}{hr} \quad (4)$$

and Decay heat < 1W/m<sup>3</sup>

The above criteria are to be achieved within 100 years ex-reactor.

Combining these and other environmental concerns, IAEA guidelines define a clearance index of a material to determine if the material can be disposed of with no special precautions. If less than 1 then the material can be disposed of or cleared as if it were non-radioactive [46].

Figs. 12–14 show dose rate, decay power, and clearance index plots against these limits for tungsten, molybdenum, tantalum, chromium, and vanadium calculated for a neutron spectra corresponding to the first wall of a conceptual fusion power plant [47]. Copper is also included for comparison.

This data shows that molybdenum is significantly more activated than the other materials considered, chromium and vanadium are notably less activated, and tantalum compares favourably with tungsten and copper at the 100 year cut-off timescales.

These graphs also show that despite the oft repeated mantra of, “everything to be recyclable in 100 years,” the currently assumed first wall armour and structural materials of tungsten and copper alloys will not meet this target with the baseline first wall neutron spectra. Given the apparent inevitability of a certain quantity of mid-level waste at the decommissioning stage of the first generation of fusion power plants (or at least for an

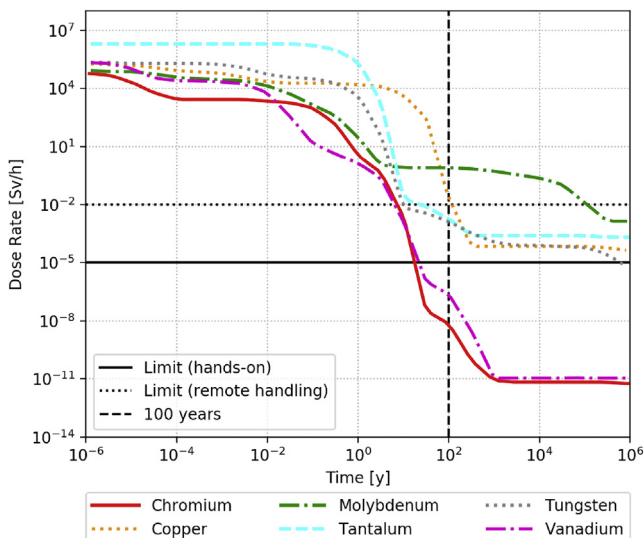


Fig. 12. Activation dose rate.

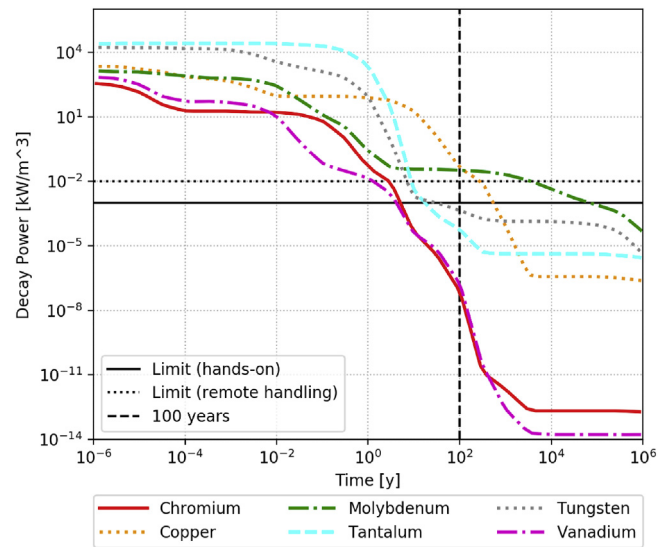


Fig. 13. Activation decay power.

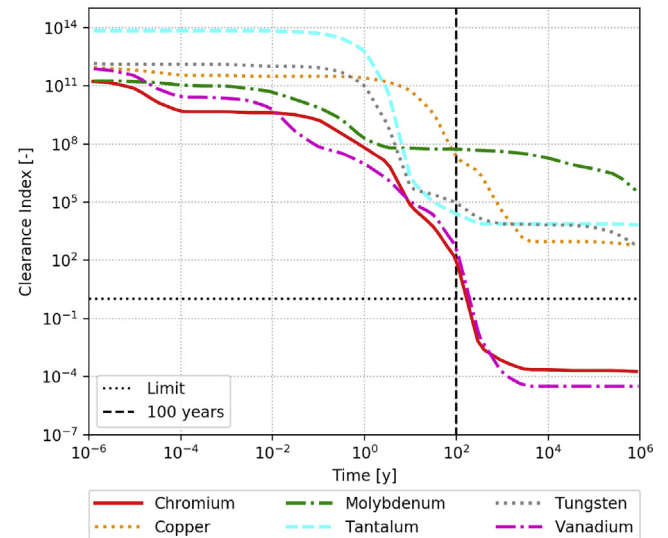


Fig. 14. Activation clearance index.

engineering demonstrator such as DEMO), it seems sensible to tentatively consider the possibility of small quantities of more activated materials during this phase of fusion power development, if concepts employing them provide a route to progressing towards commercialisation and overcoming other challenges in parallel.

If even allowing modest quantities of active waste is discounted, Gilbert et al. [48] have demonstrated that isotope tailoring provides one route to using materials which would not otherwise be palatable, and have used molybdenum as an example. Seven isotopes of molybdenum occur naturally in relatively equal abundance, one of which (Mo97) is significantly less activated than the others. Fig. 15 shows that although it does not meet the dose rate requirements, it does compare favourably with tungsten after the 100 year limit.

Achieving the enrichment needed to meet this level of activation will almost certainly be prohibitively expensive for bulk elemental molybdenum, but if quantities of isotopically tailored material are small or if Mo97 is used as a minor alloying element to enhance performance in another candidate material, it may prove a

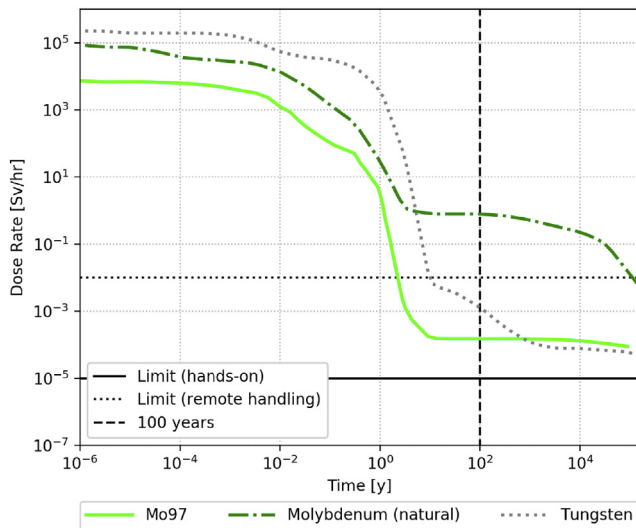


Fig. 15. Isotope tailoring of molybdenum.

worthwhile tool in the designers' arsenal and should not be immediately discounted.

The high heat flux and shallow grazing angle of incident particle fluxes on plasma facing surfaces require close geometric tolerances to be maintained throughout the lifetime of divertor components. Helium production in neutron irradiated materials causes swelling [49] which can accelerate surface erosion and induce additional stresses which in turn reduce component lifetime. Little data is available for materials other than tungsten in a fusion neutron spectrum, but the BCC crystal structure of the other refractory metals suggests that the degree of swelling will be similar.

## 7. Chemical compatibility with operating environment

Thermomechanical performance of structural materials for fusion must be maintained throughout the component lifetime while exposed to both the demanding rigours of the tokamak environment on the plasma-facing side and the coolant on internal surfaces. A full evaluation of all the mechanisms involved is beyond the scope of this paper, particularly as comparable quantitative data for each pairing of material and reagent is not available. The following sections, therefore, highlight critical issues and present a brief summary of available knowledge.

### 7.1. Tokamak gasses

The structural materials will largely be shielded from direct contact with incident particle fluxes by the tungsten armour, but will nonetheless still be exposed to the tokamak environment. Primarily, this means that vapour pressure must be low enough to maintain ultra-high-vacuum, but exposure to hydrogen isotopes and helium pose additional challenges. Tritium retention must be as low as possible in order to both minimise overall radioactive inventory in a reactor and to avoid loss of available fuel due to decay. In addition, exposure to hydrogen causes embrittlement, and this has historically been the cause of most concern (e.g. Refs. [16,20]). The degree of embrittlement, particularly when combined with radiation effects, depends heavily on partial pressure of hydrogen and operating temperature of the component. In addition, hydrogen can, in some cases, be sufficiently removed by holding the component at an elevated temperature [50].

### 7.2. Coolant

Proposed high temperature coolants for fusion high heat flux applications fall broadly into four categories: gasses, supercritical fluids, liquid metals, and molten salts. The choice of pairing of structural material and coolant is an integrated decision closely tied to the geometry and is based on multiple interdependent factors. Comparisons of thermofluid performance, based on bulk coolant temperature, heat transfer coefficient, and critical heat flux have been reported elsewhere, e.g. Refs. [15,51]. Wider balance of plant and reactivity considerations are less connected to the choice of structural material and are also well debated, e.g. Ref. [52]. Information is less well collated on issues of corrosion, erosion, and embrittlement in the context of specifically high temperature fusion applications and refractory materials, and so the following sections will focus primarily on these for each type of coolant, while highlighting gaps in knowledge, where necessary.

#### 7.2.1. Gasses

The pressure inside cooling channels will be significantly different from that outside, but compatibility with the leading candidate gas coolants, helium and hydrogen, has been covered above. Other than the embrittlement previously discussed, significant concerns regarding the use of these are generally material independent, and are more operational issues such as leak tightness, cost, thermal efficiency, and safety.

#### 7.2.2. Supercritical fluids

Supercritical water has been proposed as a coolant for both fission and fusion, is currently used in state of the art high temperature fossil fuel power plants up to 600°C, and has been proposed for applications up to 700°C [53]. Despite this, the focus of corrosion studies has been on a relatively small number of conventional materials with less information available on refractory alloys. At first inspection, the high corrosion resistance of refractory alloys suggests that this may not be a significant concern, but the release of both oxygen and hydrogen due to radiolysis under neutron exposure raises the possibility of reaction from both.

There is also some experience of using supercritical CO<sub>2</sub> for gas-cooled fission reactors and it has been proposed for the secondary coolant loop of fusion power plants [54,55], but its use as a primary coolant has not been fully explored.

In summary, both supercritical water and CO<sub>2</sub> promise high heat transfer coefficients at high temperature at the expense of very high pressure operation and unknown corrosion performance.

#### 7.2.3. Liquid metals

Liquid metals, particularly lithium, lead-lithium, and sodium have persistently been considered as coolants for both fission [56] and fusion [5]. For fusion, this has included use as both coolant and as plasma facing material for blanket and divertor applications (e.g. Refs. [6,57–59]), to the extent that a lead-lithium divertor was included as the baseline of the most advanced of the European power-plant conceptual study concepts [45].

Dual cooled lithium lead blanket (DCLL) concepts exist for both ITER and DEMO [60,61]. Liquid metals have very high boiling temperature and high heat transfer capability, even at low pressure, and, if lithium or lead-lithium is used, can perform multiple-duty as coolant, neutron multiplier, and tritium breeder. These significant benefits must be balanced with numerous challenges, however. Magnetohydrodynamic (MHD) effects due to flow in the presence of tokamak magnetic fields increase pumping power significantly, even at low velocities and when care is taken with the orientation of flow channels. Where water is used as a secondary coolant, reactivity in the event of leakages is a significant risk.

As with molten salts, corrosion and erosion are of significant concern. Compatibility with tantalum is well established, but corrosion [62] and other interactions such as wetting properties [63] require further characterisation under fusion-relevant conditions.

#### 7.2.4. Molten salts

Corrosion is the driving factor affecting compatibility between structural material and molten salts. Corrosivity depends heavily on impurities present in the salt used, and so quantitative assessments of compatibility are subject to the need for careful chemistry control. Reviews of the literature suggest that historical studies have mainly been limited to a subset of nickel based superalloys [64], but these give indications of the susceptibility of various alloying elements which can be used to infer relative performance of alloys based on these.

For fluoride salts chromium is the most readily corroded element among the most common constituents of nickel alloys, but tantalum fluoride has an even lower energy of formation suggesting yet greater vulnerability. Molybdenum, vanadium, and tungsten on the other hand are more comparable to iron and nickel, suggesting performance comparable to alloys previously studied, with molybdenum alloys historically listed as the most favourable for fusion applications (e.g. Ref. [24]). Trials using FLiBe with vanadium alloys have also identified tritium permeation and retention as a significant challenge which needs careful control measures [65].

Results for chloride salts reported in the above reviews suggest that they may be more corrosive than their fluoride counterparts, though studies on relevant materials are even more limited.

Although internal coatings can be used to allow use of a wider range of materials, if complex cooling geometries are to be employed, both the application of these coatings and the verification of their efficacy become increasingly challenging.

## 8. Manufacturing process

Purely selecting a structural material for a high heat flux component on its thermomechanical properties and chemical merits is not sufficient, however: the concept must be manufactured. The cooled structure must be formed into the desired geometry, whether tube or more complex shape, and it must be joined to the armour either directly or using an interlayer. Throughout these processes, the mechanical properties must be maintained — typically meaning the maintenance (or generation) of suitable grain structure.

### 8.1. Forming

The inherent hardness and high melting points of refractory metals makes them very difficult to form and fragile if complex shapes are used. Drawing for tubes or forging requires high ductility and very high temperature tooling. Tungsten, in particular, is difficult to machine, and cutting using electrode discharge machining is time consuming and expensive. Traditional powder metallurgy including pressing and sintering is limited to relatively simple shapes and does not lend itself to pressure-retaining geometries.

More recent work has focused on tungsten, examining the use of multilayered foils, powder injection moulding, and fibre reinforced composites and seeks to solve some of these problems, particularly striving for increased ductility [66].

Additive manufacturing opens the possibility of employing complex geometries not achievable by conventional manufacturing techniques as well as significantly more efficient use of raw

material reducing both wastage and remote handling mass [67]. Fig. 16 shows as an example the level of complexity that can be achieved in powder bed additive layer manufacturing, though robust consistency of material properties has yet to be established for a full range of refractory materials, with tantalum and vanadium as the most promising so far.

### 8.2. Joining

As stated in Section 5.2.4, The joint between tungsten armour and copper alloy substructure has historically been the primary point of failure for high heat flux components, due to the high thermal expansion mismatch. For these dissimilar metal joints, ductility is a desirable characteristic as detailed above, and the inclusion of a ductile pure copper interlayer is the usual mitigation technique. Newer concepts involving compliant structures have also shown the ability to survive large numbers of cycles at elevated heat fluxes [40]. Novel thermal cycling methods for brazing dissimilar materials [44] have also been proposed for reducing these stresses in operation.

One of the most active areas of investigation is that of functionally grading the joint. For copper and tungsten, this has been attempted using a range of methods, including plasma spray techniques [68], melt infiltration [69], spark plasma sintering [70], and laminated foils [71]. For refractory metals, wire arc additive manufacturing has been used to produce a promising three layer joint between tantalum, molybdenum, and tungsten, though this work is unpublished at the time of writing.

The mutual solubility of the two materials and any intermetallic phases formed between them are critical factors in the ease of joining, as well as proximity of melting point, if direct melt-based joining processes are to be used without e.g. braze filler. Of the materials under consideration in this paper, tantalum in particular has excellent solubility with tungsten and with its high melting point lends itself well to powder based grading processes.

## 9. Price and availability

Fig. 17 shows the historical price of a number of refractory elements, with copper included for comparison. Price has been an argument for excluding tantalum for consideration, and while costs have fluctuated significantly in recent years, it is certainly an

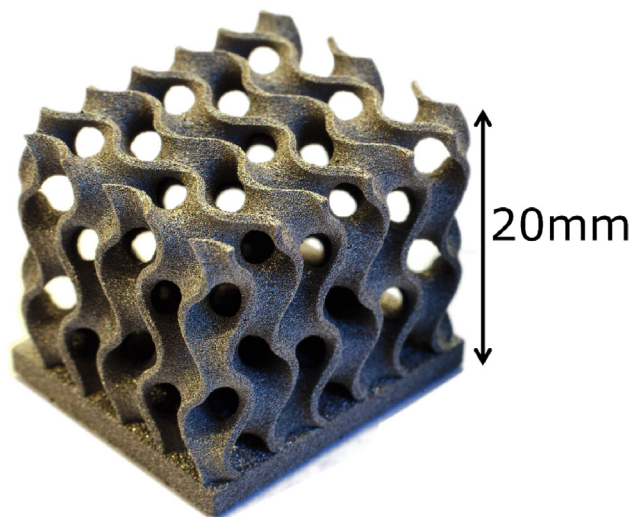


Fig. 16. Additively manufactured tungsten gyroid.

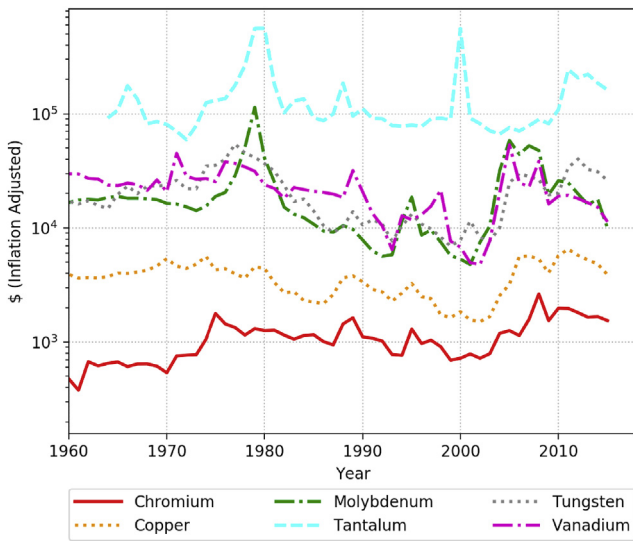


Fig. 17. Historical refractory metal prices [USGS].

ongoing concern. Being nearly an order of magnitude more costly than tungsten. Notably, chromium has remained significantly cheaper than even copper, and molybdenum and vanadium have shown a marked downward trend over the last few years making them worthy of monitoring.

Of ongoing concern is the future availability of candidate materials for fusion applications. Fig. 18 shows relative stability over the last 50 years for all materials under consideration, with similar levels of production for tungsten, molybdenum, and vanadium. Tantalum's relative scarcity and chromium's significance (e.g. as an alloying element in steel) are also clearly shown.

Concepts based around additive manufacturing require the supply of suitable feedstock. Elemental tungsten, tantalum, molybdenum, and vanadium powders for laser powder bed fusion have been sourced in small quantities and trials are ongoing with the use of both blended and pre-alloyed tungsten-tantalum ratios but quality has been highly variable between suppliers and cost remains high.

In addition, as shown in the proceeding sections, alloys of

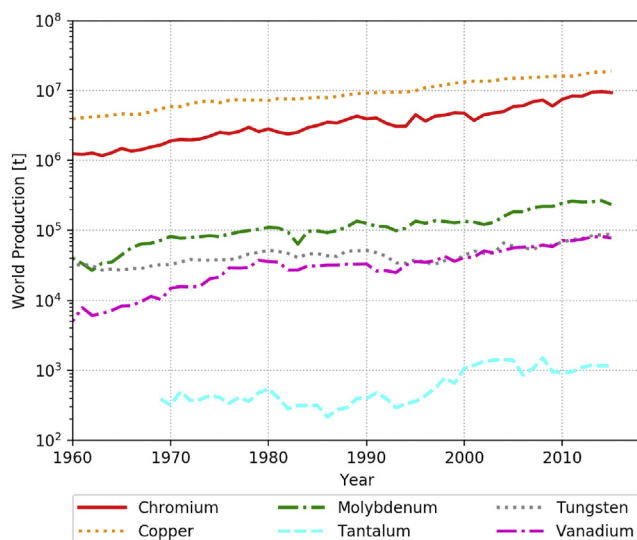


Fig. 18. World production of candidate materials [USGS].

candidate elements are likely to show better performance overall than the elements alone, and supply chain for fusion-relevant (and in some cases novel) refractory alloys would need to be fully established, including a programme of characterisation and testing, before they could be considered for inclusion as structural material candidates.

## 10. SWOT analyses

Tables 1–5 show one approach for assessing the results detailed above. Each element is subjected to a SWOT analysis summarising the strengths, weaknesses, opportunities, and threats associated with choosing alloys based on it. In this case, “**strengths**” and “**weaknesses**” are taken to be inherent properties of the material which are advantageous or disadvantageous for their use. On the other hand, “**opportunities**” and “**threats**” are external; being either possible research avenues which might prove the material to be useful or factors where there is large uncertainty either due to lack of available data or unknown future priorities.

Lack of available relevant irradiated data is a constant threat across all fusion materials and corrosion data is almost as equally sparse. Although the inclusion in each table might seem excessive, continuing to highlight the strategic relevance of these research areas remains an important task. Similarly, the potential for developing new alloys more specifically suited to fusion applications or revisiting historical research on refractory alloys such as T-111 occurs repeatedly in the “opportunities” quadrants, particularly when seeking to employ advanced technologies such as additive manufacturing with different requirements to traditional techniques.

## 11. Conclusions

Historical material selection processes for fusion high heat flux structural materials have generally taken a linear sequential approach to requirements, excluding elements from the periodic table or known alloys at each stage. This, along with a prevailing conservatism within the community, has led to a very small palette of options available to component designers. Some recent work on composites of these materials has shown enhanced strength and damage tolerance, but the potential for significant performance enhancement if alternative materials can be found for cooled structures leads to a desire to re-evaluate the initial material selection process.

Recent advances in manufacturing methods, including additive manufacturing; improved analysis and testing towards design with brittle materials; progress in the practicality of designing alloys for specific applications; and a fuller assessment of the feasibility of isotope tailoring or more pragmatic approach to the rigorous application of the “recyclable in 100 years” mantra will inevitably broaden the aforementioned palette of candidate materials. Component designers must therefore make choices based on a more nuanced parallel assessment of strengths and compromises, recognising that no “ideal” material exists for any application. Such an assessment will inevitably identify gaps in knowledge and will prompt targeted research, including alloy development, material testing, and irradiation campaigns. New materials, new manufacturing techniques, and new geometric design freedom will also need new design rules for determining structural integrity for future fusion devices and although this need is already recognised for DEMO (e.g. Ref. [72]), the early identification of candidate materials and processes will allow their timely inclusion in these design guidelines.

This paper demonstrates one such assessment, focussed on high temperature operation of divertor components, looking at

**Table 1**  
Tungsten SWOT analysis.

<b>Strengths</b> <ul style="list-style-type: none"> <li>• Current baseline material</li> <li>• No joint to armour needed</li> </ul>	<b>Weaknesses</b> <ul style="list-style-type: none"> <li>• Brittleness</li> <li>• Oxidation</li> <li>• Significant loss in strength when recrystallised</li> </ul>
<b>Opportunities</b> <ul style="list-style-type: none"> <li>• Advanced manufacturing may allow cooled structures</li> <li>• Alloy development may increase ductility</li> </ul>	<b>Threats</b> <ul style="list-style-type: none"> <li>• Lack of irradiated data</li> <li>• Variability in quality of supplied material</li> </ul>

**Table 2**  
Molybdenum SWOT analysis.

<b>Strengths</b> <ul style="list-style-type: none"> <li>• TZM has excellent high temperature strength</li> <li>• High thermal conductivity</li> <li>• Low thermal expansion</li> </ul>	<b>Weaknesses</b> <ul style="list-style-type: none"> <li>• Activation</li> <li>• Oxidation</li> <li>• Brittleness</li> </ul>
<b>Opportunities</b> <ul style="list-style-type: none"> <li>• Isotope tailoring may permit some use</li> <li>• Fusion specific alloys may be possible which are more suitable than TZM under irradiation</li> </ul>	<b>Threats</b> <ul style="list-style-type: none"> <li>• Lack of irradiated data</li> <li>• Lack of corrosion data</li> </ul>

**Table 3**  
Tantalum SWOT analysis.

<b>Strengths</b> <ul style="list-style-type: none"> <li>• Alloys have excellent high temperature performance</li> <li>• Excellent corrosion and oxidation resistance</li> <li>• Proven compatibility with liquid metals</li> <li>• Good low temperature ductility</li> </ul>	<b>Weaknesses</b> <ul style="list-style-type: none"> <li>• High cost</li> <li>• Must be operated at very high temperature to avoid embrittlement</li> <li>• Poor compatibility with molten salts</li> </ul>
<b>Opportunities</b> <ul style="list-style-type: none"> <li>• Exploration of historical alloys such as T-111</li> <li>• Results of additive manufacturing trials are promising</li> </ul>	<b>Threats</b> <ul style="list-style-type: none"> <li>• Lack of irradiated data</li> <li>• Uncertain availability</li> </ul>

thermomechanical performance, radiation damage tolerance, chemical compatibility, manufacturing, and price and availability of a number of refractory metals identified as a promising group

following a preliminary downselection exercise. Material properties and derived figures of merit are compared to current baseline materials and general observations are made at each stage.

**Table 4**  
Chromium SWOT analysis.

<b>Strengths</b> <ul style="list-style-type: none"> <li>• Good thermal mismatch behaviour at lower bulk temperatures</li> <li>• Very low Activation</li> <li>• Low Cost</li> </ul>	<b>Weaknesses</b> <ul style="list-style-type: none"> <li>• Moderate yield and ultimate strength at high temperature</li> <li>• Brittleness</li> <li>• Poor thermal stress figure of merit</li> <li>• Poor compatibility with molten salts</li> </ul>
<b>Opportunities</b> <ul style="list-style-type: none"> <li>• Designs for thermal mismatch reduction</li> <li>• Alloy development to increase ductility</li> </ul>	<b>Threats</b> <ul style="list-style-type: none"> <li>• Lack of irradiated data</li> <li>• Lack of corrosion data</li> </ul>

**Table 5**  
Vanadium SWOT analysis.

<b>Strengths</b> <ul style="list-style-type: none"> <li>• Significant body of historical research</li> <li>• Very low activation</li> <li>• Good unirradiated ductility</li> </ul>	<b>Weaknesses</b> <ul style="list-style-type: none"> <li>• Modest strength at high temperature</li> </ul>
<b>Opportunities</b> <ul style="list-style-type: none"> <li>• Alloy development may improve performance</li> <li>• Poor thermal mismatch at high temperature</li> </ul>	<b>Threats</b> <ul style="list-style-type: none"> <li>• Lack of irradiated data</li> <li>• Lack of corrosion data</li> <li>• Limited supply of suitable alloys</li> </ul>

Brittleness, manufacturability, and concerns about activation have historically been grounds for excluding many of these refractory alloys from consideration when designing divertor target concepts and other high heat flux components for fusion energy. Despite other issues such as availability and lack of data for alloys rather than pure elements rendering a number of these relatively unattractive at present, the value of further investigation into their development and subsequent use has been discussed.

## Acknowledgements

This work has been carried out within the framework of the EUROfusion Consortium and has received funding from the Euratom research and training programme 2014–2018 under grant agreement No. 633053. This project has also received funding from the European Union's Seventh Framework Programme for research, technical development, and demonstration under grant agreement No. 313781. The views and opinions expressed herein do not necessarily reflect those of the European Commission. This work has also been part-funded by the RCUK Energy Programme [grant No. EP/P012450/1]. To obtain further information on the data and models underlying this paper please contact publicationsmanager@ccfe.ac.uk.

The authors also gratefully acknowledge the support of the whole AMAZE project team, particularly Matti Coleman for assistance with defining requirements and Chris Harrington for his extensive knowledge of fusion relevant coolants.

## Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.jnucmat.2018.09.052>.

## References

- [1] M. Turnyanskiy, R. Neu, R. Albanese, R. Ambrosino, C. Bachmann, S. Brezinsek, T. Donne, T. Eich, G. Falchetto, G. Federici, D. Kalupin, X. Litaudon, M. Mayoral, D. McDonald, H. Reimerdes, F. Romanelli, R. Wenninger, J.-H. You, European roadmap to the realization of fusion energy: mission for solution on heat-exhaust systems, *Fusion Eng. Des.* 96–97 (2015) p361–p364, <https://doi.org/10.1016/j.fusengdes.2015.04.041>.
- [2] G. Fishpool, J. Canik, G. Cunningham, J. Harrison, I. Katramados, A. Kirk, M. Kovari, H. Meyer, R. Scannell, MAST-upgrade divertor facility and assessing performance of long-legged divertors, *J. Nucl. Mater.* 438 (2013) S356–S359, <https://doi.org/10.1016/j.jnucmat.2013.01.067>.
- [3] R. Zagórski, V. Pericoli, H. Reimerdes, R. Ambrosino, H. Bufferand, Evaluation of the power and particle exhaust performance of various alternative divertor concepts for DEMO, 22nd, Int. Conf. Plasma Surf. Interact. Control. Fusion Devices (2016) 39.
- [4] G. Federici, W. Biel, M. Gilbert, R. Kemp, N. Taylor, R. Wenninger, European

- DEMO design strategy and consequences for materials, *Nucl. Fusion* 57 (9) (2017), <https://doi.org/10.1088/1741-4326/57/9/092002>, 092002.
- [5] F.L. Tabarés, Present status of liquid metal research for a fusion reactor, *Plasma Phys. Contr. Fusion* 58 (1) (2016), <https://doi.org/10.1088/0741-3335/58/1/014014>, 014014.
  - [6] R.J. Goldston, R. Myers, J. Schwartz, The lithium vapor box divertor, *Phys. Scripta* T167 (T167) (2016), <https://doi.org/10.1088/0031-8949/T167/1/014017>, 014017.
  - [7] T. Hirai, V. Barabash, F. Escourbiac, A. Durocher, L. Ferrand, V. Komarov, M. Merola, ITER divertor materials and manufacturing challenges 125 (2017) p250–p255, <https://doi.org/10.1016/j.fusengdes.2017.07.009>.
  - [8] P. Norajitra, R. Giniyatulin, T. Hirai, W. Krauss, V. Kuznetsov, I. Mazul, I. Ovchinnikov, J. Reiser, G. Ritz, H.-J. Ritzhaupt-Kleissl, V. Widak, Current status of He-cooled divertor development for DEMO, *Fusion Eng. Des.* 84 (7–11) (2009) p1429–p1433, <https://doi.org/10.1016/J.FUSENGDES.2008.11.042>.
  - [9] Y. Huang, M.S. Tillack, N.M. Ghoniem, Tungsten Monoblock Concepts for the Fusion Nuclear Science Facility (FNSF) First Wall and Divertor, *Fusion Eng. Des.* 135 (2018) 346–355, <https://doi.org/10.1016/j.fusengdes.2017.06.026>.
  - [10] J. Reiser, L. Garrison, H. Greuner, J. Hoffmann, T. Weingärtner, U. Jäntsch, M. Klimenkov, P. Franke, S. Bonk, C. Bonnekoh, S. Sickinger, S. Baumgärtner, D. Bolich, M. Hoffmann, R. Ziegler, J. Konrad, J. Hohe, A. Hoffmann, T. Mrotzek, M. Seiss, M. Rieth, A. Möslang, Ductilisation of tungsten (W): tungsten laminated composites, *Int. J. Refract. Metals Hard Mater.* 69 (2017) p66–p109, <https://doi.org/10.1016/j.jrmhm.2017.07.013>.
  - [11] J.R.J. Nicholas, P. Ireland, D. Hancock, D. Robertson, Development of a high-heat flux cooling element with potential application in a near-term fusion power plant divertor, *Fusion Eng. Des.* 96–97 (2015) p136–p141, <https://doi.org/10.1016/j.fusengdes.2015.03.033>.
  - [12] D. Stork, P. Agostini, J.-L. Boutard, D. Buckthorpe, E. Diegele, S.L. Dudarev, C. English, G. Federici, M.R. Gilbert, S. Gonzalez, A. Ibarra, C. Linsmeier, A.L. Puma, G. Marbach, L.W. Packer, B. Raj, M. Rieth, M.Q. Tran, D.J. Ward, S.J. Zinkle, Materials R&D for a timely DEMO: key findings and recommendations of the EU roadmap materials assessment group, *Fusion Eng. Des.* 89 (7) (2014) p1586–p1594, <https://doi.org/10.1016/j.fusengdes.2013.11.007>.
  - [13] J. Brooks, L. El-Guebaly, A. Hassanein, T. Sizyuk, Plasma-facing material alternatives to tungsten, *Nucl. Fusion* 55 (4) (2015), <https://doi.org/10.1088/0029-5515/55/4/043002>, 043002.
  - [14] T.R. Barrett, G. Ellwood, G. Pérez, M. Kovari, M. Fursdon, F. Domptail, S. Kirk, S.C. McIntosh, S. Roberts, S. Zheng, L.V. Boccaccini, J.-H. You, C. Bachmann, J. Reiser, M. Rieth, E. Visca, G. Mazzone, F. Arbeiter, P.K. Domalpalay, Progress in the engineering design and assessment of the European DEMO first wall and divertor plasma facing components, *Fusion Eng. Des.* 109111 (2016) p917–p924, <https://doi.org/10.1016/j.fusengdes.2016.01.052>.
  - [15] W.-P. Baek, S.H. Chang, Coolant options and critical heat flux issues in fusion reactor divertor design, *J. Korean Nucl. Soc.* 29 (4) (1997) p348–p359.
  - [16] R.P. Jewett, R.J. Walter, W.T. Chandler, R.P. Frohberg, Hydrogen environment embrittlement of metals, *Tech. Rep.* (1973). March, report number NASA-CR-2163, <http://hdl.handle.net/2060/19730012717>.
  - [17] C. Linsmeier, M. Rieth, J. Aktaa, T. Chikada, A. Hoffmann, J. Hoffmann, A. Houben, H. Kurishita, X. Jin, M. Li, A. Litnovsky, S. Matsuo, A. von Müller, V. Nikolic, T. Palacios, R. Pippan, D. Qu, J. Reiser, J. Riesch, T. Shikama, R. Stieglitz, T. Weber, S. Wurster, J.-H. You, Z. Zhou, Development of advanced high heat flux and plasma-facing materials, *Nucl. Fusion* 57 (9) (2017), <https://doi.org/10.1088/1741-4326/aa6f71>, 092007.
  - [18] J.-H. You, A review on two previous divertor target concepts for DEMO: mutual impact between structural design requirements and materials performance, *Nucl. Fusion* 55 (11) (2015) 113026, <https://doi.org/10.1088/0029-5515/55/11/113026>.
  - [19] M.A. Abdou, Exploring novel high power density concepts for attractive fusion systems, *Fusion Eng. Des.* 45 (2) (1999) p145–p167, [https://doi.org/10.1016/S0920-3796\(99\)00018-6](https://doi.org/10.1016/S0920-3796(99)00018-6).
  - [20] M. Übeyli, e. Yalçın, e. Yalçın, Utilization of refractory metals and alloys in fusion reactor structures, *J. Fusion Energy* 25 (3–4) (2006) p197–p205, <https://doi.org/10.1007/s10894-006-9019-4>.
  - [21] S. Gonderman, J.K. Tripathi, T.J. Novakowski, T. Sizyuk, A. Hassanein, Effect of dual ion beam irradiation (helium and deuterium) on tungsten-tantalum alloys under fusion relevant conditions, *Nucl. Mater. Energy* 12 (2016) p346–p352, <https://doi.org/10.1016/j.nme.2017.02.011>.
  - [22] P. Norajitra, R. Giniyatulin, V. Kuznetsov, I.V. Mazul, G. Ritz, He-cooled divertor for DEMO: status of development and HHF tests, *Fusion Eng. Des.* 85 (10–12) (2010) p2251–p2256, <https://doi.org/10.1016/j.fusengdes.2010.09.006>.
  - [23] R. Konings, T.R. Allen, R.E. Stoller, S. Yamanaka, *Comprehensive Nuclear Materials*, Elsevier Science, 2011.
  - [24] D.J. Mazey, C.A. English, Role of refractory metal alloys in fusion reactor applications, *J. Less Common. Met.* 100 (C) (1984) p385–p427, [https://doi.org/10.1016/0022-5088\(84\)90078-X](https://doi.org/10.1016/0022-5088(84)90078-X).
  - [25] P.E. Moorhead, P.L. Stone, *Survey of Properties of T111*, 1970.
  - [26] S.J. Zinkle, Thermophysical and Mechanical Properties for Ta-8% W-2% Hf, *Tech. Rep.*, Oak Ridge National Laboratory, Oak Ridge, 1998.
  - [27] C. Campbell, *Elements of Metallurgy and Engineering Alloys*, ASM International, 2008.
  - [28] W.D. Klopp, A review of chromium, molybdenum, and tungsten alloys, *J. Less Common. Met.* 42 (3) (1975) p261–p278, [https://doi.org/10.1016/0022-5088\(75\)90046-6](https://doi.org/10.1016/0022-5088(75)90046-6).
  - [29] R. Wadsack, R. Pippan, B. Schedler, Chromium – a material for fusion technology, *Fusion Eng. Des.* 58–59 (2001) p743–p748, [https://doi.org/10.1016/S0920-3796\(01\)00554-3](https://doi.org/10.1016/S0920-3796(01)00554-3).
  - [30] B.A. Loomis, A.B. Hull, D.L. Smith, Evaluation of low-activation vanadium alloys for use as structural material in fusion reactors, *J. Nucl. Mater.* 179–181 (PART 1) (1991) p148–p154, [https://doi.org/10.1016/0022-3115\(91\)90030-B](https://doi.org/10.1016/0022-3115(91)90030-B).
  - [31] D.L. Smith, M.C. Billone, K. Natesan, Vanadium-base alloys for fusion first-wall/blanket applications, *Int. J. Refract. Metals Hard Mater.* 18 (2000) p213–p224, [https://doi.org/10.1016/S0263-4368\(00\)00037-8](https://doi.org/10.1016/S0263-4368(00)00037-8).
  - [32] D.L. Smith, H.M. Chung, B.A. Loomis, H.C. Tsai, Reference vanadium alloy V-4Cr-4Ti for fusion application, *J. Nucl. Mater.* 233–237 (PART 1) (1996) p356–p363, [https://doi.org/10.1016/S0022-3115\(96\)00231-0](https://doi.org/10.1016/S0022-3115(96)00231-0).
  - [33] *Structural Design Criteria for In-vessel Components (SDC-IC) v3.3*, ITER Doc. G 74 MA 8 01-05-28 W0.2, ITER Organisation, 2013.
  - [34] *ITER Material Properties Handbook*, Tech. Rep. ITER Doc. G 74 MA 16, ITER Organisation, 2005.
  - [35] Plansee, <https://www.plansee.com>.
  - [36] S. Zinkle, N.M. Ghoniem, Operating temperature windows for fusion reactor structural materials, *Fusion Eng. Des.* 51–52 (52) (2000) p55–p71, [https://doi.org/10.1016/S0920-3796\(00\)00320-3](https://doi.org/10.1016/S0920-3796(00)00320-3).
  - [37] R. Bamber, R. Morrell, C. Waldon, M. Shannon, Design substantiation of ceramic materials on fusion reactor confinement boundaries, *Fusion Eng. Des.* 125 (2017) p238–p289, <https://doi.org/10.1016/j.fusengdes.2017.07.001>.
  - [38] Y. Ueda, K. Schmid, M. Balden, J.W. Coenen, T. Loewenhoff, A. Ito, A. Hasegawa, C. Hardie, M. Porton, M. Gilbert, Baseline high heat flux and plasma facing materials for fusion, *Nucl. Fusion* 57 (9) (2017) 92006.
  - [39] P. Gavila, B. Riccardi, G. Pintsuk, G. Ritz, V. Kuznetsov, A. Durocher, High heat flux testing of EU tungsten monoblock mock-ups for the ITER divertor, *Fusion Eng. Des.* 98–99 (2015) p1305–p1309, <https://doi.org/10.1016/j.fusengdes.2014.12.006>.
  - [40] M. Fursdon, T. Barrett, F. Domptail, L.M. Evans, N. Luzginova, N.H. Greuner, J.-H. You, M. Li, M. Richou, F. Gallay, E. Visca, The development and testing of the thermal break divertor monoblock target design delivering 20 MWm<sup>-2</sup> heat load capability, *Phys. Scripta* T170 (2017) p014042, <https://doi.org/10.1088/1402-4896/aa8c8e>.
  - [41] M. Richou, F. Gallay, I. Chu, M. Li, P. Magaud, M. Missirlian, S. Rocella, E. Visca, J.-H. You, Status on the W monoblock type high heat flux target with graded interlayer for application to DEMO divertor, *Fusion Eng. Des.* 124 (2017) p338–p343, <https://doi.org/10.1016/j.fusengdes.2017.03.087>.
  - [42] J.H. You, G. Mazzone, E. Visca, C. Bachmann, E. Autissier, T. Barrett, V. Cocilovo, F. Crescenzi, P.K. Domalpalay, D. Dongiovanni, S. Entler, G. Federici, P. Frosi, M. Fursdon, H. Greuner, D. Hancock, D. Marzullo, S. McIntosh, A.V. Müller, M.T. Porfiri, G. Ramogida, J. Reiser, M. Richou, M. Rieth, A. Rydz, R. Villari, V. Widak, Conceptual design studies for the European DEMO divertor: rationale and first results, *Fusion Eng. Des.* 109–111 (PART B) (2016) p1598–p1603, <https://doi.org/10.1016/j.fusengdes.2015.11.012>.
  - [43] T. Barrett, D. Hancock, M. Kalsey, W. Timmis, M. Porton, Design study of a water-cooled divertor: alternative concepts, *Tech. Rep.* (2012). EFDA, WP12-DA502-T02-D3/CCFE/PS.
  - [44] N.R. Hamilton, J. Wood, D. Easton, M.B.O. Robbie, Y. Zhang, A. Galloway, Thermal autofrettage of dissimilar material brazed joints, *Mater. Des.* 67 (2015) p405–p412, <https://doi.org/10.1016/j.matdes.2014.11.019>.
  - [45] D. Maisonnier, I. Cook, S. Pierre, B. Lorenzo, D.P. Luigi, G. Luciano, N. Prachai, P. Aldo, DEMO and fusion power plant conceptual studies in Europe, *Fusion Eng. Des.* 81 (8–14) (2006) p1123–p1130, <https://doi.org/10.1016/j.fusengdes.2005.08.055>, PART B.
  - [46] R.A. Forrest, *The European Activation File: EAF-2007 Biological, Clearance and Transport Libraries*, 2007. Tech. Rep. UKAEA-FUS-538, EURATOM/UKAEA Fusion.
  - [47] R.A. Forrest, A. Tabasso, C. Danani, S. Jakhar, A.K. Shaw, *Handbook of Activation Data Calculated Using EASY-2007*, 2009. Tech. Rep. UKAEA FUS 552, EURATOM/UKAEA Fusion.
  - [48] M. Gilbert, L. Packer, J.-C. Sublet, R. Forrest, Inventory simulations under neutron irradiation: visualization techniques as an aid to materials design, *Nucl. Sci. Eng.* 177 (3) (2014) p291–p306, <https://doi.org/10.1318/NSE13-76>.
  - [49] D. Stork, P. Agostini, J.L. Boutard, D. Buckthorpe, E. Diegele, S.L. Dudarev, C. English, G. Federici, M.R. Gilbert, S. Gonzalez, A. Ibarra, C. Linsmeier, A. Li Puma, G. Marbach, P.F. Morris, L.W. Packer, B. Raj, M. Rieth, M.Q. Tran, D.J. Ward, S.J. Zinkle, Developing structural, high-heat flux and plasma facing materials for a near-term DEMO fusion power plant: the EU assessment, *J. Nucl. Mater.* 455 (1–3) (2014) p277–p291, <https://doi.org/10.1016/j.jnucmat.2014.06.014>.
  - [50] B.R. Simonovi, S.V. Mentus, R. Dimitrijevi, Kinetic and structural aspects of tantalum hydride formation, *J. Serb. Chem. Soc.* 68 (8–9) (2003) p657–p663.
  - [51] S. Ishiyama, Y. Muto, Y. Kato, S. Nishio, T. Hayashi, Y. Nomoto, Study of steam, helium and supercritical CO<sub>2</sub> turbine power generations in prototype fusion power reactor, *Prog. Nucl. Energy* 50 (2008) p325–p332, <https://doi.org/10.1016/j.pnucene.2007.11.078>.
  - [52] M. Porton, H. Latham, Z. Vizvary, E. Surrey, Balance of plant challenges for a near-term EU demonstration power plant, in: 2013 IEEE 25th Symp. Fusion Eng. IEEE, 2013, pp. 1–6, <https://doi.org/10.1109/SOFE.2013.6635331>.
  - [53] P. S. Weitzel, J. M. Tanzosh, B. Boring, N. Okita, T. Takahashi, N. Ishikawa, Advanced ultra-supercritical power plant (700 to 760°C) design for Indian coal, in: ASME 2011 Power Conference Collocated with JSME ICOPE 2011.

- [54] J.I. Linares, L.E. Herranz, I. Fernández, A. Cantizano, B.Y. Moratilla, Supercritical CO<sub>2</sub> Brayton power cycles for DEMO fusion reactor based on helium cooled lithium lead blanket, *Appl. Therm. Eng.* 76 (2015) p123–p133, <https://doi.org/10.1016/j.applthermaleng.2014.10.093>.
- [55] J.I. Linares, A. Cantizano, E. Arenas, B.Y. Moratilla, V. Martín-Palacios, L. Batet, Recuperated versus single-recuperator re-compressed supercritical CO<sub>2</sub> Brayton power cycles for DEMO fusion reactor based on dual coolant lithium lead blanket, *Energy* 140 (2017) p307–p317, <https://doi.org/10.1016/j.energy.2017.08.105>.
- [56] V.I. Subbotin, M.N. Arnol'dov, F.A. Kozlov, A.L. Shimkevich, Liquid-metal coolants for nuclear power, *At. Energy* 92 (1) (2002) p29–p40, <https://doi.org/10.1023/A:1015050512710>.
- [57] F. Najmabadi, A. Abdou, L. Bromberg, T. Brown, V.C. Chan, M.C. Chu, F. Dahlgren, L. El-Guebaly, P. Heitzenroeder, D. Henderson, H. E. St John, C.E. Kessel, L.L. Lao, G.R. Longhurst, S. Malang, T.K. Mau, B.J. Merrill, R.L. Miller, E. Mogahed, R.L. Moore, T. Petrie, D.A. Petti, P. Politzer, A.R. Raffray, D. Steiner, I. Sviatoslavsky, P. Synder, G.M. Syaebler, A.D. Turnbull, M.S. Tillack, L.M. Waganer, X. Wang, P. West, P. Wilson, The ARIES-AT advanced tokamak, Advanced technology fusion power plant, *Fusion Eng. Des.* 80 (1–4) (2006) p3–p23, <https://doi.org/10.1016/j.fusengdes.2005.11.003>.
- [58] S. Mirnov, V. Evtikhin, The tests of liquid metals (Ga, Li) as plasma facing components in T-3M and T-11M tokamaks, *Fusion Eng. Des.* 81 (1–7) (2006) p113–p119, <https://doi.org/10.1016/j.fusengdes.2005.10.003>.
- [59] R. Nygren, T. Rognlien, M. Rensink, S. Smolentsev, M. Youssef, M. Sawan, B. Merrill, C. Eberle, P. Fogarty, B. Nelson, D. Sze, R. Majeski, A fusion reactor design with a liquid first wall and divertor, *Fusion Eng. Des.* 72 (1–3) (2004) p181–p221, <https://doi.org/10.1016/j.fusengdes.2004.07.007>.
- [60] L.M. Giancarli, M. Abdou, D.J. Campbell, V.A. Chuyanov, M.Y. Ahn, M. Enoeda, C. Pan, Y. Poitevin, E. Rajendra Kumar, I. Ricapito, Y. Strebkov, S. Suzuki, P.C. Wong, M. Zmitko, Overview of the ITER TBM Program, 2012, <https://doi.org/10.1016/j.fusengdes.2011.11.005>.
- [61] D. Rapisarda, I. Fernandez, I. Palermo, F.R. Ugorri, L. Maqueda, D. Alonso, T. Melichar, O. Frýbort, L. Vála, M. Gonzalez, P. Norajitra, H. Neuberger, A. Ibarra, Status of the engineering activities carried out on the European DCLL, *Fusion Eng. Des.* 124 (2017) p876–p881, <https://doi.org/10.1016/j.fusengdes.2017.02.022>.
- [62] N. Rumbaut, F. Casteels, M. Brabers, M. Soenen, H. Tas, J. De Keyser, Corrosion of refractory metals in liquid lithium, in: *Mater. Behav. Phys. Chem. Liq. Met. Syst.*, Springer US, Boston, MA, 1982, pp. 131–139, [https://doi.org/10.1007/978-1-4684-8366-6\\_14](https://doi.org/10.1007/978-1-4684-8366-6_14).
- [63] P. Fiffis, A. Press, W. Xu, D. Andruczyk, D. Curreli, D.N. Ruzic, Wetling properties of liquid lithium on select fusion relevant surfaces, *Fusion Eng. Des.* 89 (12) (2014) p2827–p2832, <https://doi.org/10.1016/j.fusengdes.2014.03.060>.
- [64] D. Samuel, Molten Salt Coolants for High Temperature Reactors: a Summary of Key R&D Activities and Challenges, *Internsh. Rep.*, IAEA, 2009.
- [65] N. Taylor, B. Merrill, L. Cadwallader, L. Di Pace, L. El-Guebaly, P. Humrickhouse, D. Panayotov, T. Pinna, M.-T. Porfiri, S. Reyes, M. Shimada, S. Willms, Materials-related issues in the safety and licensing of nuclear fusion facilities, *Nucl. Fusion* 57 (9) (2017), <https://doi.org/10.1088/1741-4326/57/9/092003>, 092003.
- [66] M. Rieth, S. Dudarev, S. Gonzalez de Vicente, J. Aktaa, T. Ahlgren, S. Antusch, D. Armstrong, M. Balden, N. Baluc, M.-F. Barthe, W. Basuki, M. Battabyal, C. Becquart, D. Blagoeva, H. Boldyryeva, J. Brinkmann, M. Celino, L. Ciupinski, J. Correia, A. De Backer, C. Domain, E. Gaganidze, C. García-Rosales, J. Gibson, M. Gilbert, S. Giusepponi, B. Gludovatz, H. Greuner, K. Heinola, T. Höschen, A. Hoffmann, N. Holstein, F. Koch, W. Krauss, H. Li, S. Lindig, J. Linke, C. Linsmeier, P. López-Ruiz, H. Maier, J. Matejcek, T. Mishra, M. Muhammed, A. Muñoz, M. Muzyk, K. Nordlund, D. Nguyen-Manh, J. Opschoor, N. Ordás, T. Palacios, G. Pintsuk, R. Pippa, J. Reiser, J. Riesch, S. Roberts, L. Romaner, M. Rosinski, M. Sanchez, W. Schulmeyer, H. Traxler, A. Ureña, J. van der Laan, L. Veleva, S. Wahlberg, M. Walter, T. Weber, T. Weitkamp, S. Wurster, M. Yar, J.-H. You, A. Zivelonghi, Recent progress in research on tungsten materials for nuclear fusion applications in Europe, *J. Nucl. Mater.* 432 (1–3) (2013) p482–p500, <https://doi.org/10.1016/j.jnucmat.2012.08.018>.
- [67] D. Hancock, D. Homfray, M. Porton, I. Todd, B. Wynne, Exploring complex high heat flux geometries for fusion applications enabled by additive manufacturing, *Fusion Eng. Des.* (2018), <https://doi.org/10.1016/j.fusengdes.2018.02.097>. In Press.
- [68] G. Pintsuk, S. Brünings, J.-E. Döring, J. Linke, I. Smid, L. Xue, Development of W/Cu functionally graded materials, *Fusion Eng. Des.* 66–68 (2003) p237–p240, [https://doi.org/10.1016/S0920-3796\(03\)00220-5](https://doi.org/10.1016/S0920-3796(03)00220-5).
- [69] J.-H. You, A. Brendel, S. Nawka, T. Schubert, B. Kieback, Thermal and mechanical properties of infiltrated W/CuCrZr composite materials for functionally graded heat sink application, *J. Nucl. Mater.* 438 (1–3) (2013) 1–6, <https://doi.org/10.1016/j.jnucmat.2013.03.005>.
- [70] M. Galatanu, M. Enculescu, A. Galatanu, High temperature thermo-physical properties of SPS-ed W-Cu functional gradient materials, *Mater. Res. Express* 5 (2) (2018), 026502.
- [71] J. Reiser, M. Rieth, A. Möslang, B. Dafferner, J. Hoffmann, T. Mrotzek, A. Hoffmann, D. Armstrong, X. Yi, Tungsten foil laminate for structural divertor applications Joining of tungsten foils, *J. Nucl. Mater.* 436 (1–3) (2013) p47–p55, <https://doi.org/10.1016/j.jnucmat.2013.01.295>.
- [72] M. Porton, B. Wynne, R. Bamber, C. Hardie, M. Kalsey, Structural integrity for DEMO: an opportunity to close the gap from materials science to engineering needs, *Fusion Eng. Des.* 109–111 (2016) p1247–p1255, <https://doi.org/10.1016/j.fusengdes.2015.12.050>. Part B.