

PLASMA FACING MATERIALS FOR THE JET ITER-LIKE WALL

C. THOMSER,^{a,*} V. BAILESCU,^b S. BREZINSEK,^a J. W. COENEN,^a H. GREUNER,^c
T. HIRAI,^d J. LINKE,^a C. P. LUNGU,^e H. MAIER,^c G. MATTHEWS,^f PH. MERTENS,^a R. NEU,^c
V. PHILIPPS,^a V. RICCARDO,^f M. RUBEL,^g C. RUSET,^e A. SCHMIDT,^a I. UYTDEHOUWEN,^h
and JET EFDA CONTRIBUTORS^{i,†}

^aForschungszentrum Jülich, EURATOM Association, D-52425 Jülich, Germany

^bNuclear Fuel Plant, Pitesti, Romania

^cMax-Planck-Institut für Plasmaphysik, EURATOM Association, D-85748 Garching, Germany

^dForschungszentrum Jülich, EURATOM Association, D-52425 Jülich, Germany; Presently at ITER Organization
Route de Vinon sur Verdon, F-13115 St Paul Lez Durance, France

^eNational Institute for Laser, Plasma and Radiation Physics, Association EURATOM-MEDC, Bucharest, Romania

^fEURATOM-CCFE Fusion Association, Culham Science Centre, Abingdon OX14 3DB, United Kingdom

^gAlfvén Laboratory, Royal Institute of Technology (KTH), Association EURATOM-VR, 10044, Stockholm, Sweden

^hSCK•CEN, Belgian Nuclear Research Centre, Boeretang 200, B-2400 Mol, Belgium

ⁱJET-EFDA, Culham Science Centre, Abingdon, OX14 3DB, United Kingdom

Received December 22, 2011

Accepted for Publication April 17, 2012

The chosen materials for plasma facing components for the deuterium/tritium phase of ITER are beryllium and tungsten. These materials have already been widely investigated in various devices like ion beam or electron beam tests. However, the operation of this material combination in a large tokamak including plasma wall interaction, material degradation, erosion and material mixing has not been proven yet.

The ITER-like Wall, which has been recently installed in JET, consists of a combination of bulk tungsten and tungsten coated CFC divertor tiles as well as bulk beryllium and beryllium coated INCONEL in the main chamber. The experiments in JET will provide the first

fully representative test of the ITER material choice under relevant conditions.

This paper concentrates on material research and developments for the materials of the JET ITER-like Wall with respect to mechanical and thermal properties. The impact of these materials and components on the JET operating limits with the ITER-like Wall and implications for the ongoing scientific program will be summarised.

KEYWORDS: ITER-like wall, beryllium, tungsten

Note: The figures in this paper are in color only in the electronic version.

I. INTRODUCTION

Materials for plasma facing components in nuclear fusion devices have to withstand a multitude of extreme loading conditions. Steady state as well as transient heat loads are responsible for material degradation like thermal shock and thermal fatigue cracks, recrystallisation and melting. The impact of neutron induced material deg-

radation on the lifetime of wall components plays also an important role. Furthermore, tritium fuel retention and transmutation of elements is a major concern for the operation of nuclear fusion devices. In addition chemical as well as physical sputtering, which leads to erosion and redeposition processes of mixed layers, has to be taken into account. Finally plasma compatibility of the materials is a main challenge for plasma operation. Especially for high-Z materials the maximum tolerable impurity concentration in the plasma is quite small.

Due to these reasons the number of candidate materials for high thermally loaded plasma facing components

*E-mail: c.thomser@fz-juelich.de

†See the Appendix of F. Romanelli et al., Proceedings of the 23rd IAEA Fusion Energy Conference 2010, Daejeon, Korea.

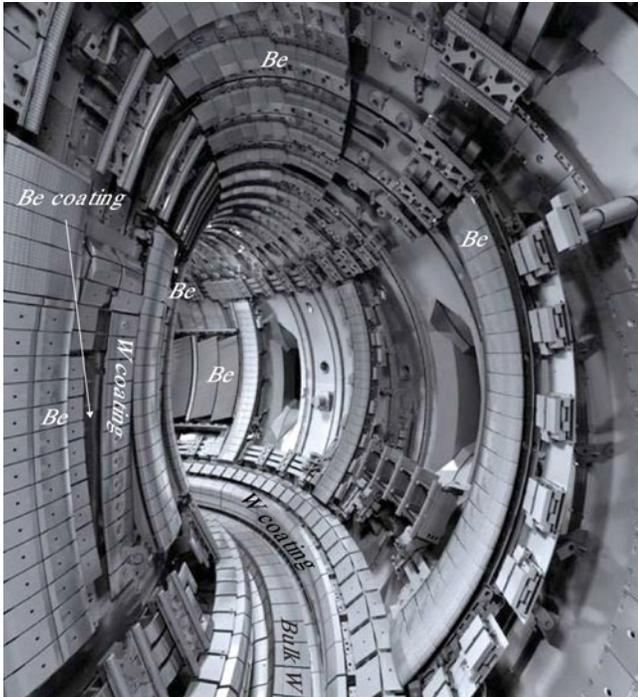


Fig. 1. Material configuration for the ITER-like Wall.

is limited. The actual material combination for the deuterium/tritium phase of ITER consists of beryllium for the main chamber wall and tungsten for the divertor. It has to be pointed out that this special material combination of beryllium and tungsten has never been tested in tokamak devices so far. Therefore the ITER-like Wall project has been launched in JET in order to investigate the current choice of plasma facing materials for the deuterium/tritium phase of ITER.¹⁻³

The material configuration for the ITER-like Wall installation in JET is presented in Fig. 1.

In the high heat loaded divertor area, bulk tungsten and tungsten coatings on CFC substrates are applied. Beryllium coatings on INCONEL^{®a} alloy 625 between the limiters (low heat flux area) and bulk beryllium tiles for the main chamber wall are installed.

This paper gives an overview on material developments of plasma facing components for the ITER-like Wall project. It summarises the material aspects for the beryllium components and major material properties. The information concerning tungsten focuses mainly on embrittlement and melting. In addition to bulk tungsten, also tungsten coatings have been applied partially in the divertor region. The development, testing, manufacturing and performance of these tungsten coatings will be reported as well. Finally, some results of beryllium coat-

ing characterisation on INCONEL substrates for low heat flux areas are presented.

II. SCOPE OF THE ITER-LIKE WALL PROJECT

The research topics for the ITER-like Wall project have already been comprehensively explained in literature⁴ and will only be shortly summarised in this paragraph. They can be separated in two parts, topics for the beryllium main chamber wall and issues for the tungsten divertor.

First, erosion and migration of the beryllium at the main wall material in ITER relevant scenarios will be examined. Furthermore, the behavior of molten beryllium and its impact on operation and wall lifetime as well as fuel retention in beryllium tiles and in co-deposited layers will be investigated. In addition the interaction of beryllium with background oxygen, wall conditioning and machine start up will be addressed experimentally.⁴

For the tungsten divertor, research is focused on fatigue lifetime and resistance of plasma facing materials to transient power loads (Edge Localised Modes). Additionally the alloying of tungsten with beryllium, which leads to a reduction of the melting point, needs to be taken into account. Moreover, the compatibility with ITER relevant plasma scenarios (tungsten sources and accumulation of tungsten in the core of the plasma) and fuel retention are important aspects for the tungsten divertor operation.⁴

In contrast to ITER, all plasma-facing components in the ITER-like Wall are only inertially cooled. Thus, the power handling capability of the ITER-like Wall is strongly determined by the heat capacity. The operation of the JET ITER-like Wall started in 2011. That is the reason why this paper contains no results of the current ITER-like Wall operation in JET. The first post-mortem analysis of materials from the ITER-like Wall is foreseen for 2012 (Ref. 5).

III. BERYLLIUM

Beryllium is a metal with a low atomic number and consists of a hexagonal closed packed crystallographic structure. Beryllium has a high thermal conductivity (190 W/(m K) at room temperature) and a good plasma compatibility, which means that it has a high allowable concentration in the fusion plasma. The maximum allowable concentration of beryllium in the plasma is given in literature with 15%. For a light metal, beryllium has an extraordinarily high melting point. Nevertheless, in absolute numbers the melting point of 1287°C is one of the major drawbacks of the material beside erosion and low neutron radiation resistance. Neutron radiation damage in beryllium results in embrittlement by defect formation.

^aINCONEL is a registered trademark of the Special Metals Corporation group of companies.

Moreover, transmutation (tritium and helium formation) leads to gas driven swelling and embrittlement especially for high temperature irradiation.⁶ The behavior in relation to oxygen can be seen from two different sides. On the one hand beryllium is able to remove oxygen from the plasma due to its oxygen affinity; on the other hand beryllium oxide in the volume of the material leads to a decrease in thermal shock resistance.

For the ITER-like Wall project, the former JET S65C VHP scrap beryllium tiles were recycled into new S65J HIP beryllium blocks. Solid beryllium main wall inner and outer guard and protection limiter tiles were designed with a segmented castellated construction mounted on vacuum cast INCONEL 625 carriers in order to reduce eddy currents and thermal stresses on the plasma facing surface. Slots are cut by electro machining (EDM) followed by chemical etching in order to remove surface impurities left from EDM processing. These limiters take most of the main wall power load. As an optimal size for the castellation, an area of $12 \times 12 \text{ mm}^2$ with a depth of 16 mm was chosen based on detailed calculations of thermally induced stresses. In Fig. 2 a detailed view of the outer poloidal limiter of the tile carrier with fixing bolts and INCONEL cast support is presented. Further details on the engineering aspects of the beryllium components can be found in literature.⁷⁻¹⁰ Details of the application of beryllium as a first wall material in JET in the past are reported in literature as well. JET has extensively used beryllium in a variety of inertially cooled components that have sustained in total, several thousand of plasma discharges. Local melting and micro cracking of small regions was found. Castellation of tiles is mandatory in order to avoid thermal fatigue.¹¹

The quantification of beryllium erosion is one of the major aspects of beryllium material performance for the

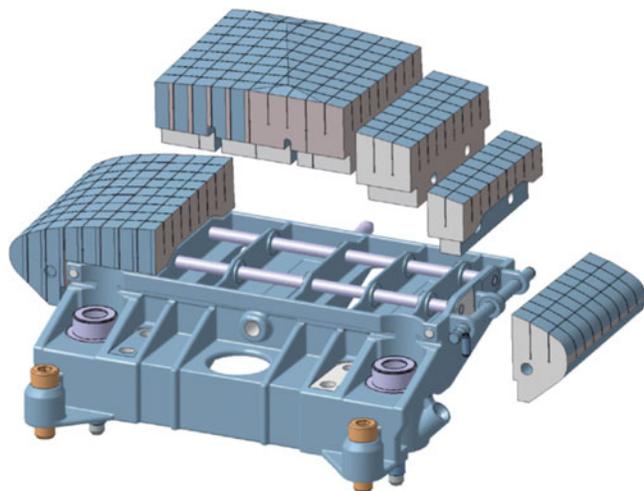


Fig. 2. Detailed view of an outer poloidal limiter (S65J HIP beryllium) with tile carrier fixing bolts and vacuum cast INCONEL 625 support.

ITER-like Wall by postmortem analysis in order to give the best possible predictions for ITER. Therefore so called marker tiles are applied, which are allocated in special positions on selected tiles of the inner and outer poloidal limiters. The beryllium marker tiles consist of a structure of $8-10 \mu\text{m}$ beryllium on a nickel interlayer of $2-3 \mu\text{m}$ followed by the bulk beryllium.¹²⁻¹⁴

Nickel was chosen as interlayer material due to the small mismatch in thermal expansion coefficients ($13 \times 10^{-6} \text{ K}^{-1}$ for nickel and $16 \times 10^{-6} \text{ K}^{-1}$ for beryllium at room temperature) and the absence of formation of intermetallic phases with beryllium up to approximately 1000°C . Thermionic vacuum arc technique was selected and optimized in order to deposit the layers.^{12,13,15}

Before the application in the ITER-like Wall, the marker tile samples were tested in an electron beam test facility at heat fluxes of $1-6 \text{ MW/m}^2$ for 10 s for screening. A damage threshold value of approximately 5 MW/m^2 was determined. Furthermore the marker tile samples withstood cyclic loading for 50 cycles up to 3.5 MW/m^2 without damage. The formation of intermetallic phases was not observed during the tests and these marker tiles perform well under the operational requirements of the ITER-like Wall of about 1 MW/m^2 for normal operation.¹³

IV. BERYLLIUM COATINGS

In between the limiters in the low heat flux area $7-9 \mu\text{m}$ thick beryllium coatings on an INCONEL 625 substrate are applied. Thermal cycling for 50 cycles at 1 MW/m^2 for 10 s was applied in high heat flux tests, where no delamination was observed. The microstructure of the coatings before and after these tests is shown in Fig. 3.

In Fig. 4 the temperature increase during the thermal loading as a function of the energy density is presented. The circle symbols represent the temperature increase of the beryllium coating on an INCONEL substrate with a thickness of $3.3-3.6 \text{ mm}$. The square symbols represent thicker INCONEL substrates. It can be concluded, that for the loading conditions similar to those in JET, the

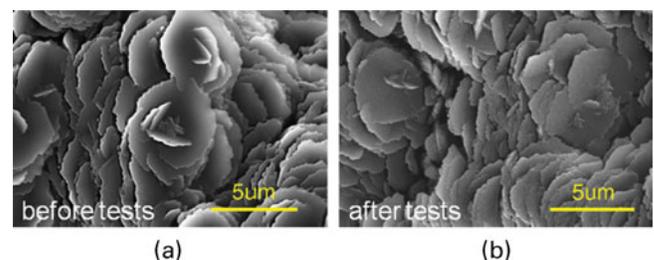


Fig. 3. Beryllium coatings on INCONEL substrate ($7-9 \mu\text{m}$ thick films) Thermal loads 1 MW/m^2 for 10 s, 50 cycles.¹⁶

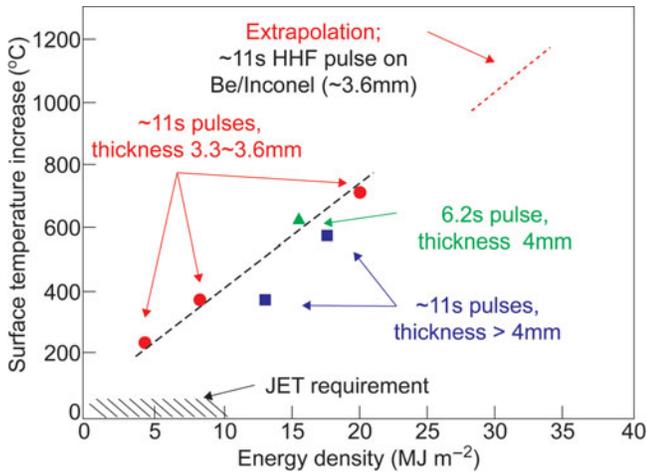


Fig. 4. Surface temperature increase as a function of deposited energy (thickness indicates the thickness of the INCONEL substrate).¹⁶

heat capacity of the samples (in this case thickness of the INCONEL substrates) is an important factor to determine the maximum surface temperatures. As expected, a lower temperature increase occurred at samples with a higher heat capacity. Using a linear extrapolation to the higher energy density range, the temperature increase of the samples with ~ 3.5 mm thickness would follow the dotted line. The extrapolation indicates that the beryllium coatings would start to melt at loads above 30 MJ/m^2 when the loading starts at the temperature of 200°C (corresponds to the base temperature of the JET ITER-like Wall). Moreover, it has to be mentioned that no delamination of beryllium coatings was found even at the highest tested power density of 2.6 MW/m^2 for 6.2 s .^{1,16}

It can be concluded that these coatings show a good performance well beyond JET requirements because of the small mismatch in thermal expansion between the

coating and the substrate. Moreover no intermetallic phases are formed up to approximately 1000°C .^{1,16}

V. TUNGSTEN

Tungsten will be used for the high heat flux areas of nuclear fusion devices. The important advantage of tungsten is its high melting point (3422°C). Moreover tungsten has a high thermal conductivity [173 W/(m K) at room temperature; 100 W/(m K) at 1527°C] and a low tritium retention potential.

Unfortunately, the cubic body centered crystallographic structure of tungsten leads to a high ductile to brittle transition temperature in comparison with cubic face centered metals due to less crystallographic slip systems. Thus tungsten is sensitive to brittle crack formation due to its limited plasticity in the low temperature range. In this context neutron and hydrogen embrittlement even degrades the deformation capability of the material. Furthermore thermal fatigue has to be taken into account.

Results of tungsten material performance and brittle crack formation under transient heat loads in dependence on temperature and absorbed power density can be found in literature.^{17–20} Recrystallisation of tungsten starting at about 1200°C influences the material performance under transients as well. The impact of tungsten melting on the power handling capability of tokamaks and the behavior of resolidified tungsten material under transients has already been investigated. Resolidified layers are less resistant to thermal shocks and the power handling capability in tungsten melting experiments in the tokamak TEXTOR at Forschungszentrum Jülich was also significantly decreased.²¹

A schematic picture of the ITER-like Wall material configuration for the divertor is presented in Fig. 5. The limit of deposited energy for the ITER-like Wall tungsten divertor stacks is mainly determined by the engineering

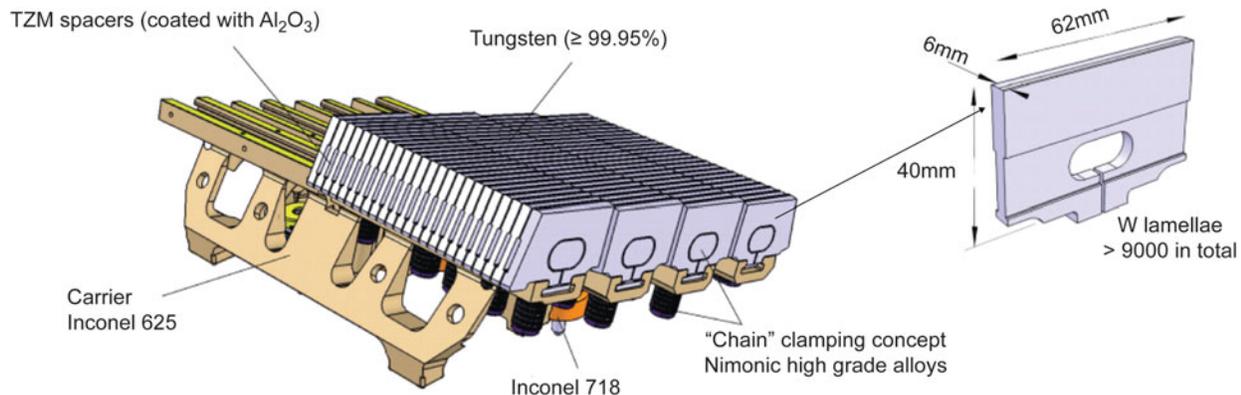


Fig. 5. Schematic picture of a bulk tungsten divertor tile (left side); in total over 9000 shaped bulk tungsten lamellas (right side) are installed in the JET-ITER-like Wall.

limit of 330°C for the clamping system and 600°C for the INCONEL carrier. Engineering aspects of the tungsten divertor material configuration are comprehensively summarised in literature.^{22,23} The lower limit for the tungsten surface temperature is the ductile to brittle transition temperature, which is below 200°C measured in four point bending tests. In the temperature range of 1200°C–2200°C (above the recrystallisation temperature for tungsten of ~1200°C) thermal fatigue of tungsten has to be taken into account.²³

A standard tungsten stack was successfully tested in high heat flux tests in the ion beam test facility Marion at Forschungszentrum Jülich. The exposure of a full scale prototype of the standard tungsten stack in the Marion facility shows that an energy density of up to 60 MJ/m² per stack can be handled with the bulk tungsten tile.²³

VI. TUNGSTEN COATINGS

The bulk tungsten divertor tiles could only be accommodated on the horizontal part of the JET divertor due to technical reasons. The majority of the ITER-like Wall divertor and some highly loaded tiles in the main chamber (for example beam shine through areas) consist of tungsten coating on a DMS 780 CFC substrate (Fig. 6).


The main challenge for the application of tungsten coatings within the ITER-like Wall project is the fact that the tiles to be coated were made from an anisotropic carbon-fiber reinforced carbon material (CFC). This leads to an anisotropic thermal expansion of the CFC substrate and consequently to an anisotropic mismatch between the substrate and the tungsten coating. Due to this mismatch between tungsten and CFC a research and

development phase was initiated in early 2005 involving various EURATOM associations to produce a total of 14 different types of coatings with respect to the employed deposition processes, coating thicknesses, and interlayer types with the goal of identifying a possible solution to the ITER-like Wall needs.²⁴

These different types of coatings were then subjected to a program of qualification tests the main part of which was high heat flux testing in the neutral beam facility GLADIS (Refs. 24, 25, and 26). After a thermal screening where the coatings were exposed to power densities of up to 23.5 MW/m² (exceeding 2200°C peak surface temperature), the most promising coating types were subjected to a low cycle fatigue loading program for 200–300 pulses at 10.5 MW/m² corresponding to a peak surface temperature of 1500°C.

The finally selected coating method was the technique of combined magnetron sputtering and ion implantation, which combines conventional magnetron sputtering with the application of high voltage pulses for the purpose of stress relaxation in the coating.^{27–29} 10–20 μm thick tungsten coatings on 3 μm molybdenum interfaces were deposited on a total of about 1700 JET CFC tiles. A picture of the microstructure of these coatings is shown in Fig. 7. The coated CFC tiles are presented in Fig. 8.

These coatings were subsequently tested in the electron beam facility JUDITH 1 and JUDITH 2 at Forschungszentrum Jülich, Germany.^{30,31} The results of ELM-like heat load tests in JUDITH 1 are presented in Fig. 9. Tests were always performed for 100 pulses of 1 ms at different absorbed power densities (79–316 MW/m²) and temperatures (room temperature up to 400°C). Delamination and cracking start to occur at absorbed power densities of about 158 MW/m². Below this value no failure of the coatings was observed. Failure occurrence is mainly dependent on the absorbed power density and less affected by the test temperature of the specimens.

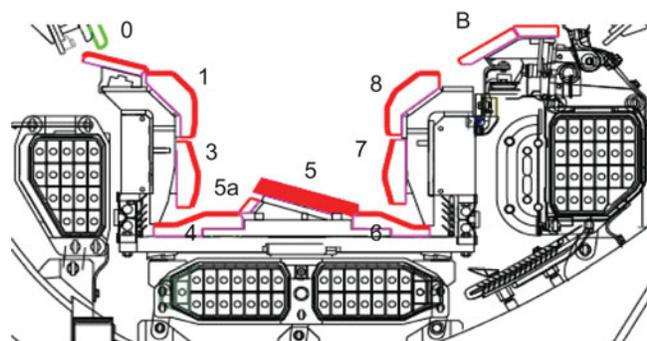

Tile 5: bulk tungsten

Tiles 1, 6, 7, 8: 20–25 μm W coating with Mo interlayer (substrate DMS 780)

Tiles 0, 3, 4, 5a, B, C: 10–15 μm W coating with Mo interlayer (CFC substrate DMS 780)

Fig. 6. Schematic illustration of JET divertor material configuration in the ITER-like Wall Project.

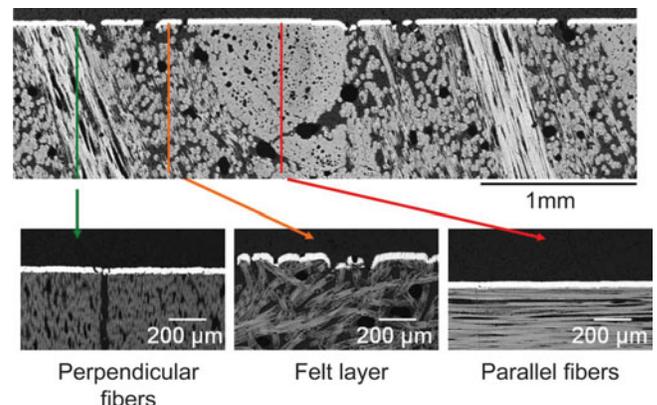


Fig. 7. Metallographic images of longitudinal (top) and transverse (bottom row) cross sections of the CFC substrate and the tungsten coating.³⁰

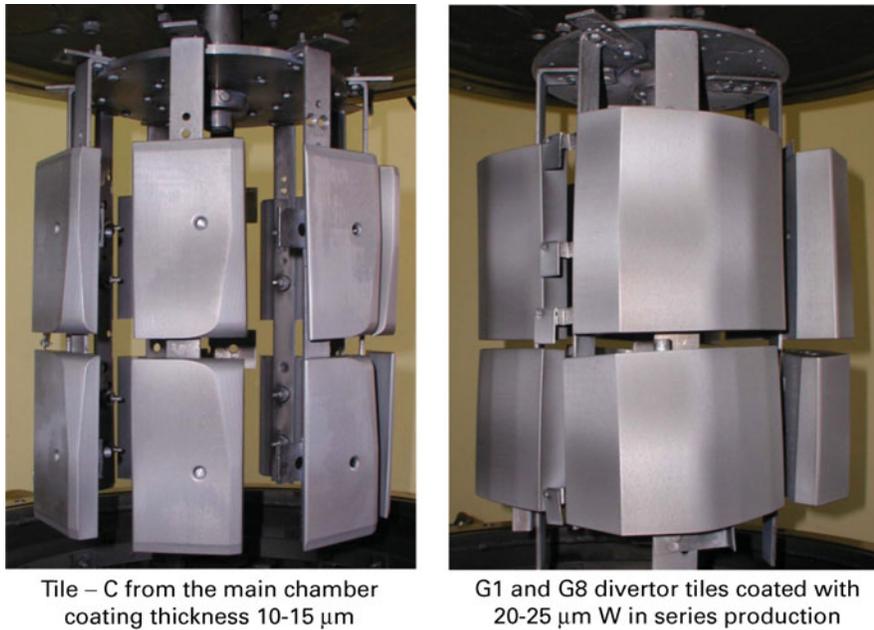


Fig. 8. Tungsten coated CFC tiles in the coating device.²⁹

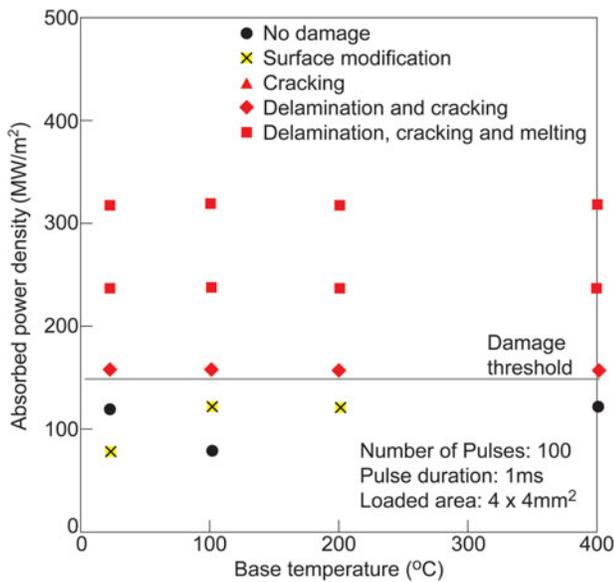


Fig. 9. Failure occurrence of tungsten coatings under ELM-like heat loads in dependence on absorbed power density and test temperature.³²

It always occurs first on fibers parallel to the surface of the CFC substrate due to the high mismatch in thermal expansion coefficients of the coating and substrate and the bad thermal conductivity of this fiber orientation into the bulk of the material. Beside cracking and delamination even melting is observed at absorbed power densities of about 237 MW/m². It has to be pointed out that

melting of the coating is only a result of the delamination of the coating.³² Only the very largest JET ELMs approach 158 MW/m² at the outer strike point (bulk tungsten tile will be used for most experiments).

Finally coating failure due to carbide formation at temperatures of 1350°C for 1–20 h was investigated in the neutral beam facility GLADIS. The tests were performed at 16.5 MW/m² for 1.5 s and up to 200 pulses. Clear threshold behavior for the heating time was found: Coating with a heat treatment above 2–5 hours, corresponds to the carbide formation, are prone for cracking and delamination.³³

VII. SUMMARY AND OUTLOOK

In order to summarize the results, a comparison of the heat load limits between ITER and the ITER-like Wall in JET is presented in Table I for the major material choices of beryllium for the first wall and tungsten for the divertor. It has to be pointed out, that a direct comparison is difficult since there are major differences in the technology like the cooling concept for the components and the size of the device. ITER has an approximately ten times higher vacuum vessel volume compared to JET and actively water cooled components.

For the operation with the ITER-like Wall during the years 2011 and 2012 the material characterization focuses mainly on fuel retention and material migration, material limits and long term samples under transient and steady-state heat loads. A list of material related experiments in this period is provided below^{35,40}:

TABLE I

Comparison of Heat Loads for the ITER-Like Wall and ITER for the Relevant Plasma-Facing Materials*

	Material	Operation Limits ITER-Like Wall ^a Not Actively Cooled	Operation Limits ITER ^a Actively Water Cooled
First wall	Beryllium	Surface temperature <900°C (due to the beryllium melting temperature) HFF ^b <22 MW m ⁻² s ^{1/2}	Power density 1–5 MW/m ² (steady state)
Divertor	Tungsten	Surface temperature limit <1200–2200°C HFF ^b 20–35 MW m ⁻² s ^{1/2} Transients (ELMs) ^c ~0.1–0.5 MJ/m ² (ms range)	Surface temperature limit ~1500°C (depending on design and tungsten armor thickness) Power density ~5–20 MW/m ² (steady state) Transients (ELMs) ^c ~0.5–1 MJ/m ² (submillisecond range)
	Tungsten coatings on CFC	Surface temperature <1200°C (due to carbidization) HFF ^b <5 MW m ⁻² s ^{1/2} (transients, for 10 ² ELMs)	Not applicable

*References 34 through 39.

^aWithout off-normal events^bHFF = Heat flux factor^cNo material parameters, for the material performance of tungsten under transient heat loads see Refs. 18 and 19.

1. Recovery wall conditioning
 - Initial first wall Be erosion, Be and W material mixing and fuel retention
 - C and Be migration in all scenarios
 - H-modes prior to long term sample retrieval with tracer injection
 - Long term samples analysis
2. Fuel retention
 - Evaluation of fuel retention in all scenarios
 - Gas balance analysis with impurity seeding
3. Tungsten erosion
 - Divertor W erosion and ELM induced sputtering
 - Long term evolution of W erosion and migration
4. Beryllium power handling
 - Beryllium tile power handling
5. Divertor power handling
 - Bulk tungsten tile power handling
6. Monitoring pulses
 - Beryllium migration monitoring
 - ITER-like Wall status monitoring
 - Recovery wall conditioning

One especially interesting material experiment focuses on the behavior of already recrystallised tungsten lamellas in comparison to non-recrystallised tungsten lamellas under steady state and transient heat loads in the divertor. In a later stage the impact of tungsten melting on the plasma operation will be investigated. The exploration of ITER operating scenarios with the ITER-like Wall and physical topics essential to the efficient exploitation of the ITER-like Wall and ITER will be another focus of the research program.⁵

ACKNOWLEDGMENTS

This work was supported by EURATOM and carried out within the framework of the European Fusion Development Agreement. The views and opinions expressed herein do not necessarily reflect those of the European Commission.

REFERENCES

1. T. HIRAI et al., "R&D on Full Tungsten Divertor and Beryllium Wall for JET ITER-Like Wall Project," *Fusion Eng. Des.*, **82**, 1839 (2007).

2. R. NEU et al., "Investigation of Tungsten Coatings on Graphite and CFC," *Phys. Scr. T.*, **128**, 150 (2007).
3. G. F. MATTHEWS et al., "Current Status of the JET ITER-Like Wall Project," *Phys. Scr. T.*, **138**, 014030 (2009).
4. G. F. MATTHEWS et al., "Overview of the ITER-Like Wall Project," *Phys. Scr. T.*, **128**, 137 (2007).
5. S. BREZINSEK et al., "Overview of Experimental Preparation for the ITER-Like Wall at JET," *J. Nucl. Mater.*, **415**, 1, Suppl., S936 (2011).
6. D. GELLES et al., "Radiation Effects in Beryllium Used for Plasma Protection," *J. Nucl. Mater.*, **212–215**, 29 (1994).
7. V. RICCARDO et al., "Operational Limits for the ITER-Like Wall in JET," *Phys. Scr. T.*, **138**, 014033 (2009).
8. V. THOMPSON et al., "Analysis and Design of the Beryllium Tiles for the JET ITER-Like Wall Project," *Fusion Eng. Des.*, **82**, 15–24, 1706 (2007).
9. I. NUNES et al., "Optimization of the JET Beryllium Tile Profile for Power Handling," *Fusion Eng. Des.*, **82**, 15–24, 1846 (2007).
10. V. PHILIPPS et al., "Overview of the JET ITER-Like Wall Project," *Fusion Eng. Des.*, **85**, 1581 (2010).
11. E. B. DEKSNIS et al., "Beryllium Plasma-Facing Components: JET Experience," *Fusion Eng. Des.*, **37**, 4, 515 (1997).
12. M. RUBEL et al., "Beryllium Plasma-Facing Components for the ITER-Like Wall Project at JET," *J. Phys. Conf. Ser.*, **100**, 062028 (2008).
13. T. HIRAI et al., "Thermal Load Testing of Erosion-Monitoring Beryllium Marker Tile for the ITER-Like Wall Project at JET," *Fusion Eng. Des.*, **83**, 1072 (2008).
14. A. WIDDOWSON et al., "Testing of Beryllium Marker Coatings in PISCES-B for the JET ITER-Like Wall," *J. Nucl. Mater.*, **390–391**, 988 (2009).
15. C. P. LUNGU et al., "Beryllium Coatings on Metals for Marker Tiles at JET: Development of Process and Characterization of Layers," *Phys. Scr. T.*, **128**, 157 (2007).
16. T. HIRAI et al., "Characterization and Heat Flux Testing of Beryllium Coatings on Inconel for JET ITER-Like Wall Project," *Phys. Scr. T.*, **128**, 166 (2007).
17. J. LINKE et al., "Performance of Different Tungsten Grades under Transient Thermal Loads," *Nucl. Fusion*, **51**, 7, 073017 (2011).
18. TH. LOEWENHOFF et al., "Evolution of Tungsten Degradation Under Combined High Cycle Edge-Localized Mode and Steady-State Heat Loads," *Phys. Scr. T.*, **145**, 014057 (2011).
19. M. WIRTZ et al., "Comparison of the Thermal Shock Performance of Different Tungsten Grades and the Influence of Microstructure on the Damage Behavior," *Phys. Scr. T.*, **145**, 014058 (2011).
20. M. RIETH et al., "Review on the EFDA Programme on Tungsten Materials Technology and Science," *J. Nucl. Mater.*, **417**, 1–3, 463 (2011).
21. J. W. COENEN et al., "Analysis of Structural Changes and High-Heat-Flux Tests on Pre-Damaged Tungsten from Tokamak Melt Experiments," *Phys. Scr. T.*, **145**, 014066 (2011).
22. PH. MERTENS et al., "A Bulk Tungsten Divertor Row for the Outer Strike Point in JET," *Fusion Eng. Des.*, **84**, 1289 (2009).
23. PH. MERTENS, "Detailed Design of a Solid Tungsten Divertor Row for JET in Relation to the Physics Goals," *Phys. Scr. T.*, **145**, 014002 (2011).
24. H. MAIER et al., "Tungsten Coatings for the JET ITER-Like Wall Project," *J. Nucl. Mater.*, **363–365**, 1–3, 1246 (2007).
25. H. GREUNER et al., "Design, Performance and Construction of a 2 MW Ion Beam Test Facility for Plasma Facing Components," *Fusion Eng. Des.*, **75–79**, 345 (2005).
26. H. GREUNER et al., "High Heat Flux Facility GLADIS: Operational Characteristics and Results of W7-X Pre-Series Target Tests," *J. Nucl. Mater.*, **367–370**, part B, 1444 (2007).
27. H. MAIER et al., "Qualification of Tungsten Coatings on Plasma-Facing Components for JET," *Phys. Scr. T.*, **138**, 014031 (2009).
28. C. RUSET et al., "Tungsten Coatings Deposited on CFC Tiles by the Combined Magnetron Sputtering and Ion Implantation Technique," *Phys. Scr. T.*, **128**, 171 (2007).
29. C. RUSET et al., "Development of W Coatings for Fusion Applications," *Fusion Eng. Des.*, **86**, 1677 (2011).
30. C. THOMSER et al., "Material Performance of Tungsten Coatings Under Transient Heat Loads," *Phys. Scr. T.*, **145**, 014059 (2011).
31. A. SCHMIDT et al., "First Demonstration of Non-Destructive Tests on Tungsten-Coated JET Divertor CFC Tiles in the Electron Beam Facility JUDITH-2," *Phys. Scr. T.*, **138**, 14034 (2009).
32. C. THOMSER et al., "Tungsten Coatings Under Fusion Relevant Heat Loads," *Prob. Atom. Sci. Tech.*, **6**, 54 (2010).
33. H. MAIER et al., "Performance of W Coatings on CFC with Respect to Carbide Formation," *J. Nucl. Mater.*, **415**, 1, Suppl., S310 (2011).
34. J. LINKE, "High Heat Flux Performance of Plasma Facing Materials and Components Under Service Conditions in Future Fusion Reactors," *Fusion Sci. Technol.*, **57**, 2T, 293 (2010).
35. G. F. MATTHEWS et al., "JET ITER-Like Wall—Overview and Experimental Programme," *Phys. Scr. T.*, **145**, 014001 (2011).
36. T. EICH et al., "Type-I ELM Power Deposition Profile Width and Temporal Shape in JET," *J. Nucl. Mater.*, **415**, 1, Suppl., S856 (2011).
37. R. A. PITTS et al., "Physics Basis and Design of the ITER Plasma-Facing Components," *J. Nucl. Mater.*, **415**, 1, Suppl., S957 (2011).
38. A. LOARTE et al., "Characteristics of Type I ELM Energy and Particle Losses in Existing Devices and Their Extrapolation to ITER," *Plasma Phys. Control. Fusion*, **45**, 1549 (2003).
39. H. THOMSEN et al., "Power Load Characterization for Type-I ELMY H-Modes in JET," *Nucl. Fusion*, **51**, 123001 (2011).
40. F. ROMANELLI, EFDA (Attachment 2 to Letter Ref: 8019-FR/LDH-L), 2011.