

UKAEA-CCFE-CP(19)22

Vaughan Thompson, Russell Eaton, Rene Raffray,
Konstantin Egorov

Properties of Low Friction Anti-Seize Coatings for Fusion Applications

This document is intended for publication in the open literature. It is made available on the understanding that it may not be further circulated and extracts or references may not be published prior to publication of the original when applicable, or without the consent of the UKAEA Publications Officer, Culham Science Centre, Building K1/0/83, Abingdon, Oxfordshire, OX14 3DB, UK.

Enquiries about copyright and reproduction should in the first instance be addressed to the UKAEA Publications Officer, Culham Science Centre, Building K1/0/83 Abingdon, Oxfordshire, OX14 3DB, UK. The United Kingdom Atomic Energy Authority is the copyright holder.

The contents of this document and all other UKAEA Preprints, Reports and Conference Papers are available to view online free at <https://scientific-publications.ukaea.uk/>

Properties of Low Friction Anti-Seize Coatings for Fusion Applications

Vaughan Thompson, Russell Eaton, Rene Raffray, Konstantin Egorov

UKAEA-CCFE-CP(19)22

Vaughan Thompson, Russell Eaton, Rene Raffray,
Konstantin Egorov

Properties of Low Friction Anti-Seize Coatings for Fusion Applications

This document is intended for publication in the open literature. It is made available on the understanding that it may not be further circulated and extracts or references may not be published prior to publication of the original when applicable, or without the consent of the UKAEA Publications Officer, Culham Science Centre, Building K1/0/83, Abingdon, Oxfordshire, OX14 3DB, UK.

Enquiries about copyright and reproduction should in the first instance be addressed to the UKAEA Publications Officer, Culham Science Centre, Building K1/0/83 Abingdon, Oxfordshire, OX14 3DB, UK. The United Kingdom Atomic Energy Authority is the copyright holder.

The contents of this document and all other UKAEA Preprints, Reports and Conference Papers are available to view online free at <https://scientific-publications.ukaea.uk/>

Properties of Low Friction Anti-Seize Coatings for Fusion Applications

Vaughan Thompson, Russell Eaton, Rene Raffray, Konstantin Egorov

Properties of Low Friction Anti-Seize Coatings for Fusion Applications

Vaughan Thompson¹, Russell Eaton², Rene Raffray², Konstantin Egorov²

¹CCFE, Culham Science Centre, Abingdon, OX14 3DB, UK

²ITER Organization, Route de Vinon-sur-Verdon - CS 90 046 - 13067 St Paul Lez Durance Cedex, France

Remote maintenance in fusion machines such as JET and ITER relies on sliding interfaces such as bolted joints. Experience in JET, where removal torques much higher than installation values with uncoated bolts is commonplace, led to the installation of experimental bolted assemblies in 2015: the first of its kind in JET. These assemblies included some 660B stainless steel ITER Blanket-specific bolts with a solid sputtered coating of MoS₂ as part of an ITER-funded project known as CHEF (Coating and Humidity Experiments on Fasteners).

CHEF also includes two ex-vessel activities. The first is a characterisation of the coating fundamental properties including outgassing, friction, wear and sensitivity to humidity: on flat sample disks. The second is the measurement of the coating performance on bolted assemblies subjected to a sequence of tests: initial tightening cycles, thermal vacuum exposure, environmental exposure (high humidity and high temperature), repeated thermal vacuum exposure, and final tightening cycles. This sequence approximates to a possible operation cycle of ITER bolted joints which receive an accidental humidity exposure during operation.

Keywords: Coating, Outgassing, Low Friction, MoS₂, Bolts

1. Introduction

MoS₂ which is commonly used in paste form as a general fastener lubricant is also available in a thin (~ 2 µm) sputtered coating which is vacuum compatible, [1]. A typical application is for low friction coating of bearings for use in space where the coatings would always be in a dry state. However, sputtered MoS₂ is believed to be moisture-sensitive and could be accidentally exposed to moisture in a tokamak. The CHEF project includes humidity exposure of both disks and bolts.

In addition, MoST -- an MoS₂ variant -- has also been tested. MoST contains titanium which provides moisture resistance, [2], but its vacuum performance is not so well established. The MoST thickness used here is 1.0-1.4 µm and, following recommendation from the coating supplier, is applied on top of a 2-3 µm sputtered under-coat of CrN. The CrN provides a hard skin to protect the relatively weak 660 B substrate from deformation under high surface loads. This arrangement is intended to align the substrate strength (660B yield ~ 700 MPa) with the bearing capacity of the coating (~ > 1500 MPa), and is sometimes known as the “ice on mud” approach.

The sulphur in these coatings makes outgassing measurements essential as its properties (chemical reactivity, high Z (16)) can lead to persistent radiation losses in plasmas. CHEF includes the use of a highly sensitive outgassing facility described in § 3.

2. JET In-Vessel Tests

There were 36 experimental bolted assemblies exposed inside JET during 2015-16. They were self-contained with spacers and nuts allowing controlled ex-vessel assembly and dis-assembly, Fig.1. Eight

assemblies were part of CHEF using MoS₂ coated 660B bolts and uncoated 660B nuts. The remaining assemblies had a range of JET-relevant features including spirallock® thread form, and uncoated Nimonic and Inconel bolts. The CHEF assemblies performed well after exposure with their high pre-loads maintained and undoing torques similar to their high installation values. Detail examination of these assemblies and the testing of the JET ones are ongoing and will be the subject of a further publication



Fig. 1. JET In-Vessel Bolted Assembly

3. CHEF Vacuum Facility

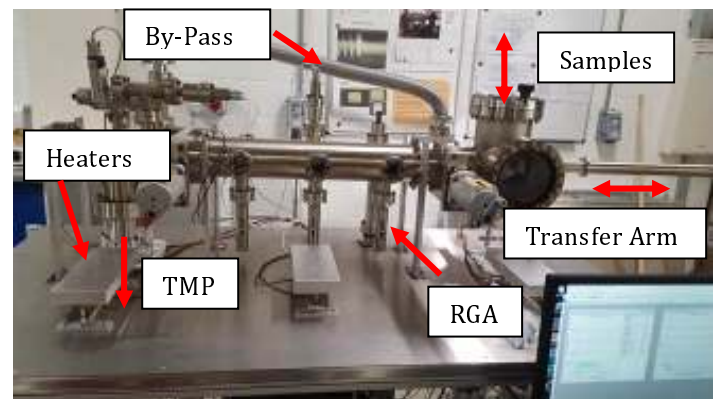


Fig. 2. CHEF Vacuum Facility

Fig 2 shows the high sensitivity outgassing vacuum facility which was engineered in the MRF (Materials Research Facility) at UKAEA Culham for the CHEF project.

Sample transfer is via an Ar-purged vacuum load lock chamber and magnetically coupled transfer arm allowing the main sample chamber (100 mm diameter x 600 mm long) to be permanently under vacuum ($< 10^{-2}$ mBar during transfer (mostly Ar) and $< 3 \times 10^{-10}$ mBar during operation). The chambers and closely coupled equipment can be baked to 200°C by enclosing the whole facility with insulated panels and using 3 x 1 kW heaters mounted on the bench. There is an RGA (Residual Gas Analyser) with remote electronics and a bakable sensor inside the thermal enclosure. A dedicated PC monitors the RGA, four vacuum gauges (two cold cathode and two convection Pirani), seven thermocouples, and has an encrypted network connection so that key operations (e.g. temperature checking and RGA switching) can be done remotely.

A 40 kVA UPS supplies all the electrical equipment – except for the heaters – giving high reliability continuous operation. The tests last typically 4 days (coated disks) or 28 days (bolted assemblies) and the facility has been continuously operating for over 12 months.

4. Friction Disk Tests

To simplify the humidity exposure for the disk tests, two extreme conditions were used. In the first “dry” condition, the samples were stored dry and when exposed, the RH was monitored to ensure that it never exceeded 65%. In the second “wet” condition, the disks were soaked in distilled water for 1 hour before drying naturally for 24 hours. The resulting four test types are designated MoSTD, MoSTW, MoS2D, MoS2W where D and W stand for dry and wet respectively. Fig. 3 shows the MoSTW disks at the start of drying – note how the coating repels the water. Both sets of wet samples fully dried in due course without any visible residue.

Each test included a CO (Chamber Only) and ST (Sample Test) phase. The CO phase preceded the ST phase in order to provide the outgassing background. The thermal profiles were approximately 4 hour dwell at 20 °C, 12 hour ramp up to 150 °C, 24 hour dwell at 150 °C and 12 hour ramp back to 20 °C.

The RGA recorded the ion currents for all masses in the range 1-200 amu and was normally operated in “bar chart” mode with one measurement per amu taken every 10 seconds to monitor trends. At key points, including the start and end of the 150 °C dwell, the RGA was switched to “analogue” mode with 32 samples per amu taken to provide more detail. Fig.4 shows a typical result (MoS2W end of 150 °C dwell) where the CO (blue) and ST (red) phases are overlaid so that the effect of the samples can be highlighted.

The expected presence of H₂, H₂O and CO₂ in similar quantities in both phases is evident by the ion current peaks at 2, 17-18, and 44 respectively. There is also the commonly observed peak at mass 28 which could be due to N₂, CO or other gases as discussed later. The difference due to the presence of the samples is clear evidence of sulphur gases coming from the coatings with peaks at 32-34 (H₂S), 64 and 48 (SO₂) and 76 (CS₂).



Fig. 3. CHEF Friction Disks During Soak Test (MoST)

There are also other peaks in the spectra which are less easy to quantify and so a procedure has been written to de-convolve the mass spectra into parent molecule ions. The procedure takes a library of 26 candidate molecule cracking patterns and performs a least-squares fit with the measured spectra. The result is a predicted molecular ion current for each of the candidates and Fig.5 illustrates the results for the case above (ST phase). The fit uses all the masses from 1-100 (results above 100 were insignificant) and the figure illustrates the 25 most significant along with the 12 most significant molecules. The ratio of RMS error (measured – fit) to the RMS measured value over all masses was generally $< 5\%$ showing a good quality fit.

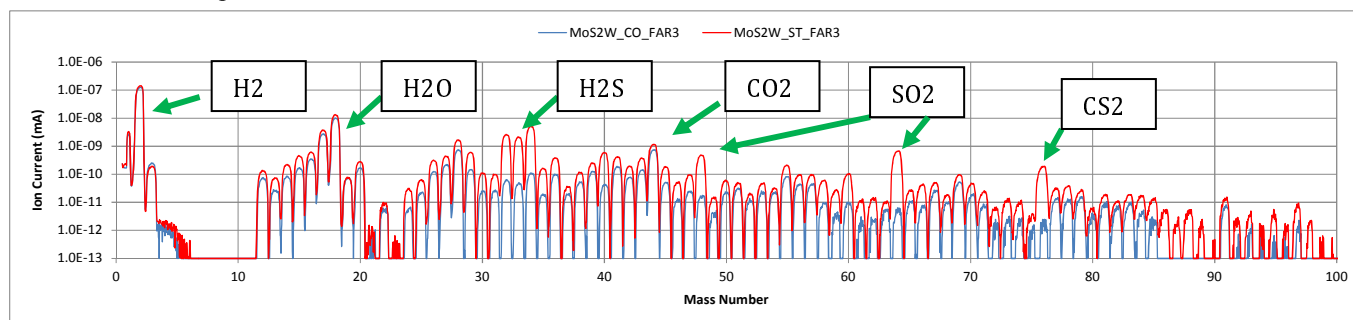


Fig. 4. Analogue Scans (End of 150 °C Dwell). MoS2W

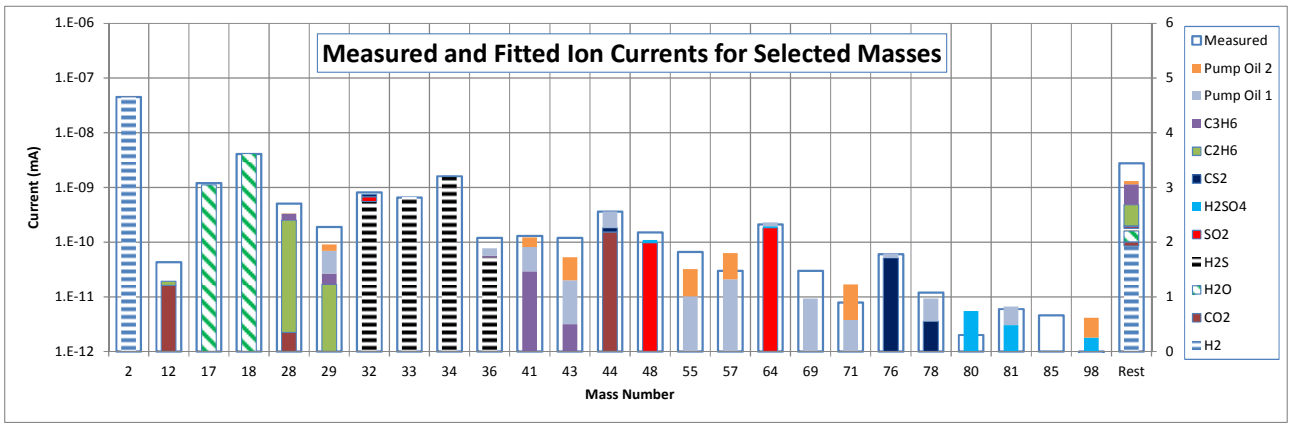


Fig.5. Measured and Fitted Ion Currents. (MoS2W ST Phase End of 150 °C Dwell).

The open columns represent the measured results and the coloured ones the fitted values. Where more than one parent molecule contributes to a single mass e.g. 28, the total coloured column is to the same logarithmic scale as the measured values, but the division within the column is linear to represent the true proportions of separate contributions. As H₂ has a single dominant peak at mass 2, a good fit is guaranteed. But there are also good fits for H₂O, H₂S and SO₂ where multiple cracking fragments are present. The results also indicate traces of C₂H₆ (ethane), C₃H₆ (propylene) and vacuum pumping oils. As both the turbo and scroll pumps are oil-free, the likely source of these vapours is residual contamination from the un-baked bypass system used during the sample transfer. They are present in both phases and so are unlikely to be from the samples. The bulk of the measured ion current at mass 28 is accounted for by C₂H₆ and CO₂ rather than N₂ and CO which, along with O₂, have very low fitted values.

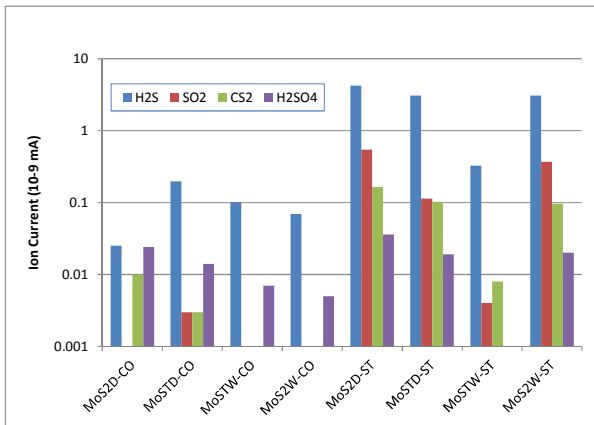


Fig.6. Sulphur Gas Ion Current Comparison.

Fig.6 shows the sulphur gas ion currents at the end of the 150 °C dwell for the four CO tests (LHS) and four ST tests (RHS). H₂S dominates the coating outgassing with little differences between coatings and pre-conditioning (wet versus dry). There are also clear indications of SO₂ and CS₂ from all but the dry MoST case. H₂SO₄ was expected for the MoS₂ cases: but the levels were low and not significant.

After vacuum testing, the coating friction coefficients, μ , were measured using a PoD (Pin on

Disk) tester with the disks rotated beneath uncoated pins at a contact pressure selected to be representative of highly loaded bolts (1500 MPa). There were 12 tests to cover the four disk types with three test conditions each: air at 22 °C, vacuum at 22 °C and 150 °C. The rig monitored μ continuously up to 5000 revolution or a value $\mu > 0.3$ (indicative of complete coating wear-through): whichever occurred first. The material combinations and surface finishes (Ra) replicated those in the bolted assemblies: 660B, ~ 0.1 μm , coated (disks and bolts) and 660B, ~ 0.5 μm , uncoated (pins and nuts).

Table 1. PoD Results.

Env.	Coat	Exp.	Temp. °C	$\mu(\text{init.})$	Revs to μ	
					> 0.1	> 0.3
Vac.	MoST	Dry	22	0.033	41	329
Vac.	MoST	Dry	150	0.061	54	395
Air	MoST	Dry	22	0.081	5000	5000
Vac.	MoST	Wet	22	0.091	78	139
Vac.	MoST	Wet	150	0.046	179	355
Air	MoST	Wet	22	0.051	5000	5000
Vac.	MoS2	Dry	22	0.060	48	94
Vac.	MoS2	Dry	150	0.051	82	194
Air	MoS2	Dry	22	0.082	27	97
Vac.	MoS2	Wet	22	0.052	31	83
Vac.	MoS2	Wet	150	0.072	30	60
Air	MoS2	Wet	22	0.051	46	111

Table 1 includes the number of revolutions to reach $\mu = 0.1$ which is the desired limiting value for the ITER bolt coating. The results show initial $\mu \sim 0.06$ as expected. The lifetimes vary enormously with MoST giving the longest particularly when tested in air: but even the shortest lifetime of 27 revolutions is more than sufficient for typical bolting applications.

5. Bolted Assembly Tests

The CHEF bolted assembly is similar to the JET in-vessel case and comprises a bolt coated on threads and washer face, plane washer coated on the top face, disk spring washer, spacer and un-coated nut, Fig.7. Standard

M10 threads were used. The bolt ends were faced so that the length could be accurately measured and used to deduce bolt preload due to elastic stretching when combined with the calculated bolt stiffness.

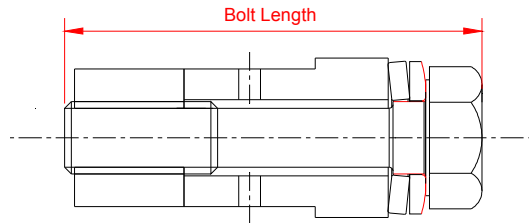


Fig. 7. CHEF Bolted Assembly

The assemblies are currently going through their second thermal vacuum exposure and so results here are for the un-exposed prototypes.

To challenge the coating performance in these early tests, the bolts were tightened to a target pre-load of 80% of tensile yield (and a coating contact pressure ~ 1000 MPa). The pre-load was controlled via bolt length measurements at intermediate stages and the coating μ (average of head and thread) was deduced from torque measurements. Fig.8 shows how the pre-load ratio varies with μ for 6 tightening cycles. Two types of coated washer were tested – domed and plane – and both the MoS₂ cases show excellent performance with μ staying around 0.05-0.07 (similar to the disk PoD value) and pre-loads staying close to the 80%.target.

However the MoST cases reached only about 70% initially, dropping to 40-60% with cycles as μ increased to about 0.25-0.3.

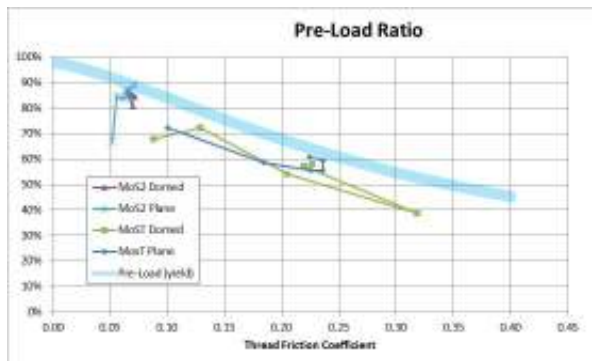


Fig. 8. Ratio of Pre-Load to Yield

This behavior is due to the slightly higher initial friction in the bolt threads causing torsion in the bolt shaft to reduce the available tension. The blue band indicates the theoretical tension yield when combined with torsion and the MoST case travels down this line as the bolt suffers damage due to yielding and coating damage leads to ever higher friction as attempts were made to reach the target pre-load.

Fig.9 shows one of the MoST cases where there is clear damage to the coating. It is likely that the MoS₂ case was close to reaching this runaway situation and so for the subsequent endurance tests, the target pre-load was reset to 65%.



Fig. 9. MoST Coating Damage After 6 Cycles

6. Summary

Experimental bolted assemblies exposed inside JET during 2015-1016 demonstrated the low friction and anti-seize properties of MoS₂ applied as a solid sputtered coating onto 660B bolts representing an application for ITER blanket modules. Ex-vessel disk tests were used to measure the key properties of outgassing, humidity sensitivity and wear rates of this coating along with a titanium containing variant: MoST. Additional ex-vessel tests on bolted assemblies have so far revealed the durability of these coatings to repeated tightening cycles.

Acknowledgments

This work was carried out by the UKAEA and funded by the ITER Organization under contract ITER/CT/16/4300001328. The JET In-Vessel tests were carried out within the framework of the Contract for the Operation of the JET Facilities and received funding from the European Union's Horizon 2020 research and innovation programme. The views and opinions expressed herein do not necessarily reflect those of the European Commission or of the ITER Organization. The authors wish to acknowledge contributions from Chris Smith, Damian Brennan, Nicolas Balshaw, Sol Omolayu, Tom Keenan and Juan Benayas (UKAEA) and Philippe Chappuis (ITER Organization).

References

- [1] E. W. Roberts, The tribology of sputtered MoS₂ films, Proc. I.Mech.E. Vol.1 1987.
- [2] D. G Teer, New solid lubricant coatings, Wear 251 (2001) 1068-1074.