

UKAEA-CCFE-PR(19)19

Mikhail Lavrentiev, N.L. Allan, C. Wragg

# Quantum and Classical Monte Carlo Study of Lithium Oxide

Enquiries about copyright and reproduction should in the first instance be addressed to the  
UKAEA  
Publications Officer, Culham Science Centre, Building K1/0/83 Abingdon, Oxfordshire,  
OX14 3DB, UK. The United Kingdom Atomic Energy Authority is the copyright holder.

# Quantum and Classical Monte Carlo Study of Lithium Oxide

Mikhail Lavrentiev, N.L. Allan, C. Wragg



# Quantum and Classical Monte Carlo Study of Lithium Oxide

M.Yu. Lavrentiev<sup>(1)\*</sup>, N.L. Allan<sup>(2)</sup>, C. Wragg<sup>(2)</sup>

<sup>(1)</sup>*United Kingdom Atomic Energy Authority, Culham Science Centre, Abingdon, Oxon, OX14 3DB, United Kingdom*

<sup>(2)</sup>*School of Chemistry, University of Bristol, Bristol BS8 1TS, United Kingdom*

\* Corresponding Author, E-mail: Mikhail.Lavrentiev@ukaea.uk

## Abstract

Extensive Monte Carlo simulations of lithium oxide,  $\text{Li}_2\text{O}$ , an important material for fusion applications over a wide range of temperatures have been performed. In the low temperature range 1 – 500 K, quantum corrections to the enthalpy and unit cell size were determined. We show that the classical Monte Carlo underestimates both these quantities and the difference between unit cell parameter with and without quantum corrections is large enough that such corrections should be included in any comparison between theory and experiment. Over the range 300 – 1000 K, the formation energy of Schottky and Frenkel defects are calculated, several possible diffusion mechanisms identified, and the migration energy of vacancy-mediated Li diffusion estimated. At temperatures above 1000 K, the superionic phase transition and subsequent melting are simulated.

## 1. Introduction

Lithium oxide,  $\text{Li}_2\text{O}$ , is a prospective material for use in fusion power plants as a blanket breeding material that converts high energy neutrons into heat and breeds tritium for the fusion reaction [1,2].  $\text{Li}_2\text{O}$  has the antifluorite structure (space group  $Fm\bar{3}m$ ), with the conventional cubic unit cell consisting of four O and eight Li atoms (see Figure 1) and a lattice parameter  $a$  which varies between 4.6 and 4.7 Å, depending on temperature. Li atoms form a simple cubic lattice, while O atoms are packed in a face-centred cubic lattice. There have been numerous experimental and theoretical studies of its properties, mostly at high temperatures over 1000 K. These studies have confirmed the existence of a superionic phase transition at a temperature  $T_c$  between 1200 and 1350 K. Oishi *et al.* [3] in a study of lithium self-diffusion found a transition temperature close to 1273 K, while inelastic neutron scattering data by Hull *et al.* [4] suggests  $T_c \approx 1350$  K and neutron diffraction experiments by Farley *et al.* [5] give  $T_c \approx 1200$  K. This transition is related to disordering of the lithium lattice, while the oxygen lattice remains intact up to the melting point  $T_m$  (experimentally 1705 K [6] or 1711 K [7]). However, details of the disorder and of the diffusion mechanism below and above the transition temperature are still a matter of discussion. Experimental activation energies might be affected by e.g. association of migrating ions with charged impurities. Oishi *et al.* [3] estimate the activation energy of self-diffusion in the intrinsic region (above 1000°C) to be 2.52 eV and identify this as the sum of the Li migration energy and the formation energy of a Frenkel defect. In the low-temperature (extrinsic) region they estimate the migration energy of Li diffusion to be 1.01 eV, which is considered far too high by Matsuo *et al.* [8] who believes this value is affected by the presence of divalent impurities such as  $\text{Mg}^{2+}$ ,  $\text{Ca}^{2+}$  *etc.* This suggestion is in agreement with results by Oei and Richtering [9], who reported activation energy of 1.1 eV for  $\text{Li}_2\text{O}$  crystal containing a small amount of MgO. In [8], characteristic (activation) energy of cation diffusion in the extrinsic region is estimated to be between 0.38 and 0.48 eV. The smaller value was obtained for a single crystal, while the higher value was obtained for a wet sintered pellet. Matsuo *et al.* [8] believe that the  $\text{OH}^-$  impurities in the latter sample might associate with Li ions and increase effective energy of diffusion. Computational studies usually investigate  $\text{Li}_2\text{O}$  without impurities, and a molecular dynamics study by Mulliner *et al.* [10] found cation hopping along (100) direction with an activation energy of 0.28 eV as the main mechanism of diffusion at temperatures below 1200 K.

The temperatures at which a lithium oxide breeding blanket is intended to work are between 680 and 1100 K [11], a temperature range which has attracted less simulation-related research. In this

work, we concentrate on low ( $< 300$  K) and intermediate temperature regions (300 – 1000 K). The former region presents an interesting opportunity for studying quantum effects due to the low mass of Li. Our aim here is to calculate quantum corrections to the Monte Carlo simulations of enthalpy, the unit cell size and volume, and compare with results of direct free energy minimization at the same temperatures using quasiharmonic lattice dynamics [12-16]. At intermediate temperatures, we investigate diffusion in the lithium subsystem below the superionic transition temperature. We also calculate the formation enthalpies of the most abundant defects: Schottky (Li and O vacancies) and Frenkel (Li vacancy and interstitial) and compare our results with experimental data and previous theoretical results. Finally, we briefly turn our attention to temperatures above 1000 K and compare our Monte Carlo results for the transition temperatures  $T_c$  and  $T_m$  with experiment and previous molecular dynamics studies.

## 2. Methods

Classical Monte Carlo simulations were performed on a system of 64 ( $4 \times 4 \times 4$ ) unit cells with 768 atoms. Each simulation consisted of equilibration and accumulation stages; equilibration included  $5 \times 10^7$  steps; in the accumulation stage,  $10^8$  steps were performed. During one step of the Monte Carlo simulation a random decision is made to alter one of the variables of the calculation, which may either be an atomic position or one of the cell dimensions, i.e. all simulations are carried out within the NPT ensemble under ambient pressure and lattice vibrations are automatically included [17]. The magnitude of the change is also chosen at random, but within a specified amount and governed by the variables  $r_{\max}$  and  $v_{\max}$  respectively. The magnitude of these variables is adjusted automatically so that the acceptance/rejection ratio is 0.3. After each move/volume alteration the change in energy is calculated and a decision whether to accept or reject this is made according to the standard Metropolis scheme [18].

A method that takes into account quantum corrections in Monte Carlo simulations is based on a discretization of the density matrix [19] and is described in detail in [20]. It can be visualized as replacement of each of the  $N$  atoms in a system by a “molecule” consisting of  $l$  atoms of the same species [21]. These atoms are joined together into a ring or polymer so that each of them interacts only with its two neighbours. This interaction is represented by a spring with coefficient

$$k = \frac{lmk_B^2 T^2}{\hbar^2}, \quad (1)$$

where  $m$  is the mass of the atom,  $k_B$  the Boltzmann constant,  $T$  the temperature and  $\hbar$  the Planck

constant. The equilibrium distance of the spring is zero, so that the lowest energy configuration of the molecule corresponds to all atoms being in one point. The classical interaction between the atoms belonging to different molecules is nonzero only between correspondingly numbered atoms, so that atom 1 of molecule 1 does not interact with atom 2 of molecule 2, etc. This interaction is scaled in accordance with the number of atoms in each “molecule”:

$$V_{cl} = \frac{1}{l} \sum_{a=1}^l \sum_{i < j}^N v_{cl}(\mathbf{r}_{ia} - \mathbf{r}_{ja}), \quad (2)$$

with indices  $i, j$  numbering atoms in the system and index  $a$  numbering atoms within a “molecule”. This model can be relatively easily implemented in classical Monte Carlo programs and the main computational restriction that arises is related to the increase of overall number of atoms in simulation box from  $N$  to  $Nl$ . For quantum Monte Carlo simulations performed in this study, each atom was replaced by a ring that could include  $l = 2, 4, \text{ or } 8$  atoms, so that the largest system studied included 6144 atoms. Larger systems need longer simulations in order to reach equilibrium, so for the cases of 4 and 8 atoms in a “molecule”, the equilibration stage was extended to  $10^8$  steps.

Several interatomic interaction potentials have been developed for lithium oxide (see, e.g., [22-24]). In the present study we used the potential developed by Fracchia *et al.* [25] from *ab initio* calculations and successfully applied to the study of the superionic transition [25], as well as in a recent non-equilibrium molecular dynamics study of diffusion in  $\text{Li}_2\text{O}$  above 873 K [10]. Each short-range interaction is described by a Buckingham potential of the form

$$V(r) = A \exp\left(-\frac{r}{\rho}\right) - C/r^6, \quad (3)$$

with parameters  $A, \rho,$  and  $C$  given in Table 1. Effective charges are +0.944 for Li and -1.888 for O (in units of  $|q_e|$ ).

### 3. Low temperature properties and quantum effects

Over the temperature range 1 to 300 K, simulations were performed for  $l$  values of 1, 2, 4, and 8; for higher temperatures, only values of  $l = 1, 2,$  and 4 were used. The temperature dependence of the enthalpy and of the unit cell size for these values of  $l$  is shown in Figure 2. Similar behaviour is observed with increasing the size of “molecules”; the magnitude of the enthalpy and unit cell parameter increase because of the effect of vibrations taken into account in Monte Carlo with quantum corrections. This behaviour was found previously in studies of the free energy of a



harmonic oscillator where exact solutions are available [20,26]. At lower temperatures, the parameter  $l$  must be large in order to reach convergence in the quantum-mechanical limit, as can be seen in Figure 2 for the results at 1 K.

In order to find the limit of enthalpy at large values of  $l$ , we approximated the enthalpy at each temperature between 100 K and 500 K as a function of  $l$ :

$$H(T, l) = H_\infty(T) + A(T)/l + B(T)/l^2, \quad (4)$$

setting  $B(T) = 0$  for 400 K and 500 K, since only three values of  $l$  were used at these temperatures. Next, values of the enthalpy in the limit of infinite  $l$ ,  $H_\infty(T)$  were fitted using the polynomial approximation (following [27,28]):

$$H_\infty(T) = H_0 + c_1T^4 + c_2T^6 + cT^8 \quad (5)$$

The same procedure was performed for the unit cell parameter  $a$ , resulting in:

$$a_\infty(T) = a_0 + d_1T^4 + d_2T^6 + d_3T^8 \quad (6)$$

In Figure 3, we show the enthalpy and the unit cell parameter calculated using classical ( $l = 1$ ) Monte Carlo and in the quantum limit, together with the respective polynomial fits. For comparison we have also calculated the unit cell size by direct free energy minimization in the quasiharmonic approximation [12-14] using the program GULP [15,16]. The convergence with the size of the Monkhorst-Pack grid [29] used to sum over phonon wave-vectors  $\mathbf{k}$  in the Brillouin zone was checked. A  $20 \times 20 \times 20$  grid was found to provide sufficient accuracy – at temperatures 100 K, 500 K, and 1000 K increasing the grid to  $32 \times 32 \times 32$   $\mathbf{k}$ -points resulted in change of the enthalpy by less than 0.01 kJ/mol and the lattice parameter by less than 0.0003 Å. The agreement between quantum Monte Carlo and GULP results is excellent, and at low temperatures both results substantially deviate from the classical Monte Carlo simulations. It is instructive here to compare our results with experiment and several other computational studies. While we are not aware of any experimental determination of the lattice parameter below 300 K, room temperature measurements are in the range 4.60 to 4.62 Å [4,5,30]. Hull *et al.* [4] have presented a fit of the lattice parameter based on measurements in the temperature range 293-1603 K to terms in  $T$  and  $T^3$ . While this fit describes experimental data at and above 293 K very well, a straightforward extrapolation to lower temperatures [31-33] seems questionable because of the different form of the polynomial expansion valid at low temperatures (6). As Figure 3(b) shows, the difference between the unit cell parameter calculated using quantum and classical methods can be as high as 0.03 Å close to 0 K, i.e. a rather substantial quantity which must be allowed for when comparing theory and experiment.

#### 4. Defects and diffusion in solid state

Two most important types possible of defects in  $\text{Li}_2\text{O}$  are Frenkel and Schottky defects. The cation Frenkel defect is an interstitial  $\text{Li}^+$  ion that has left a vacancy in the Li sublattice. The Schottky defect is the neutral combination of O and two Li vacancies.

In order to model a Frenkel defect, a single Li ion was removed from its position in the unit cell and placed in an interstitial position in O sublattice, where it is surrounded by eight Li ions. The distance between the Li ion and the Li vacancy created by its removal was made as large as possible in order to minimize the Coulomb interaction between them. Classical Monte Carlo simulations were then performed at several temperatures between 1 and 300 K with a  $4 \times 4 \times 4$  simulation box containing 768 atoms. To check the importance of quantum effects, quantum simulations with values of the parameter  $l = 2$  and  $l = 4$  were also performed at 300 K. Similarly, the Schottky defect was modelled with two Li and one O vacancies situated as far away from each other as possible. For Frenkel defect, annihilation of vacancy and interstitial was observed during the simulation at temperatures above  $T = 300$  K for  $l = 1$  and  $l = 2$ , so simulations were performed for  $l = 4$ , where both vacancy and interstitial remained in their positions during the whole run. Similarly, for Schottky defects, clustering of the vacancies was observed at temperatures above 300 K for  $l = 1$  and  $l = 2$ , in that the three vacancies migrated into nearest neighbour positions to each other. To avoid clustering, simulations at  $T = 500$  K and  $T = 1000$  K were also performed for the value  $l = 4$ .

Our results for defect formation enthalpies are compared with available experimental and theoretical data in Table 2. At the lowest temperature 1 K, our calculated Frenkel and Schottky defect formation enthalpies are 2.28 eV and 4.77 eV, respectively. These values remain almost unchanged until 300 K. Increasing the parameter  $l$  at 300 K does not result in any substantial variation of the formation enthalpies: the Frenkel defect enthalpy decreases slightly to 2.19 eV, while the Schottky defect enthalpy remains unchanged. At 500 K, the formation enthalpies of both defects decreased slightly to 2.18 eV and 4.69 eV, respectively, with further decrease to 2.08 eV and 4.65 eV, respectively, at  $T = 1000$  K. Comparison with available experimental data shows that our results for high temperature formation enthalpy of Frenkel defect are in very good agreement with those obtained from the electric conductivity measurements of Chadwick *et al.* performed at temperatures up to 1300 K [34] and up to 1500 K [35]. Farley *et al.* [5] attempted to

estimate the fraction of Li ions that leave their regular sites to occupy interstitial positions at high temperatures (up to 1603 K) from neutron diffraction data and report a lower formation energy value for the Frenkel pair of ~2.1 eV which almost coincides with our value at  $T = 1000$  K. Note however that the model-dependent estimate of the number of interstitials in [5] assumes the Li ion interstitial position is midway between two regular site cations. Our Monte Carlo simulations show that the interstitial Li ion always lies in the centre of the cube formed by the cations, except when the ion moves from one cube to another. We are not aware of any experimental determination of the formation enthalpy of Schottky defect, but our results agree with previous calculations and confirm Schottky defects are higher in energy than the Frenkel and thus less important in diffusion.

As mentioned above, at elevated temperatures Monte Carlo runs include jumps of Li ions, as well as Li-vacancy recombination. This makes it possible to investigate the nature of Li diffusion in  $\text{Li}_2\text{O}$  and to estimate the Li vacancy migration energy from the simulations. First, we studied the types of movements of Li interstitials in the lattice. Snapshots of 5000 configurations obtained during accumulation stage of Monte Carlo run in large (6144 atoms) simulation boxes with a single Frenkel defect were stored and the positions of the interstitial atom relative to the centre of mass of the simulation box calculated. At temperatures of 500 K and 700 K, the coordinates of this atom change very little and it remains near its initial position for the entire run. For example, the standard deviation of interstitial Li position from that averaged at 700 K is only about 0.07-0.08 of the corresponding nearest neighbour Li-Li distance along each of the crystallographic axes. The calculation at the same temperature for the eight surrounding Li cations shows that they also remain near their crystallographic positions, with a slightly smaller standard deviation of 0.06-0.07 of the nearest neighbour Li-Li distance. At 900 K, a single jump of the interstitial atom into the position of a neighbouring cation was detected in the accumulation stage of the simulation ( $10^8$  steps), with a corresponding jump of the displaced cation into another interstitial position (an interstitialcy mechanism), resulting in overall interstitial displacement by  $\mathbf{r} = (a/2, 0, -a/2)$  away from its initial position. Several such jumps occur at  $T = 1000$  K. Thus, the interstitialcy mechanism of Li diffusion activates around 900 – 1000 K.

The majority of large (of the order of interatomic distance) changes of position of Li atoms were found to be Li-vacancy exchanges. The first such exchange was detected at a temperature as low as 500 K. All such migrations were between a vacancy and one of its six nearest neighbour Li atoms along the (100) direction. A part of the path of the vacancy in simulation box via such

exchanges recorded at 900 K is shown in Figure 4. Calculations of migration enthalpy usually employ only quasiharmonic lattice dynamics or molecular dynamics methods [36]. Monte Carlo simulations have been rarely used (e.g., the difference Monte Carlo study of Ar, Ag, and Cu by De Lorenzi *et al.* [37], performed on a small system of 31 atoms in a 32-site simulation box). The current simulations that include Li-vacancy jumps at several temperatures provide an interesting opportunity to estimate the migration energy for vacancy-mediated Li diffusion in a Monte Carlo run. To do this, the logarithm of the number of jumps during the accumulation stage is plotted as a function of inverse temperature between 500 K and 1000 K (Figure 5). The temperature dependence is indeed almost linear and from the gradient the migration energy is  $\sim 0.28$  eV. This value agrees well with the majority of previous theoretical estimates of the vacancy migration energy: 0.21 eV [34], 0.26 eV [38], 0.34 eV [40], 0.28-0.33 eV [42], 0.28 eV [10]. Most of these theoretical calculations lie below the previously reported experimental vacancy migration enthalpies of 0.49 eV [34], 0.5 eV [35] or  $\sim 0.4$  eV [8]. As we mentioned in the Introduction, one possible reason for this discrepancy might be the association of the vacancies, either with O vacancies, or with positively charged impurity ions, such as  $\text{Mg}^{2+}$ . However, the most recent experimental NMR study report a value of 0.31 eV [43], in excellent agreement with calculation.

Large Li ions hops far away from both vacancy and interstitial were observed only at the highest studied temperature, 1000 K. They include hops of a single atom into a neighbouring position along the (100) direction followed by it or the atom displaced by it hopping shortly thereafter to the initial lattice site. Such hops correspond to the emergence of the soft mode, discussed in [25] at the edge of the Brillouin zone in the [100] direction. Softening of this mode as well as of the [110] transverse acoustic mode at the zone boundary was found also in [44]. These modes involve movements of Li atoms only in the [100] direction and indicate the approach of the superionic transition. Also, a single event of a coordinated four Li ion jump in a closed square loop, similar to those found by Mulliner *et al.* [10] at 973 K, was seen. We did not investigate Li diffusion at temperatures above 1000 K, so we were unable to observe defect-free interstitial-related diffusion seen in [10] in the superionic regime. However, we can see now that addition of a Frenkel defect allows rather accurate estimate of the vacancy-mediated migration energy in the temperature range 500 – 1000 K.

## **5. Melting and superionic phase transition**

Changes related to the superionic transition and melting were studied by calculating several properties of  $\text{Li}_2\text{O}$ . We have examined unit cell size and enthalpy as well as the specific heat. Further, structural changes in the lattice were investigated by calculating the radial correlation functions  $g(\text{Li} - \text{Li})$  and  $g(\text{O} - \text{O})$ , calculated from interatomic distances using snapshots of 5000 configurations obtained during the accumulation stage of Monte Carlo run (details of calculation are given in Ch. 6 of [20]). An example of radial correlation functions calculated at 1000 K (below both transitions) is given in Figure 6.

An important point concerning high-temperature Monte Carlo simulations is the choice of initial configuration. If the run begins with the ideal crystal lattice, the absence of interfaces, due to the periodic boundary conditions, can result in overheating phenomena that lead to an overestimation of the melting temperature. Simulations that start with a mixed initial configuration are a more reliable method of finding the melting point. At temperatures above 1000 K we used both approaches. In the first, simulation started from the solid configuration with atoms in their ideal positions. In the second, initially a simulation at very high temperature  $T = 2400$  K was performed that resulted in a final liquid configuration. Half of that configuration was taken, and the simulation box completed with ideal solid configuration, so that the starting configuration was half-solid and half-liquid.

First, we calculated the melting temperature of  $\text{Li}_2\text{O}$ . Until now, two studies with the current potential were performed that gave contradictory results. Fracchia *et al.* [25] estimated the melting point to lie between 1700 K and 1900 K. However, later work with the same potential [22] found a very high melting point of 2250 K, estimated from a sharp rise in the lattice parameter. In both studies, molecular dynamics simulations were performed, making the large disagreement between [25] and [22] even more puzzling. Our results for the unit cell parameter calculated from the two different initial configurations are shown in Figure 7 and they are strikingly different above 1500 K. The simulation with entirely solid initial configuration exhibits a jump of the unit cell parameter between 2100 K and 2200 K, close to the results reported in [22]. For the mixed solid-liquid configuration, the corresponding jump takes place between 1500 K and 1550 K, much closer to the experimental melting point of 1705 K [6] or 1711 K [7], as well as to the results reported in [25]. Thus, an initial mixed configuration results in a more realistic value of the melting temperature, and so we used calculations with mixed configuration throughout the high-temperature simulations. Melting in the region 1500-1550 K from the initial mixed configuration is also confirmed by a jump in the enthalpy (Figure 8) and abrupt fall in the height

of the maximum of the radial distribution functions, i.e. the first peak (Figure 9) both for Li-Li and O-O.

The superionic transition manifests itself in several ways. First, a broad maximum of the specific heat that begins in our simulations at about 1100 K and continues until the melting of the crystal (Figure 10), is observed. All of the available experimental data on specific heat (Tanifuji *et al.* [45], who also includes results from [46-48]) are restricted to temperatures below 1125 K, thus omitting the superionic transition range. The fit by Barin and Knacke [48] that extends up to 1843 K is shown in Figure 10. The molecular dynamics study by Wilson *et al.* [49] found a superionic transition-related peak in the heat capacity at  $\sim 1450$  K with a subsequent decrease well below the melting point. In our simulations, however, the heat capacity rises all the way up to the melting point, where the specific heat abruptly falls by about  $10 \text{ J mol}^{-1} \text{ K}^{-1}$  (Figure 10). Further experimental studies of the heat capacity up to and beyond the melting point are highly desirable. The entropy of the superionic transition in our study is similar to that found in [49]: integrating the excess of the specific heat over the fit shown in Figure 10, we obtained a transition entropy of about  $6.45 \text{ J mol}^{-1} \text{ K}^{-1}$ , or  $0.78R$ , close to  $5.8 \text{ J mol}^{-1} \text{ K}^{-1}$  [49]. Both these estimates are below the experimental values for other superionic conductors that vary between 13 and  $28 \text{ J mol}^{-1} \text{ K}^{-1}$  [50]. A possible explanation of that difference is that in the case of  $\text{Li}_2\text{O}$ , the transition to superionic state may be interrupted by the melting, as for AgBr [51], the superionic material that has the lowest transition entropy ( $13.6 \text{ J mol}^{-1} \text{ K}^{-1}$ ) of those listed in [50]. Another manifestation of the superionic transition is the faster than linear increase of the thermal expansion coefficient starting from about 1200 K (Figure 11). Similar to the case of the specific heat, the rise continues all the way up to the melting point.

## 6. Conclusions

In this work, we had two aims: (i) to investigate the applicability of Quantum Monte Carlo corrections to a real system and to estimate the importance of these corrections and (ii) to investigate whether the interatomic interaction potential developed in [25] can describe all the most important properties of  $\text{Li}_2\text{O}$ , including the low temperature unit cell size and temperature dependence, solid state diffusion, superionic transition and melting. The use of the Quantum Monte Carlo method in which each of the atoms is replaced by a ring-like “molecule” consisting of several atoms of the same species increases the applicability of the simulations down to very

low temperatures where quantum corrections are important. Several runs with the number  $l$  of atoms in a “molecule” increasing from 1 to 8 is sufficient to estimate values of  $H$  and  $a$  in the limit of infinite  $l$ . Values of the unit cell parameter and the enthalpy obtained by this method polynomially (see (5,6) and Figure 3) approach corresponding values at very low temperature, and are in excellent agreement with those obtained using lattice dynamics to calculate the free energy directly in the quasiharmonic approximation. Linear extrapolations of high-temperature behaviour of  $a(T)$  to the low temperatures, as carried out in previous studies, do not give the correct low-temperature limit, which is important when comparing theory and experiment.

In the medium temperature range, we calculated enthalpies of formation of Frenkel and Schottky defects, investigated the nature of Li diffusion and estimated the migration energy of the Li-vacancy jump. All results are in very good agreement with available experimental data. In particular, the migration energy of Li-vacancy jump agrees very well with the most recent NMR study [43]. Above 1000 K, the potential [25] is able to describe the superionic transition in the cation subsystem and the melting of the crystal. Temperatures of both transitions were found in good agreement with experiment. The superionic transition manifests itself in a peak in the specific heat and two interesting questions remain for future experimental studies: (i) whether or not this increase extends up to the melting point, and (ii) how large is the jump of the specific heat during melting? Further possible work important for fusion applications might include potential based Monte Carlo and *ab initio* investigations of the long-standing problem of tritium behaviour in the  $\text{Li}_2\text{O}$  lattice [52-54].

## **Acknowledgements**

This work was funded in part (MYL) by EPSRC grant EP/P012450/1 and the RCUK Energy Programme (Grant Number EP/I501045). To obtain further information on the data and models underlying this paper please contact [PublicationsManager@ukaea.uk](mailto:PublicationsManager@ukaea.uk).

## References

1. J. G. van der Laan *et al.*, *J. Nucl. Mater.* **283–287**, 99 (2000).
2. M. J. Sadowski, *Nukleonika* **60**, 331 (2015).
3. Y. Oishi *et al.*, *J. Nucl. Mater.* **87**, 341 (1979).
4. S. Hull *et al.*, *J. Nucl. Mater.* **160**, 125 (1988).
5. T. W. D. Farley *et al.*, *J. Phys.: Condens. Matter* **3**, 4761 (1991).
6. Y. Y. Liu *et al.*, *Fusion Technol.* **8** (1985) 1970.
7. M. S. Ortman and E. M. Larsen, *J. Am. Ceram. Soc.* **66**, 645 (1983).
8. T. Matsuo *et al.*, *J. Chem. Soc., Faraday Trans. 2* **79**, 1205 (1983).
9. Y. S. Oei and H. Richtering, *Ber. Bunsenges. Phys. Chem.* **80**, 1007 (1976).
10. A. D. Mulliner *et al.*, *Phys. Chem. Chem. Phys.* **17**, 21470 (2015).
11. D. L. Smith *et al.*, *Fusion Technol.* **8**, 10 (1985).
12. M. B. Taylor *et al.*, *Faraday Discuss.* **106**, 377 (1997).
13. M. B. Taylor *et al.*, *Phys. Rev. B* **56**, 14380 (1997).
14. M. B. Taylor *et al.*, *Comp. Phys. Comm.* **109**, 135 (1998).
15. J. D. Gale and A. L. Rohl, *Mol. Simul.*, **29**, 291 (2003).
16. J. D. Gale, *Z. Krist.*, **220**, 552 (2005).
17. D. Frenkel and B. Smit, *Understanding Molecular Simulation*, 2nd ed. Academic Press, San Diego (2002).
18. N. Metropolis *et al.*, *J. Chem. Phys.* **21**, 1087 (1953).
19. R. P. Feynman and A. R. Hibbs, *Quantum mechanics and path integrals*. McGraw-Hill, New York (1965).
20. M. P. Allen and D. J. Tildesley, *Computer simulation of liquids*, 2<sup>nd</sup> edition, Oxford University Press (2017).
21. D. Chandler and P. G. Wolynes, *J. Chem. Phys.* **74**, 4078 (1981).
22. T. Oda *et al.*, *J. Nucl. Mater.* **367-370**, 263 (2007).
23. T. X. T. Sayle, P. E. Ngoepe, and D. C. Sayle, *J. Mater. Chem.* **20**, 10452 (2010).
24. R. Asahi *et al.*, *Modelling Simul. Mater. Sci. Eng.* **22**, 075009 (2014).
25. R. M. Fracchia *et al.*, *J. Phys. Chem. Solids* **59**, 435 (1998).
26. K. S. Schweizer *et al.*, *J. Chem. Phys.* **75**, 1347 (1981).
27. T. H. K. Barron, J. G. Collins, and G. K. White, *Adv. Phys.* **29**, 609 (1980).
28. T. H. K. Barron and G. K. White, *Heat Capacity and Thermal Expansion at Low Temperatures*. Plenum, New York (1999).



29. H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
30. R. Juza, W. Uphoff, and W. Gieren, *Z. anorg. allg. Chem.* **292**, 71 (1957).
31. R. Dovesi *et al.*, *Chem. Phys.* **156**, 11 (1991).
32. J. García Rodeja, M. Meyer, and M. Hayoun, *Model. Simul. Mater. Sci. Eng.* **9**, 81 (2001).
33. X.-F. Li *et al.*, *Solid State Commun.* **139**, 197 (2006).
34. A. V. Chadwick *et al.*, *Solid State Ionics* **28-30**, 185 (1988).
35. A. V. Chadwick, *Phil. Mag. A* **64**, 983 (1991).
36. J. H. Harding, *Rep. Prog. Phys.* **53**, 1403 (1990).
37. G. De Lorenzi, G. Jacucci, and C. P. Flynn, *Phys. Rev. B* **36**, 9461 (1987).
38. P. W. M. Jacobs and M. L. Vernon, *J. Chem. Soc. Faraday Trans.*, **86**, 1233 (1990).
39. J. L. Gavartin *et al.*, *Model. Simul. Mater. Sci. Eng.* **1**, 29 (1992).
40. A. De Vita *et al.*, *Europhys. Lett.*, **19**, 605 (1992).
41. P. Goel, N. Choudhury, and S. L. Chaplot, *J. Phys.: Condens. Matter* **19**, 386239 (2007).
42. M. M. Islam, T. Bredow, and C. Minot, *J. Phys. Chem. B* **110**, 9413 (2006).
43. P. Heitjans and S. J. Indris, *J. Phys.: Condens. Matter* **15**, 1257 (2003).
44. M. K. Gupta *et al.*, *Phys. Rev. B* **85**, 184304 (2012).
45. T. Tanifuji, K. Shiozawa, and S. Nasu, *J. Nucl. Mater.* **78**, 422 (1978).
46. C. H. Shomate and A. J. Cohen, *J. Am. Chem. Soc.* **77**, 285 (1955).
47. E. N. Rodigina and K. Z. Gomelskii, *Russian J. Phys. Chem.* **35**, 898 (1961).
48. I. Barin and O. Knacke, *Thermochemical Properties of Inorganic Substances* (Springer-Verlag, Berlin) 416 (1973).
49. M. Wilson, S. Jahn, and P. A. Madden, *J. Phys.: Condens. Matter* **16**, S2795 (2004).
50. M. O'Keeffe and B. G. Hyde, *Phil. Mag.* **33**, 219 (1976).
51. W. Jost, *Z. phys. Chem.* **21**, 202 (1959).
52. R. Shah, A. De Vita, and M. C. Payne, *J. Phys.: Condens. Matter* **7**, 6981 (1995).
53. R. Shah *et al.*, *Phys. Rev. B* **53**, 8257 (1996).
54. T. Oda and S. Tanaka, *J. Nucl. Mater.* **417**, 743 (2011).

## Tables

Interaction	$A$ (eV)	$\rho$ (Å)	$C$ (eV·Å <sup>6</sup> )
Li-Li	0.0	1.0	0.0
Li-O	653.84	0.285723	0.0
O-O	0.0	1.0	76.651

Table 1. Short-range Buckingham potential parameter set.  $A$ ,  $\rho$  and  $C$  are defined in equation (3).

A cut-off of 8 Å was used.

Type of defect	This work				
	Temperature (K)				
	1	300	500	1000	
Frenkel (experimental)					2.1* [5], 2.53 [34], 2.6 [35]
Frenkel (calculated)	2.28	2.30 ( <i>l</i> = 1) 2.25 ( <i>l</i> = 2) 2.19 ( <i>l</i> = 4)	2.18 ( <i>l</i> = 4)	2.08 ( <i>l</i> = 4)	2.12 [34], 2.37 [35], 2.55* [38], 1.98* [39], 2.2* [40], 1.7*-2.2* ([32], five different potentials), 2.0* [41], 1.93-2.33* ([22], four different potentials)
Schottky (calculated)	4.77	4.74 ( <i>l</i> = 1) 4.68 ( <i>l</i> = 2) 4.74 ( <i>l</i> = 4)	4.69 ( <i>l</i> = 4)	4.65 ( <i>l</i> = 4)	5.15 [34], 5.24 [35], 5.8* [38], 4.73* [39]

Table 2. Comparison of values of Frenkel and Schottky formation enthalpies obtained in this work with available experimental and calculated values for enthalpies or energies (\*) (eV).

## Figures

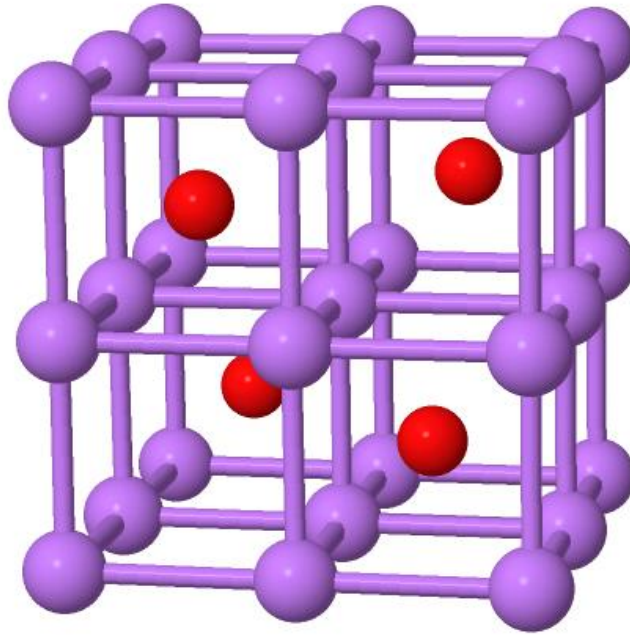


Figure 1. Cubic unit cell of Li<sub>2</sub>O. Red spheres represent oxygen atoms, violet spheres represent lithium atoms.

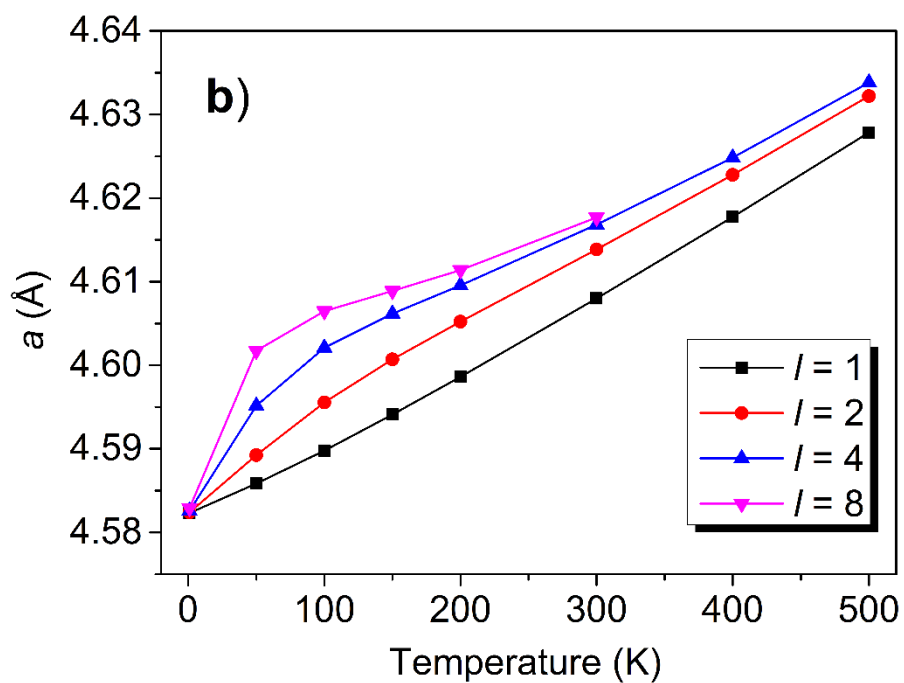
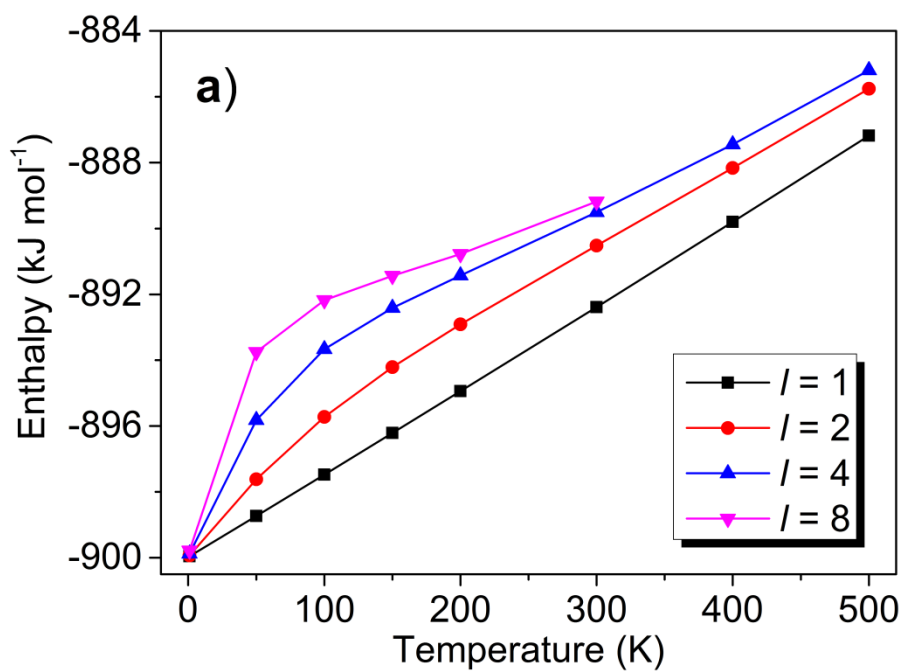


Figure 2. Enthalpy  $H$  (kJ mol<sup>-1</sup>) (a) and lattice parameter  $a$  (Å) (b) of Li<sub>2</sub>O as a function of temperature for values of the quantum Monte Carlo parameter  $l = 1, 2, 4, 8$ .

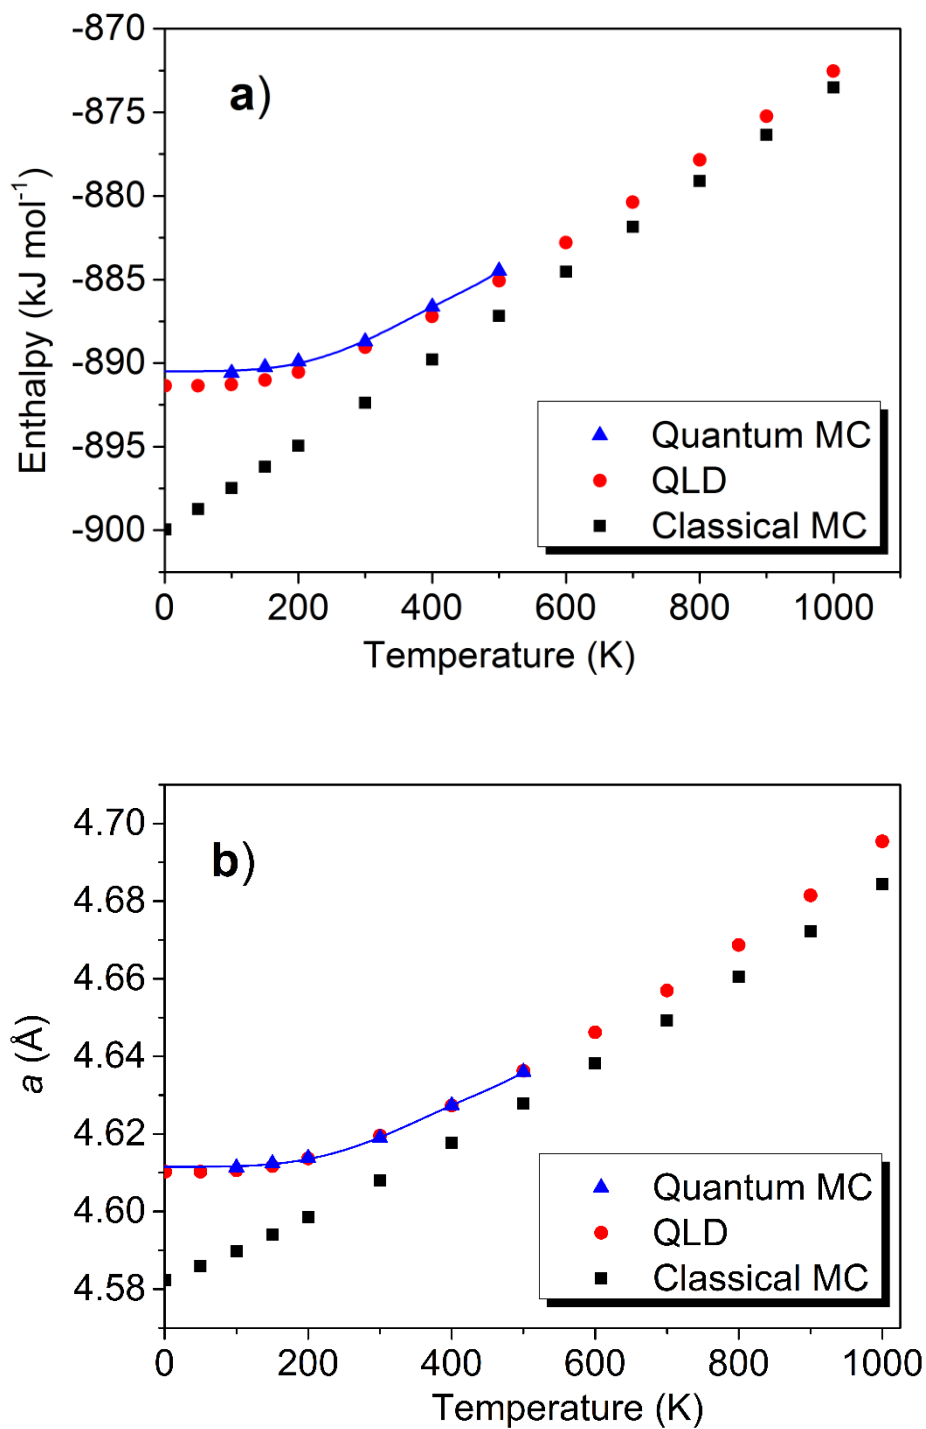


Figure 3. Enthalpy  $H$  ( $\text{kJ mol}^{-1}$ ) (a) and unit cell size  $a$  ( $\text{\AA}$ ) (b) of  $\text{Li}_2\text{O}$  in the limit of large quantum Monte Carlo parameter  $l$  vs temperature. Blue lines are polynomial fits (see formula (5) for  $H(T)$ , (6) for  $a(T)$ ). Free energy minimization results using the quasiharmonic lattice dynamics (QLD) and results obtained from classical Monte Carlo ( $l = 1$ ) simulations are shown for comparison.

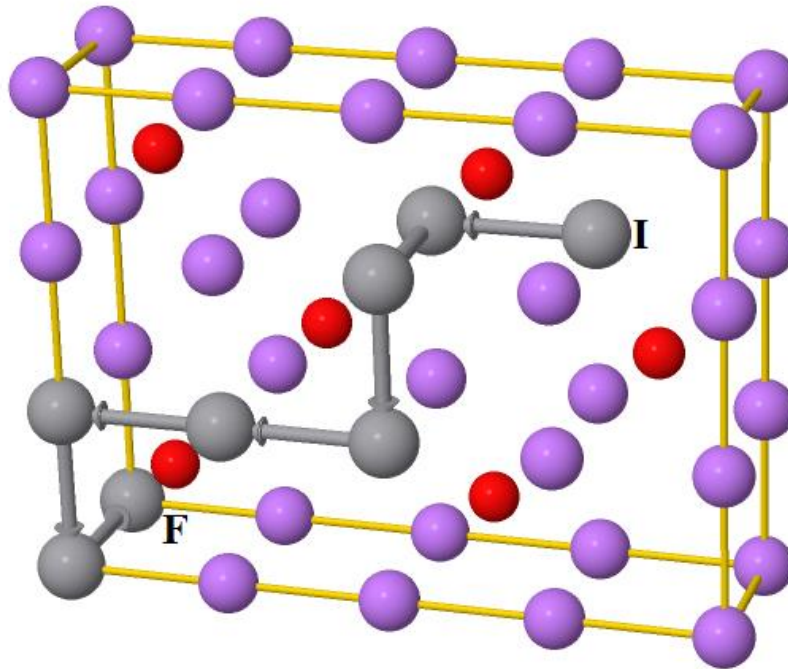


Figure 4. Part of the path of a vacancy generated in a Monte Carlo run at temperature  $T = 900$  K with a single Frenkel defect in the simulation box. Vacancy is represented by grey spheres. Initial and final positions of the vacancy are denoted **I** and **F**, respectively. Each vector shows single vacancy hop, accompanied by reverse hop of the Li atom.

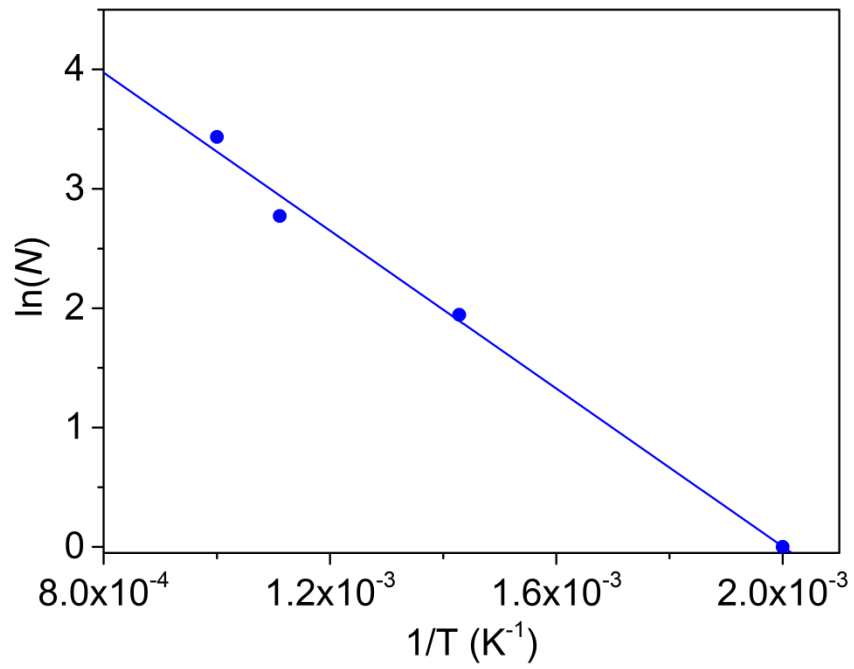


Figure 5. Temperature dependence of the logarithm of the number  $N$  of Li cation jumps during the simulation. The straight line is a linear fit:  $\ln(N) = 6.61968 - 3308.1765/T$ .



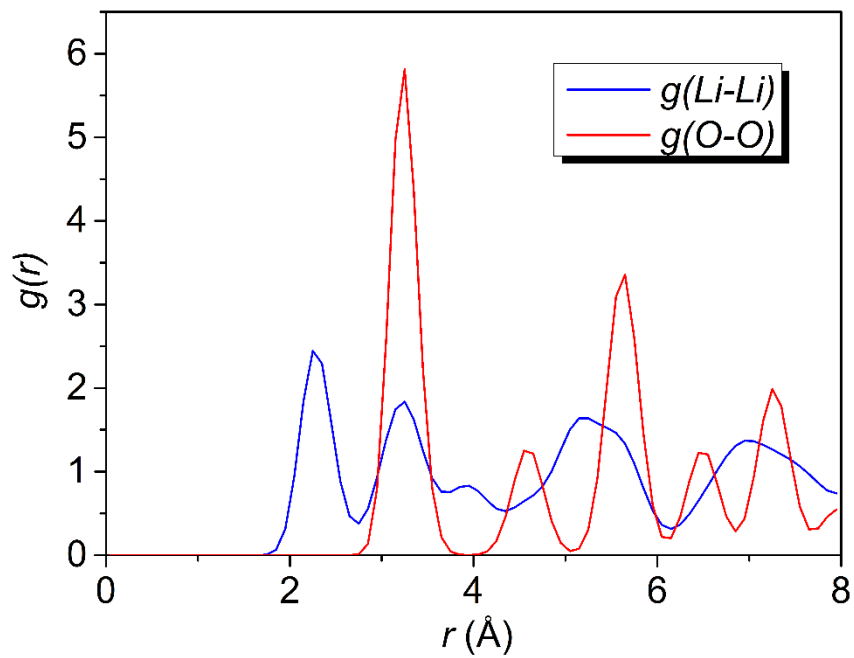


Figure 6. Radial distribution functions  $g(\text{Li} - \text{Li})$  (blue) and  $g(\text{O} - \text{O})$  (red), calculated at  $T = 1000 \text{ K}$ .

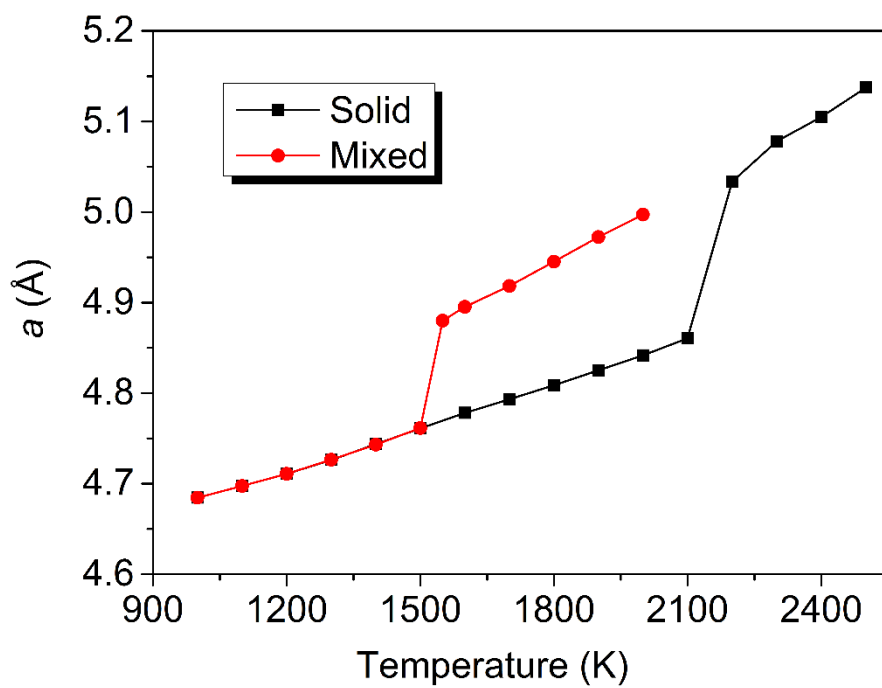


Figure 7. Unit cell size  $a$  (Å) vs temperature for simulations starting from solid (black) and mixed solid-liquid (red) systems.

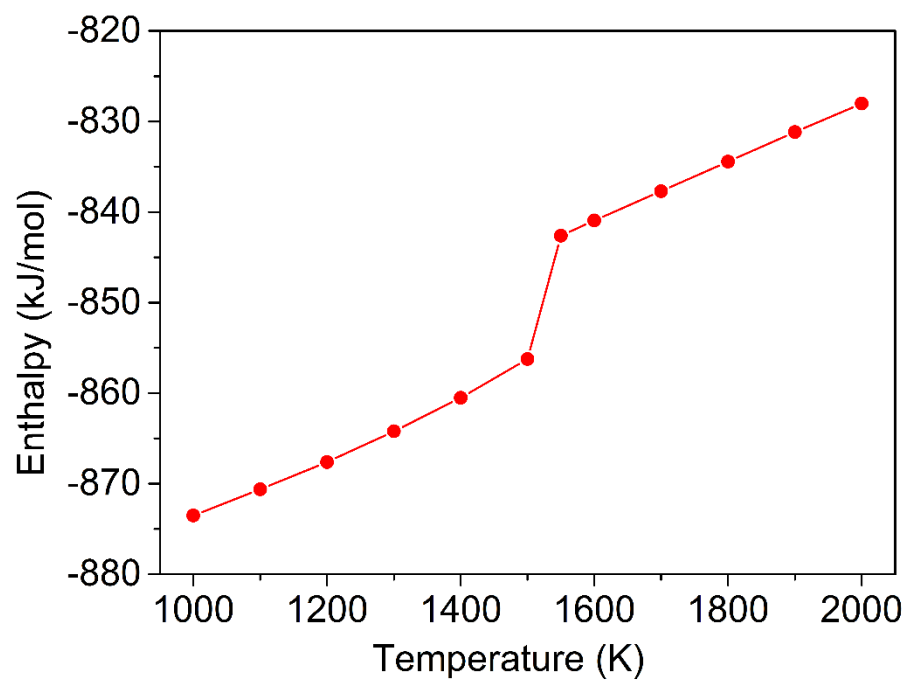


Figure 8. Enthalpy  $H$  (kJ/mol) vs temperature for simulation starting from mixed (half-solid, half-liquid) system.

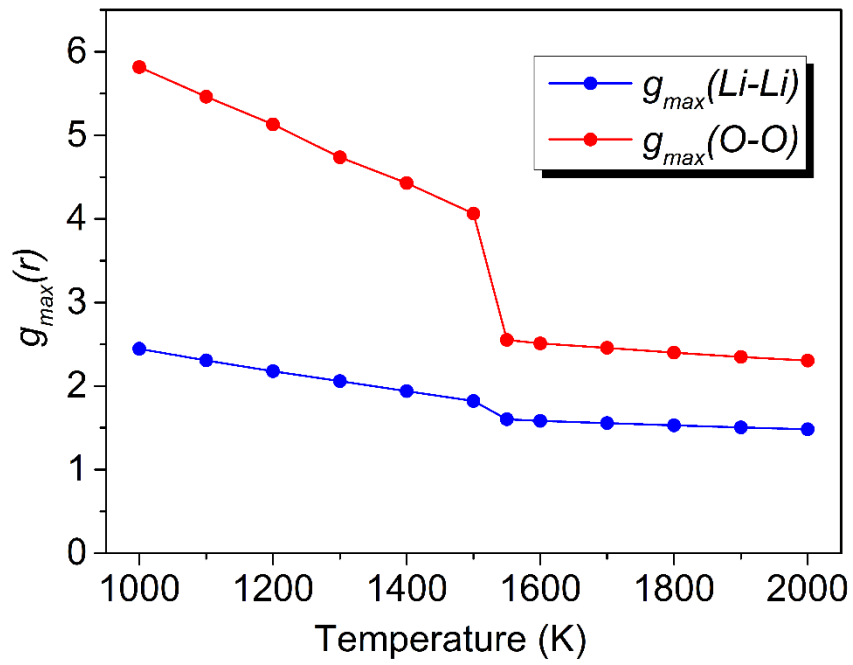


Figure 9. Maximum value of the radial distribution functions  $g(Li - Li)$  and  $g(O - O)$  vs the temperature of the simulation starting from the mixed (half-solid, half-liquid) system as described in the text.

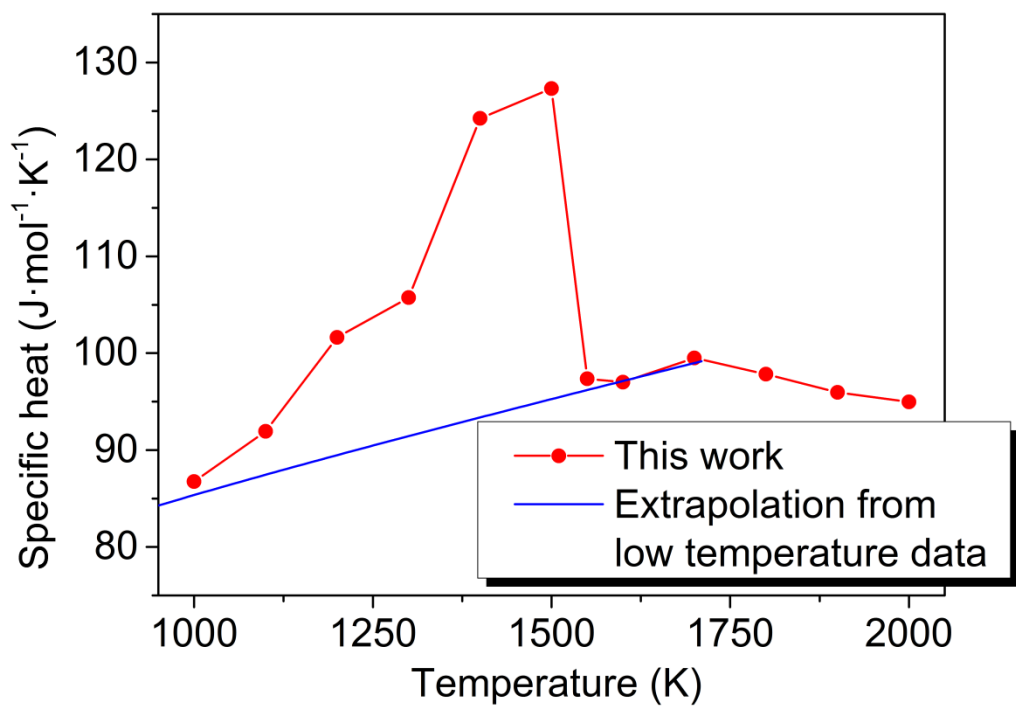


Figure 10. Specific heat of Li<sub>2</sub>O calculated starting from mixed (half-solid, half-liquid) system (red) compared with extrapolation from low temperature data (Barin and Knacke [47], as reported in [44]).

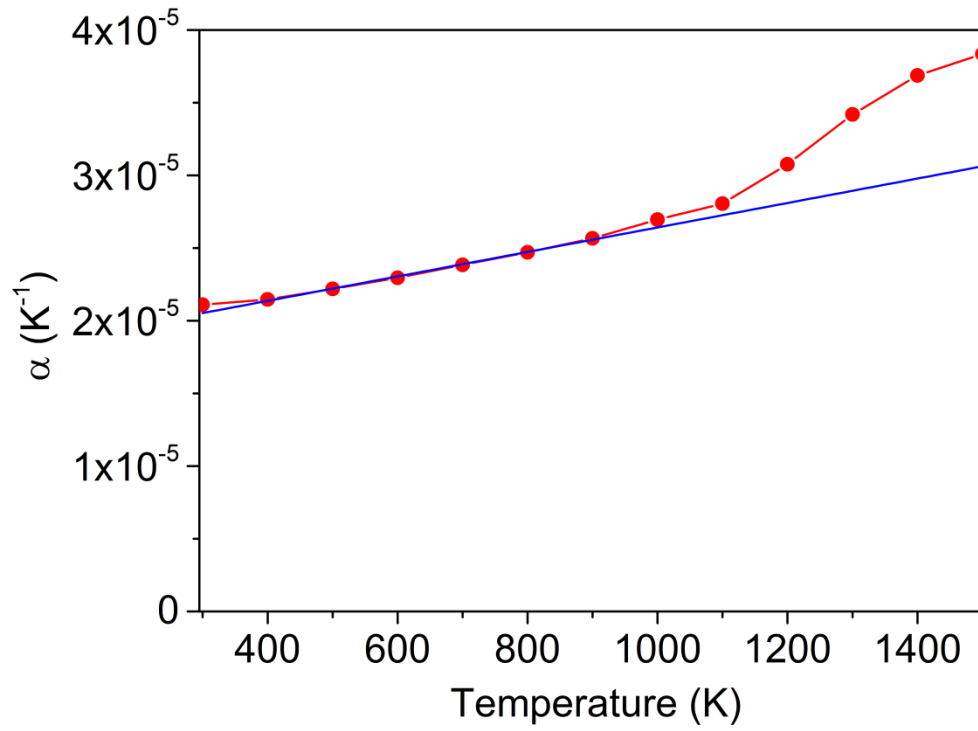


Figure 11. Thermal expansion coefficient of  $\text{Li}_2\text{O}$  (red line and points)  $\alpha = \frac{1}{a} \frac{da}{dT}$  numerically calculated from the Monte Carlo results for the lattice parameter  $a(T)$ . Straight blue line is a linear fit of  $\alpha(T)$  between 400 K and 900 K.

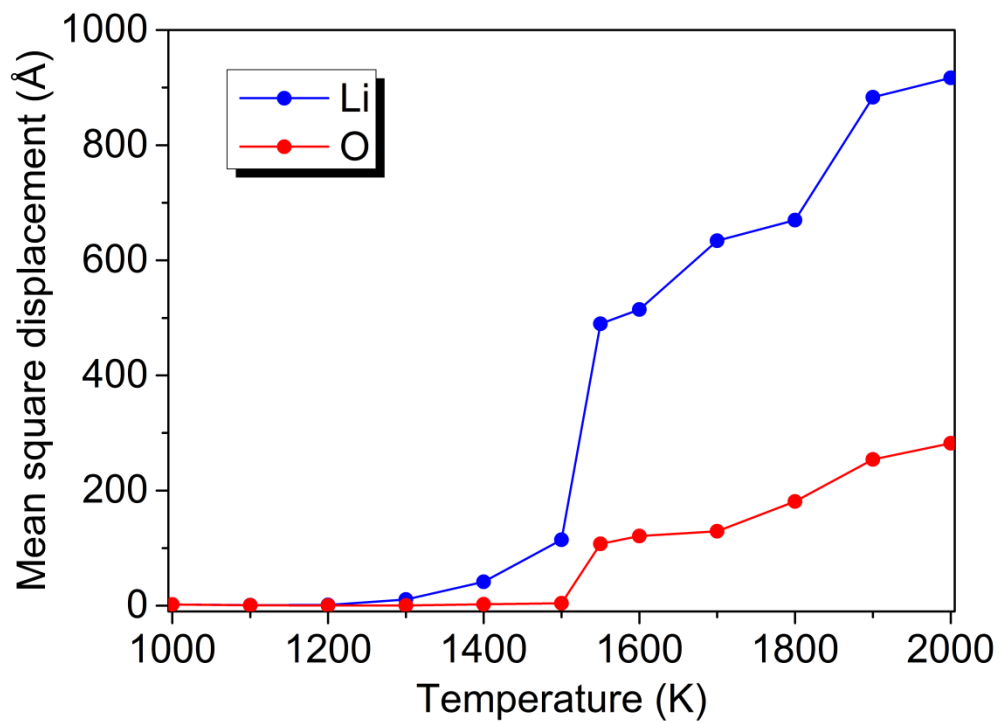


Figure 12. Mean square displacement of Li and O atoms during the accumulation stage of Monte Carlo run.